



Properties of fresh and hardened concrete

Konstantin Kovler^{a,*}, Nicolas Roussel^b

^a Technion – Israel Institute of Technology, Haifa, Israel

^b Laboratoire Central des Ponts et Chaussées, Paris, France

ARTICLE INFO

Article history:

Received 7 January 2011

Accepted 21 March 2011

Keywords:

Fresh concrete (A)

Hardened concrete

Portland cement (D)

Properties (C)

ABSTRACT

The present paper reviews the literature related to the properties of fresh and hardened concrete published after the previous (12th) International Congress on the Chemistry of Cement held in Montreal in 2007.

Workability and fundamental rheological properties, reversible and non-reversible evolution, thixotropy, slump loss, setting time, bleeding, segregation and practical issues related to formwork filling and pressure, are addressed among the properties of fresh concrete.

Among hardened concrete properties compressive strength and other mechanical and physical properties of hardened concrete, such as tensile strength, elastic properties, shrinkage, creep, cracking resistance, electrical, thermal, transport and other properties are covered. Testing, interpretation, modeling and prediction of properties are addressed, as well as correlation with properties of fresh concrete and durability, effects of special binders, recycled and natural aggregates, fiber reinforcement, mineral and chemical admixtures. Special attention is given to the properties of hardened lightweight and self-compacting concrete.

© 2011 Elsevier Ltd. All rights reserved.

Contents

1.	Introduction	776
2.	Properties of fresh concrete	776
2.1.	Workability and fundamental rheological properties	776
2.2.	Measurement of rheological properties	776
2.3.	Effect of time on fresh properties	777
2.3.1.	Reversible evolution and thixotropy	777
2.3.2.	Non-reversible evolution and slump loss	777
2.3.3.	Hydration and setting time	777
2.4.	Stability of fresh concrete	777
2.4.1.	Cement paste and bleeding	778
2.4.2.	Aggregates and segregation	778
2.5.	Fresh concrete properties and casting prediction tools	778
2.5.1.	Formwork filling	778
2.5.2.	Formwork pressure	778
3.	Properties of hardened concrete	779
3.1.	Testing and interpretation	779
3.2.	Modeling and prediction of properties	780
3.3.	Correlation with properties of fresh concrete and durability	780
3.4.	Effect of special binders	781
3.5.	Effect of recycled aggregates	781
3.6.	Effect of natural aggregates	783
3.7.	Effect of fiber reinforcement	783
3.8.	Effect of slag and pozzolanic additions	784
3.9.	Effect of chemical admixtures	785

* Corresponding author. Tel.: +972 4 8292971; fax: +972 4 8295697.

E-mail address: cvrkost@technion.ac.il (K. Kovler).

3.10. Properties of hardened light-weight concrete	786
3.11. Properties of hardened SCC	787
4. Summary and perspectives	788
References	789

1. Introduction

The present paper reviews the literature related to the properties of fresh and hardened concrete published after the previous (12th) International Congress on the Chemistry of Cement held in Montreal in 2007.

The paper has been prepared jointly by Konstantin Kovler and Nicolas Roussel, while the second author was in charge of the properties of fresh concrete, and the first author dealt with those of hardened concrete.

Workability and fundamental rheological properties, reversible and non-reversible evolution, thixotropy, slump loss, setting time, bleeding, segregation and practical issues related to formwork filling and pressure are addressed among the properties of fresh concrete.

Properties of hardened concrete cover compressive strength, tensile strength, elastic properties, shrinkage, creep, cracking resistance, electrical, thermal, transport and other properties.

Special attention is given to the aspects of testing concrete properties, interpretation of test results, modeling and prediction of properties, as well as to correlation with properties of fresh concrete and durability, effects of special binders, recycled and natural aggregates, fiber reinforcement, mineral and chemical admixtures, and properties of special concretes.

The authors admit that there is an obvious difference in style between the two sections dealing with fresh and hardened concrete. The reader has to take into account the big difference in quantity of literature relating to the two topics covered in the present paper, which has forced a different approach.

2. Properties of fresh concrete

2.1. Workability and fundamental rheological properties

Fresh concretes, as many materials in industry or nature, behave as yield stress fluids. There exists therefore a minimum value of the stress applied to the material for irreversible deformation and flow to occur. The behavior of fresh concrete in steady state is thus often approximated by a yield stress model of the following general form [1–4]:

$$\dot{\gamma} = 0 \rightarrow \tau < \tau_{00} \quad (1a)$$

$$\dot{\gamma} \neq 0 \rightarrow \tau = \tau_{00} + f(\dot{\gamma}) \quad (1b)$$

where τ_{00} (Pa) is the yield stress, $\dot{\gamma}$ (s^{-1}) the shear rate and f is a positive continuously increasing function of the shear rate with $f(0) = 0$. Concretes are often described as Bingham fluid with a plastic viscosity μ_p (Pa s), $f(\dot{\gamma}) = \mu_p \dot{\gamma}$ [1].

This behavior results from a complex interplay between numerous physical phenomena, the understanding of which is still ongoing [3,4]. It can be kept in mind at this stage that the broad poly-dispersity of concrete components implies at least four main types of interactions (surface forces (or colloidal interactions), Brownian forces, hydrodynamic forces and various contact forces between particles). Depending on the size of the particles, on their volume fraction in the mixture and on external forces (e.g. the magnitude of either the applied stress or strain rate), one or several of these interactions dominate [5,6].

From both a workability and practical point of view, yield stress may be associated to filling capacity and more generally to whether or not concrete will flow or stop flowing under an applied stress whereas plastic viscosity may be associated to the velocity at which a given concrete will flow once flow is initiated. It can be noted that, in the field of concrete casting unlike polymer or metal casting, the applied stress is mainly due to gravity.

Although measurements of plastic viscosity have several practical applications (pumping, casting rates...), yield stress is the most important parameter for formwork filling in practice [1,7]. During an industrial casting process, a purely viscous fluid (i.e. no yield stress) would self level under the effect of gravity and the viscosity of the material will dictate the time needed to obtain a horizontal surface. In the case of a yield stress fluid such as concrete, if the shear stress generated by gravity during casting, which is a complex function of formwork shape and local density of steel reinforcements, becomes lower than the yield stress of the concrete, flow may stop before the concrete self levels or before the formwork is entirely filled.

2.2. Measurement of rheological properties

Yield stress is a unique material property and may, in the case of cement pastes (i.e. fine particles), be measured using conventional rheological tools such as Couette Viscometer [8] or parallel plates rheometer [9]. In the case of fresh concrete because of the coarse aggregates, large scales rheometers had to be developed [10–12]. Even if, in situ, simpler and cheaper tests such as the slump test [13] are still often preferred, these apparatus represent a big step forward in the field of concrete science. However, there still exists a discrepancy between the various concrete rheometers [14,15]. Although they reach the same rheological classification of materials, they do not measure the same absolute values of the rheological parameters (i.e. τ_{00} and μ_p).

Concerning the measurement of yield stress, it has been demonstrated over the years that the result of the slump test, the most common industrial test for fresh concrete, can be correlated in specific conditions to the yield stress of a given concrete.

It is generally admitted that, similar to casting, during a slump test, flow stops when shear stress in the tested sample becomes equal to or smaller than yield stress [2]. Consequently the shape at stoppage is directly linked to the material yield stress. From a practical point of view, in civil engineering, two geometrical quantities may be measured, the “slump” or the “spread”. The slump is the difference between the height of the mold at the beginning of the test and after flow stoppage. The spread is the final diameter of the collapsed sample. In most of the applications of the ASTM Abrams cone, the initial height of which is 30 cm, the slump is measured if it is smaller than 25 cm, otherwise the spread is measured (slump flow test for SCC).

Following the pioneering work of Murata [2], subsequent works established analogous relationships either for conical or cylindrical molds [16–21]. However, in the case of some conical molds or in the case of high yield stress values (i.e. low slumps) with cylindrical molds, a systematic discrepancy between predicted and measured slumps was obtained. Two different regimes, one regime of low slumps and one regime of large spreads, were recently identified [22]. Two analytical solutions describing these asymptotic regimes, namely large height to diameter ratio or large diameter to height ratio, are

available in literature [23,24]. Numerical simulations of the slump test were also carried out for the ASTM Abrams cone [23]. An excellent agreement between predicted and measured slumps over a wide range of yield stress was obtained. It may be useful to remind here this correlation for slumps between 5 and 25 cm:

$$S = 25.5 - 17.6 \frac{\tau_{00}}{\rho} \quad (2)$$

with S the measured slump and ρ the density of the tested concrete.

2.3. Effect of time on fresh properties

2.3.1. Reversible evolution and thixotropy

In the case of many modern cementitious materials, the knowledge of the yield stress at the end of the mixing phase is not sufficient to describe the observed behavior from the concrete mixing plant to the casting phase. An evolution of the material rheological behavior is often noted during this time period. This evolution is mainly due to the thixotropic behavior of cementitious materials.

Several authors [25–34] have demonstrated that, when left at rest, concrete builds up an internal structure. Its apparent (or static) yield stress increases whereas, when flowing, the material fluidity increases at a rate which increases with the applied shear rate.

It has been shown recently in [29,30,34] that this evolution in the case of cement pastes can be correlated to the applied shear rate and to the recent flow history of the material. From a practical point of view, concrete often reaches its most destructured state during the mixing phase. According to its flow history between the mixing plant and the formwork (mixing truck, rest period, casting phase...), its apparent yield stress (or static yield stress) continuously evolves whereas its intrinsic yield stress (or dynamic yield stress), which is only linked to the mix design of the material, does not change.

From all of the above, it can be concluded that, in practice, a concrete is called thixotropic if it seems to build up a structure rather quickly at rest and becomes reversibly apparently more and more fluid while flowing. It has to be noted that, to be rigorously correct, all concretes, as a majority of mineral suspensions, are thixotropic. However, in the opinion of the present authors, it can be admitted that, in practice, a “thixotropic concrete” is a concrete displaying a rather short structuration characteristic time (typically several minutes) and a de-structuration characteristic time of several tens of seconds in the 1 to 10 s^{-1} shear rate range of industrial interest [34].

It has to be noted that, between the two aspects of thixotropy described here (structuration at rest and de-structuration under flow), the understanding and measuring of the first one is far more important from a practical point of view. In the potential points of practical interest such as formwork pressure, concrete is indeed not flowing. It is at rest and what really matters is the increase of its apparent yield stress. That is why recent approaches to quantify thixotropic behavior of fresh concrete have focused on the structuration phenomenon.

Billberg, in his recent work on thixotropy of SCC [31], has developed a very interesting method to measure the increase in apparent yield stress at rest. Measurements were performed using a concrete rheometer. Both static and dynamic yield stresses are measured in order to distinguish the reversible structuration due to thixotropy from the non-reversible evolution due to normal slump loss. Using this methodology, Billberg showed that apparent or static yield stress increases linearly with resting time. This was also reported in [34]. In both papers, the order of magnitude of the increase rate in yield stress was between 0.1 and 1.7 Pa/s . Finally, it can be noted that industrial methods allowing for simple, fast and cheap measurements of structuration rates have been recently developed [35].

2.3.2. Non-reversible evolution and slump loss

Unfortunately, in the case of concrete, things are more complex as hydration processes start as soon as cement and water are mixed together. The intrinsic or dynamic yield stress of the material is permanently and chemically evolving as described by Otsubo and co-workers [25] and Banfill [26]. Recently, Jarny and co-workers [32] have however shown using MRI velocimetry that, over short timescales, thixotropic (i.e. reversible) effects dominate while, over larger timescales, non-reversible processes dominate, which lead to irreversible evolutions of the behavior of the fluid. These two effects might in fact act at any time but, according to the above scheme, they appear to have very different characteristic times. As a consequence it is reasonable to consider that there exists an intermediate period, say around 30 min, for which irreversible effects have not yet become significant. This means that it seems possible to consider the effect of thixotropy and only thixotropy on short periods of time from the last strong remixing of the material (not more than 30 min as an order of magnitude) during which the irreversible evolutions of concrete can be neglected. When it is not the case, the material fluidity can strongly decrease and slump loss may be measured at an early stage of the casting process.

It can moreover be kept in mind that compatibility problems or delayed action of polymers may also be at the origin of slump loss or more generally dynamic yield stress evolution [36–39]. This complex topic at the boundary of physics and chemistry is however out of the scope of this paper.

2.3.3. Hydration and setting time

As discussed above, because of thixotropy and non-reversible effects, apparent yield stress is continuously increasing. It is now accepted that the flocculated structure of the cement grains is fixed just after mixing or remixing and that it does not change. Only the amplitude of the interaction force is changing with time. Moreover, no particular evolution occurs at the time of setting. Setting time of concrete is therefore only a technological parameter, defined according to standards [40].

Various empirical tests are used to study the hardening and setting of cementitious materials. These are sometimes alternatively described as consistency or setting time measurements. These tests include the Vicat needle, penetrometers of various shapes and the proctometer also known as the Proctor needle, as well as the Hilti nail gun [41]. Some of these techniques measure the penetration resistance (i.e. penetration force) under an imposed speed, while others measure the penetration depth for an imposed load.

The recent developments in ultrasound spectroscopy [42–47] and in oscillating rheometry [40,48] allows for the measurement of the evolutions of both shear and bulk elastic moduli during setting of cement paste. Based on these new techniques, recent papers showed the existence of a relation between shear yield stress and the empirical setting time measurements [40,49]. These correlations show that what is defined as initial setting time corresponds to a yield stress of the material of the order of a couple hundred kPa (to be compared to the few Pa or tens of Pa of a freshly mixed cement paste).

2.4. Stability of fresh concrete

Concrete is a multiphase material. The densities of the numerous components entering traditional concrete mix fitting vary between 1000 kg/m^3 (water) and 3200 kg/m^3 (cement). Even lighter material may be used in the case of lightweight concrete. With such a mixture, gravity quickly becomes the enemy of homogeneity. In the field of cementitious materials, heterogeneities induced by gravity are divided in two categories depending on the phase that is migrating: bleeding and segregation. Both are induced by the density difference between the components but bleeding phenomenon is concerned with water migration whereas segregation is concerned with the movement of the coarsest particles.

2.4.1. Cement paste and bleeding

Bleeding (i.e. the accumulation of water at the surface of the paste) of a potentially usable fluid cement paste shall be neglectable. It results from the difference in density between cement grains and water. Bleeding, in the range of interest of industrial cementitious materials, cannot be described as the settlement of individual cement grains in a dilute system but rather as a consolidation process (i.e. the upward displacement of water through a dense network of interacting cement grains) [50–52]. The interactions between cement grains and permeability of freshly mixed cement pastes are therefore first order parameters of a cement paste resistance to bleeding. The bleeding phenomenon can be slowed down by the viscous nature of the interstitial fluid, which has to travel to the surface under the effect of gravity. Viscosity agents can therefore be used to reduce the amplitude of bleeding before setting [53]. They are able to thicken the interstitial water and slow down the bleeding phenomenon. This may reduce the practical consequences of bleeding and make them neglectable from an industrial point of view.

2.4.2. Aggregates and segregation

Attempts to correlate rheology of fresh concrete to stability can be found in literature [54,55]. Figures linking either empirical test results or even quantitative measurement of segregation to slump or slump flow for a given concrete have often been plotted. Although a correlation may, in certain cases, be obtained, it has to be kept in mind that segregation is a multi-phasic separation phenomenon (the minimum number of phases is two: a suspending fluid and some solid inclusions). As such, the only relevant approach is a multi-phasic one. The rheological behavior of concrete has no role to play; only the rheological behavior of the suspending fluid(s) does matter. When correlations between concrete behavior and stability are measured, it is only because concrete behavior is strongly linked to the behavior of its suspending fluid(s).

Segregation (or stability) is often associated to static sedimentation. The particles settle in a given sample or in the formwork as their density is higher than the density of suspending fluid. However, it must not be forgotten that, if the inclusions density is lower than the suspending fluid density, the situation may be reversed. This is the case for instance for lightweight concretes. The physical phenomena are of course the same no matter the direction in which the particles are moving. Moreover, it must not be forgotten that some other reasons than gravity may induce segregation. Indeed, obstacles or confined flows may generate flow conditions in which the suspending fluid is not able to “carry” its particles.

It was shown in [56–58] that yield stress of the constitutive cement paste or mortar is the key parameter of concrete stability. Viscosity alone, although it plays a strong role in the dynamic segregation induced by flow [59], is not able to stabilize the coarsest particles at rest [57]. Thixotropy of the suspending phase (mortar or cement paste) can improve the ability of the material to stay homogenous during the “dormant” period until setting by increasing the apparent yield stress of the suspending phase.

2.5. Fresh concrete properties and casting prediction tools

A lot of work has been carried out in order to understand the correlation between mechanical properties and mix design and many tests have been developed in order to measure these mechanical properties (mechanical strength and delayed deformations for instance) but, on the other hand, many developments were also carried out in the field of structural engineering in order to correlate the needed properties of the concrete to be cast with the structure to be built. This last step has been missing for years in the fresh concrete properties field. Only recently, researchers have started to work on casting prediction tools.

It can be noted that this new research area has appeared at the same time as Self Compacting Concretes. This extremely fluid concrete was expected to be the answer to casting problems. However, it has to be kept in mind that, no matter how fluid a concrete is, there will always exist a formwork and steel bars configuration in which casting problems may occur.

2.5.1. Formwork filling

As discussed above, the ideal mix design of a fluid concrete is located somewhere between two opposite objectives. On one hand, concrete has to be as fluid as possible to ensure that it would fill the formwork under its own weight. On the other hand, it has to be a stable mixture. Therefore, a compromise between stability and fluidity has to be reached. The most straightforward approach is to find the minimum fluidity (or workability) that will guarantee the adequate filling of the formwork and assume that this minimum fluidity will ensure an acceptable stability. The only available method in the traditional toolbox of the civil engineer is to try various mix design and, for each of them, cast the real size element and choose the most suitable mixture (if there is one). This is expensive, time consuming and does not guarantee that an answer will be obtained. However, in the case of stable fluid concretes, the numerical tools of non-Newtonian fluid mechanics become available. They allow the numerical simulation of the casting phase and, for a very low economical cost, the determination of the minimum needed fluidity.

Mori and Tanigawa [60] first demonstrated the applicability of Viscoplastic Divided Element Method (VDEM) to simulate the flow of concrete in a reinforced beam section and the filling of a reinforced wall. Kitaoji et al. [61] confirmed the applicability of 2D VDEM to simulate the flow of fresh concrete cast into an unreinforced wall. The results of a form filling experiment in a vertical wall have also been compared with the corresponding 3D simulation [62]. The results show good correlation with respect to detection of free surface location, dead zones and particle paths.

Numerical simulations were also applied to an industrial casting of a very high strength concrete pre-cambered composite beam in [63]. The results of the simulations carried out for various values of the rheological parameters (Bingham model) helped to choose the target value of the minimum fluidity needed to cast the element. The numerical predictions were validated by experimental observations of two trial castings. Although the assumptions needed to carry out the simulations were over-simplistic, a satisfactory agreement was found between predicted and measured concrete flow.

It is the opinion of the present authors that, in the future, computational modeling of flow could become a practical tool allowing for the simulation of either total form filling as described above or detailed flow behavior such as particle migration, orientation of fibers and formation of granular arches between reinforcement (“blocking”) [64–67].

2.5.2. Formwork pressure

The consequences of thixotropy on casting processes are numerous but, in the last few years, for economic reasons, research has mostly focused on formwork pressure issues. In most of the current building codes or technical recommendations [68–71], the main parameters affecting formwork pressure during casting are the density of concrete, the formwork dimensions, the pouring rate of concrete, the temperature, and the type of binder and admixture.

However, it was recently demonstrated that, in the case of modern fluid concretes such as SCC, the thixotropic behavior of the material plays a major role [72–76]. It can be noted that this influence was in fact indirectly taken into account in the above semi-empirical technical recommendations via the effect of temperature and type of the binder, which are both strongly linked to the ability of the material to build up a structure at rest.

During placing, concrete behaves as a fluid but, as described above, if cast slowly enough or if at rest, it builds up an internal structure and has the ability to withstand the load from concrete cast above it without increasing the lateral stress against the formwork. It was demonstrated in [74,75] that, for a SCC confined in a formwork and only submitted to gravity forces, the lateral stress (also called pressure) at the walls may be less than the hydrostatic pressure as some shear stress is supported by the walls. It was also demonstrated that this shear stress reached the value of the yield stress, which itself increased with time because of thixotropy. Finally, if there is no sliding at the interface between the material and the formwork, the yield stress (not less or not more) is fully mobilized at the wall and a fraction of the material weight is supported (vertically) by the formwork. The pressure exerted by the material on the walls is then lower than the value of the hydrostatic pressure.

As apparent yield stress is increasing with time because of thixotropy and hydration, formwork pressure decreases. During casting, the increase in apparent yield stress allows for a reduction in pressure. This is in competition with the casting process, which, by increasing the concrete height in the formwork, increases formwork pressure. If the concrete is thixotropic or if the casting rate is sufficiently low, the effect of structural build up will dominate and pressure will be far lower than hydrostatic pressure. Inversely, for non thixotropic concrete and high casting rates, pouring will dominate and pressure will be close to hydrostatic pressure. Khayat has shown in [77] that most models proposed in literature were based on these two aspects and that they were all able to predict accurately formwork pressure allowing for a reduction in the formwork cost during a casting process.

3. Properties of hardened concrete

The present chapter reviews the literature related to the properties of hardened concrete published after the previous congress (the 12th International Congress on the Chemistry of Cement (Montreal, 2007)). The focus is given on compressive strength, which is considered as the main engineering property of concrete. The rest of mechanical and physical properties of hardened concrete, such as tensile strength, elastic properties, shrinkage, creep, cracking resistance, electrical, thermal, transport and other properties, are addressed as well.

A certain number of works addressing strength and other properties of hardened concrete have been published with the goal to develop new methods of testing, to interpret test results, to model and predict the development of properties in time or under specific mechanical or environmental loading. However, during preparation of the present state-of-the-art it was discovered that most of the papers on concrete properties address not the properties themselves, but rather their influence on numerous different factors (such as different type of loading, or introduction of chemical or mineral admixtures, recycled aggregates etc. into concrete mixes), or the properties of certain types of concrete, such as lightweight, self-compacting, fiber-reinforced, high-strength and other types of concrete. In view of this, the paper starts with the general review of hardened concrete properties and continues with reviewing of the properties of different types of concrete and of the effects caused by the replacement of conventional concrete constituents (Portland cement and aggregates) with new or special materials (including industrial by-products with cementitious or pozzolanic properties), or by their introduction to concrete mixes.

About 34,000 papers on properties of hardened concrete have been published in the years 2007–2010. This number exceeds by ~20% that in the 4 years preceded the previous (12th) International Congress on the Chemistry of Cement held in Montreal in 2007 (Fig. 1). As will be demonstrated in further sections, in some fields, such as in properties of hardened self-compacting concrete (SCC) and concrete made with recycled aggregates (RA), the real boom with publications has been observed in the last few years.

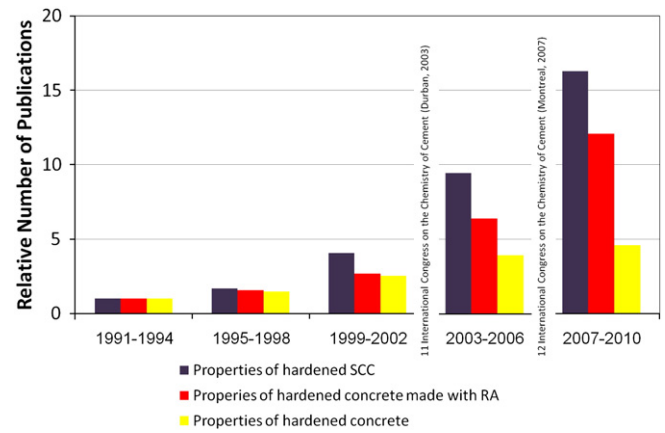


Fig. 1. Growth in publications on properties of hardened self-compacting concrete (SCC), concrete made with recycled aggregates and concrete in general.

3.1. Testing and interpretation

Mechanical concrete properties at high temperatures depend on many parameters. The main parameters are the specimen type and the test conditions. The report [78] describes the test parameters and test procedures for relaxation tests in the range of 20 to 750 °C.

The paper [79] describes microwave reflection and transmission properties measured from various sides of hardened mortar and concrete specimens with different water-to-cement (w/c) ratios. These properties are important in predicting/measuring accurate electrical properties of cement-based materials which can eventually be utilized in structural health monitoring, public safety, and propagation-related research.

The paper [80] proposes a critical analysis of the studies since the 1950s attempted to quantify the influence of specimen shape on the determination of concrete compressive strength, with special regard to the problem of conversion from cylinder to cube strength and vice versa. To obtain quantitative predictions and to investigate on the influence of the friction between the platens of the testing machine and the concrete specimen, uniaxial compressive tests are numerically simulated by using a nonlinear finite element model.

Accurate determination of the compressive strength of very high strength concrete is difficult due to large testing machine capacity requirements and the need for cylinder end preparation. An experimental program was conducted to determine whether alternate specimen types can be reliably used to determine the compressive strength of an ultra-high-performance fiber-reinforced concrete (UHPFRC) in the strength range from 80 to 200 MPa [81]. The 76 mm cylinders as well as the 70.7 and 102 mm cubes are found to be acceptable alternatives to the standard 102 mm cylinders. The 70.7 mm cube specimen is recommended for situations where machine capacity and/or cylinder end preparation are of concern.

The compressive strength of normal strength concrete at elevated temperatures up to 700 °C and the effect of cooling regimes were investigated and compared [82]. Strength loss was more significant on the specimens rapidly cooled in water.

Most standardization agencies allow small-cylinder specimens (100×200 mm) to be used in compressive strength concrete testing. Some engineers are still skeptical about using small cylinders, however, as they believe that compressive strength testing results from small cylinders are too varied. Limited studies have been conducted regarding the precision of small cylinders compared to precision studies for conventional cylinders (150×300 mm). The paper [83] describes the results of a comparative concrete testing program conducted by 15 laboratories in Edmonton, Canada, over the past 10 years.

An integrated software package for performing simulations of a number of engineering test measurements, including isothermal calorimetry, adiabatic temperature change, chemical shrinkage, elastic moduli, and compressive strength, has been developed recently [84].

In the work [85] a program of systematic laboratory testing has been undertaken to determine the effect of displacement rates and moisture contents on concrete strength, axial strain, lateral strain and acoustic emission. Findings from those results were used to conduct a detailed analysis of the crack closure, crack initiation, secondary cracking, crack damage and peak failure of dry, partially wet and fully wet concrete specimens at displacement rates corresponding to loading rates (0.05–0.25 mm/min). The strength of wet concrete was significantly reduced in comparison with the strength of dry specimens at the same displacement rate (e.g. 25% reduction at the loading rate of 0.15 mm/min), and this reduction depended on displacement rate.

Many nondestructive methods for strength gain monitoring seem to have limited capabilities in monitoring of the strength gain in a continuous manner. Electro-mechanical impedance (EMI) sensing technique utilizing smart piezoelectric materials can serve as a tool for the implementation of an online strength gain monitoring of early-age concrete [86].

In the works [87,88] an effort to extend the applicability of the EMI sensing technique is made for in situ strength gain monitoring of early age concrete.

3.2. Modeling and prediction of properties

In the study [89] waste rubberized aggregates were used as sand in mortar production which had two different sizes, 0–1 and 1–4 mm. Flexural and compressive strengths were determined and modeled by artificial neural network and fuzzy logic methods. It is concluded that the strength decreases considerably with the content of waste rubber aggregates. The same type of modeling was used in another work of the authors dealing with properties of concrete made with waste autoclaved aerated concrete aggregate [90].

The article [91] introduces genetic programming (GP) as a new tool for the formulations of properties of self-compacting concretes (SCC). The GP based formulation is found to be reliable, especially for hardened concrete properties (compressive strength, ultrasonic pulse velocity and electrical resistivity).

A finite element-based cohesive zone model was developed using bilinear softening to predict the monotonic load versus crack mouth opening displacement curve of geometrically similar notched concrete specimens [92]. The softening parameters for concrete material are based on concrete fracture tests, total fracture energy (G_F), initial fracture energy (G_F), and tensile strength (f_t), which are obtained from a three-point bending configuration.

In the study [93] compression strength and physical properties of the forty concrete carrot specimens taken from some buildings which collapsed by 1999 earthquakes were investigated and the correlations between compressive strength and physical properties (ultrasound velocity and Schmidt rebound) determined. The models tried to maximize using Genetic Algorithm (GA) and Linear Programming (LP) depending on specimens' properties.

The main purpose of the paper [94] was to propose an incorporating improved grammatical evolution (GE) into the genetic algorithm (GA), called GEGA, to estimate the compressive strength of high-performance concrete (HPC).

Ultrasonic pulse velocity technique is one of the most popular non-destructive techniques used in the assessment of concrete compressive strength. However, ultrasonic pulse velocity is affected by a number of factors, which do not necessarily influence the concrete compressive strength in the same way or to the same extent. The paper [95] deals with the analysis of such factors on the velocity–strength relationship. The relationship between ultrasonic pulse velocity, static and dynamic

Young's modulus and shear modulus was also analyzed. The influence of aggregate, initial concrete temperature, type of cement, environmental temperature, and w/c ratio was determined experimentally. The multi-layer feed-forward neural network was used for modeling the velocity–strength relationship.

Numerous empirical formulas have been developed for the relationship between concrete strength and w/c ratio. They are simple but have restricted limits of validity. A new type of strength formulas that have a second independent variable beside the w/c ratio, such as the cement content, or water content, or paste content, etc., is suggested in [96].

Various prediction models have been developed to predict the creep and shrinkage in concrete. RILEM has compiled the experimental studies which are stored in a computerized data bank [97]. Creep and shrinkage have been predicted up to 5000 days of observation by the ACI-209R-82 model, the B3 model, the CEB-FIP model code 1990, and the GL2000 model. Predicted values of creep and shrinkage were compared with the experimental results of Russell and Larson, in 1989, as well as the RILEM data bank. Prediction of creep and shrinkage by GL2000 model is found to be the closest to the experimental results.

Artificial neural networks (ANNs) were used to predict elastic modulus of both normal and high strength concrete [98]. The results predicted by ANN are also compared to those obtained using empirical results of the buildings codes and various models.

A micromechanics model for aging basic creep of early-age concrete is proposed in [99]. The viscoelastic boundary value problems on two representative volume elements, one related to cement paste (composed of cement, water, hydrates, and air), and one related to concrete (composed of cement paste and aggregates), have been formulated.

3.3. Correlation with properties of fresh concrete and durability

In several works an attempt to find a correlation between properties of hardened concrete, fresh concrete and durability, was undertaken. The following works can serve as an example.

The experimental study [100] examines the effects of mix design, formwork and consolidation on the quality of the surface of high w/c concrete. Pulse velocity, pull off strength and compressive strength were measured to evaluate the quality and mechanical properties of the hardened concrete. The results show that the rheological properties of fresh concrete can be correlated to the mechanical and permeation properties of the hardened concrete.

The experimental investigation on the frost-salt scaling resistance of air-entrained concrete containing CEM II/B-S 42.5N and CEM III/A 42.5N-HSR/NA slag-blended cements was performed in [101]. The mass of scaled material was increased for increased slag content, in spite of increased compressive and flexural strengths, decreased water absorption and water penetration depth. Increasing slag content resulted in a decrease of the total volume of air in hardened concrete and in a corruption of the air void system exhibited by a decrease of micropores content. The increase of mass of scaled material was proportional to the increase of the spacing factor of air voids, except for CEM III/A cement concrete exhibiting accelerated scaling.

The paper [102] provides an overview of the early-age properties of cement-based materials, from a materials science perspective. The major physical and chemical processes occurring at early ages are reviewed and strategies for mitigating early-age cracking are presented.

Concrete can crack during hardening, especially if shrinkage (including autogenous, thermal and drying components) is restrained. The concrete permeability due to this cracking may rise significantly and thus increase leakage and reduce durability. The restrained shrinkage ring test serves as an efficient tool to estimate

cracking sensitivity. Different modifications have been suggested recently to improve the estimation, such as introducing an integrated cracking potential criterion, based on time-to-cracking and stress rate at cracking [103], and creating the thermal strain effects by increasing the temperature of the brass ring (by a fluid circulation) in order to expand it [104].

3.4. Effect of special binders

This study [105] investigated the use of two kinds of waste from landfills, calcium carbide residue and fly ash (FA), as a low CO₂ emission concrete binder. Ground calcium carbide residue (CR) was mixed with original fly ash (OF) or ground fly ash (GF) at a ratio of 30:70 by weight and was used as a binder to cast concrete without Portland cement. The effects of FA finenesses and water to binder (W/B) ratios of CR–OF and CR–GF concretes on compressive strength, modulus of elasticity, and splitting tensile strength were investigated. The hardened concretes produced from CR–OF and CR–GF mixtures had mechanical properties similar to those of normal Portland cement concrete.

The paper [106] presents the engineering properties of inorganic polymer concretes (IPCs). The study includes a determination of the modulus of elasticity, Poisson's ratio, compressive strength, and the splitting tensile strength and flexural strength of IPCs, made with Class-F fly ash. IPC mix designs were adopted to evaluate the effects of the inclusion of coarse aggregates and granulated blast furnace slag into the mixes. The engineering properties of IPCs are close to those predicted by the relevant standards.

Hwangtoh-based alkali-activated concrete mixes were tested to explore the significance and limitations of the development of cementless concrete [107]. Hwangtoh, which is a kind of kaolin, was incorporated with inorganic materials, such as calcium hydroxide, to produce a cementless binder. The main variables investigated were the water–binder ratio and fine to total aggregate ratio. Compressive strength gain, splitting tensile strength, moduli of rupture and elasticity, stress–strain relationship, and bond resistance were measured. Test results show that the mechanical properties of hwangtoh-based concrete were significantly influenced by the water–binder ratio and to less extend by fine to total aggregate ratio.

3.5. Effect of recycled aggregates

The growth in publications on properties of hardened concrete made with recycled aggregates (RA), especially after the 11th International Congress on the Chemistry of Cement (Durban, 2003), is quite impressive. Fig. 1 shows that number of publications on this specific topic in the years since 2003 increased 3 times faster than in general. In most of these studies the new types of RA and their combinations were suggested and maximum replacement ratios of RA, which do not jeopardize mechanical properties of hardened concrete, were determined.

In the study [90], cylindrical compressive strength and ultrasound pulse velocity of hardened concrete were determined experimentally for concrete made with waste autoclaved aerated concrete aggregates. It is found that concrete lighter than crushed stone concrete can be produced by using this kind of RA.

Four different recycled aggregate concretes were produced in [108]; made with 0%, 25%, 50% and 100% of recycled coarse aggregates. The mix proportions were designed in order to achieve the same compressive strengths. Recycled aggregates were used in wet condition, but not saturated, to control their fresh concrete properties, effective w/c ratio and lower strength variability. The lower modulus of elasticity of recycled coarse aggregate concretes with respect to conventional concretes was found.

Mixed color waste recycled glass cannot be reused in glass industry. The research work [109] studied the feasibility of recycled glass sand (RGS) and pozzolanic glass powder (PGP) in concrete as

sand and cement replacement, respectively. Ground granulated blast furnace slag (GGBS) and metakaolin (MK) were used to replace Portland cement and investigate the effect of RGS on the behavior and properties of concrete. No significant differences were observed in compressive strength of concrete with RGS, while an average reduction of 16% was occurred when 20% of the Portland cement was replaced by PGP.

Test results of nine RA concretes and a control concrete using only natural aggregates are reported [110]. The replacement levels of both recycled coarse and fine aggregates were 30, 50, and 100%. Compressive and tensile strengths, moduli of rupture and elasticity, and free shrinkage were measured. The properties of hardened concrete were evaluated with respect to the relative water absorption of aggregates combining the quality and volume of RA. Test results showed that the properties of hardened concrete with RA depended on the relative water absorption of aggregates, and that the moduli of rupture and elasticity were lower than those calculated by the design equations of ACI 318-05, when the relative water absorption of aggregates is above 2.5% and 3.0%, respectively.

The paper [111] concerns the use of fine RA to partially or globally replace natural sand in the production of structural concrete. Compressive and splitting tensile strengths, modulus of elasticity and abrasion resistance are reported. It is shown that the use of fine RA does not jeopardize the mechanical properties of concrete, for replacement ratios up to 30%.

The paper [112] presents the results of a research program carried out in Portugal to evaluate the properties of concrete made with crushed bricks replacing natural aggregates. Compressive and tensile splitting strengths, modulus of elasticity and stress–strain behavior were investigated at w/c ratios of 0.45 and 0.5. The results of concrete produced with RA were compared with a reference concrete produced with natural limestone aggregates. Observed results indicate that ceramic residuals could be used as partial replacement of natural aggregates in concrete without reduction of concrete properties for 15% replacement and with reductions up to 20% for 30% replacement. The type and manufacturing process of bricks influence the properties.

The paper [113] presents the results of an experimental investigation carried out to evaluate the mechanical properties of concrete in which fine aggregate was partially (by 10, 20 and 30%) replaced with used-foundry sand (UFS), a by-product of ferrous and nonferrous metal casting industries. Compressive, splitting tensile and flexural strengths, and modulus of elasticity were determined at 28, 56, 91, and 365 days. Test results indicated a marginal increase in the strength properties of plain concrete by the inclusion of UFS.

In the study [114], the usage of ground elastic wastes such as rubber in SCC is investigated at the rubber replaced aggregate contents of 60, 120 and 180 kg/m³. Compressive strength, high temperature and freezing–thawing resistances of rubberized self-compacted concrete (RSCC) have been compared to the properties of ordinary SCC. It is shown that increase in RA content decreases compressive strength and durability. However, the different viscosity agents can provide appropriate results for RSCC containing the same rubber aggregate content, and the hardened properties of RSCC are better than the properties of ordinary concrete even if they are lower than the ones of SCC.

Different proportions of coarse aggregate materials were substituted by porcelain from sanitary installations in [115]. The results show that the concrete produced has the same mechanical characteristics as conventional concrete, thus opening a door to selective recycling of sanitary porcelain and its use in the production of concrete.

Using recycled waste expanded polystyrene foam (EPS) in lightweight concrete was studied in [116]. In this study, thermally modified waste EPS foams have been used as aggregate. Modified waste expanded polystyrene aggregates (MEPS) were obtained by heat treatment method by keeping waste EPS foams in a hot air oven

at 130 °C for 15 min. MEPS aggregate was used as a replacement of natural aggregate, at the levels of 0, 25, 50, 75 and 100% by volume. The 28-day compressive strengths of MEPS concrete range from 12.58 to 23.34 MPa, which satisfies the strength requirement of semi-structural lightweight concrete.

The objective of the study [117] is to investigate the strength of concrete made with coarse RA. The variables that are considered in the study include the recycled concrete and target concrete strength. The toughness and soundness test results of the RA coarse aggregate concrete showed higher loss than in concrete with natural aggregate, but remained within the acceptable limits. The compressive and splitting tensile strengths of concrete made with recycled coarse aggregate depend on the mix proportions. It is found that the strength of recycled concrete can be 10–25% lower than that of conventional concrete.

In the work [118] the effect of crusher dust replacement levels of fine aggregate and hooked-end steel fibers with different aspect ratios and different volumes on some properties of concrete was investigated. The mixes were tested for compressive and splitting tensile strength, water penetration, flexural toughness energy and impact energy. Compressive and splitting tensile strength, water penetration depth, flexural toughness and impact energy for different dust replacement level and fiber reinforcement index were determined.

The utilization of the waste marble dust (MD) in self-compacting concrete (SCC) as filler material was the main objective of the study [119]. MD replaced binder of SCC at contents of 0, 50, 100, 150, 200, 250 and 300 kg/m³. Compressive and flexural strength, ultrasonic velocity, porosity and compactness are determined at the end of 28 days for the hardened concrete specimens. It is concluded that workability of fresh SCC was not affected up to 200 kg/m³ MD content, and the mechanical properties of hardened SCC decreased by using MD at the contents exceeding 200 kg/m³.

Ultra-high performance fiber reinforced concrete (UHPFRC) is known for its outstanding mechanical performance. In the paper [120] several possibilities are examined for reducing the price of producing UHPFRC and for bringing UHPFRC away from solely precast applications and onto the construction site as an in situ material. Recycled glass cullet and two types of local natural sand were examined as replacement materials for the more expensive silica sand normally used to produce UHPFRC. In addition, curing of UHPFRC cubes and prisms at 20 °C and 90 °C has been investigated to determine differences in mechanical properties. The results showed that the use of recycled glass cullet (RGC) yields ~15% lower flexural strength, compressive strength and fracture energy. Specimens cured at 20 °C give approximately 20% lower compressive strength, 10% lower flexural strength and 15% lower fracture energy than specimens cured at 90 °C from 1 to 7 days.

The effects of aggregate-to-cement (A/C) ratios and types of aggregates on the properties of pre-cast concrete blocks are evaluated in [121]. A/C ratios between three and six and three types of aggregates (i.e., natural crushed aggregate (NCA), recycled crushed aggregate (RCA) and recycled crushed glass (RCG)) were used in the experiments. It was found that the compressive strength of the paving blocks decreased as the A/C ratio increased. The results showed that the strength was directly proportional to the crushing strength of the aggregates (i.e., 10% fines value). Moreover, the water absorption of the blocks had a good correlation with the water absorption ability of the aggregate particles. The use of RCA as a replacement of NCA in the production of concrete blocks reduced the density and strength but increased the water absorption of the blocks. However, the potential high water absorption of the blocks as a result of the incorporation of RCA could be ameliorated by the use of RCG since RCG particles had a low water absorption value.

Environmental and economic factors are increasingly encouraging higher value utilization of demolition debris. Hence, an experimental study was undertaken to explore the feasibility and potential of using

field-demolished concrete as full replacement of natural aggregates to produce high strength concrete (HSC) [122]. The mechanical properties of hardened concrete made with WCAs were investigated. The preliminary results indicated that HSC with up to 80 MPa of 28-day compressive strength made with field-demolished concrete as coarse aggregates and natural sand as fine aggregates can be obtained with the facilitation of a modified mixing method and addition of silica fume.

A novel triple mixing method (TM) was developed to realize surface-coating of aggregate with pozzolanic materials for further improving microstructure of interfacial transition zone (ITZ) and properties of RA concrete [123]. Effects of mixing method and coating by various admixtures on compressive strength and chloride ions penetration resistance of RA concrete were investigated. Through preparing the new–old–new concrete sandwich specimen and SEM observation of the old concrete surface after fracture, effect of surface-coating of the recycled aggregate (RA) in RAC with various admixtures on ITZ microstructure was studied. The results showed that properties of RAC can be further enhanced by using TM, as compared to that of using the double-mixing method (DM). Through SEM observation, it is revealed that the coated pozzolanic particles can consume CH accumulated in the pores and on the surface of the attached mortar to form new hydration products, which cannot only in situ strengthen the RA, but further improve the microstructure of the ITZ, thus the strength and durability of the RAC was further enhanced.

The paper [124] reports the results of an experimental program aimed to examine the performance of concrete produced with washed glass sand (WGS), as natural sand substitute by mass. The effects of up to 50% WGS on fresh, engineering and durability related properties have been established and its suitability for use in a range of normal-grade concrete production assessed. WGS characteristics results showed that the post-container glass waste can be crushed to provide WGS of physical properties that satisfy the current requirements set in appropriate standards for natural sand for concrete. The density and water absorption of WGS was found to be lower than natural sand. Studies of hardened concrete properties, comprising bulk engineering properties (compressive cube and cylinder strength, flexural strength, modulus of elasticity, and drying shrinkage) and durability (near surface absorption and alkali silica reaction) showed similar performance for concrete produced with natural aggregates and up to 15% WGS.

Low grade RA obtained from a construction waste sorting facility were tested to assess the feasibility of using these in the production of concrete blocks [125]. The characteristics of the sorted construction waste are significantly different from that of crushed concrete rubbles that are mostly derived from demolition waste streams. This is due to the presence of higher percentages of non-concrete components (e.g. >10% soil, brick, tiles, etc.) in the sorted construction waste. In the study reported in this paper, three series of concrete block mixtures were prepared by using the low grade recycled aggregates to replace (i) natural coarse granite (10 mm) and (ii) 0, 25, 50, 75 and 100% replacement levels of crushed fine aggregate (granite <5 mm) in the concrete blocks. Density, strength and drying shrinkage as well as strength reduction after exposure to 800 °C are presented. The results show that the soil content in the recycled fine aggregate was an important factor in affecting the properties of the blocks produced and the mechanical strength decreased with increasing low grade recycled fine aggregate content. But the higher soil content in the recycled aggregates reduced the reduction of compressive strength of the blocks after exposure to high temperature due probably to the formation of a new crystalline phase. The results show that the low grade recycled aggregates obtained from the construction waste sorting facility has potential to be used as aggregates for making non-structural pre-cast concrete blocks.

Reuse of waste from construction and demolition is one of the most important purposes in the world. One of the most important

wastes, due its wide range of reuse possibilities, is ceramic waste from the construction and ceramic industry. The aim of the research [126] was to investigate some of the physical and mechanical properties of a laboratory-produced concrete to which had been added varying proportions of white ceramic powder as fine aggregate, obtained from the demolition site rubble and from the waste of ceramic industries. Initial experiments were carried out to characterize the ceramic powder and its suitability as fine aggregate. Thereafter, the results of the concrete trials (compression, flexi-traction and Brazilian test) show that the concrete thus obtained has the same mechanical characteristics as that made with conventional sand.

The purpose of the paper [127] is to provide new data related to the field of recycled concrete in Spain. In keeping with this, several procedures were established, on the basis of which conclusions have been drawn regarding the suitability or non-suitability of recycled aggregates in Spain. Standard tests were carried out to determine the density, water absorption, grading, shape index, flakiness index and fragmentation resistance. Subsequently, proportion parameters were defined for average performance fresh and hard concrete made with these aggregates. These parameters were used to produce conventional concrete (CC) and conventional concrete with silica fume (CCS). The mixes were then adjusted for the production of recycled concrete (RC) and recycled concrete with silica fume (RCS) both containing 50% recycled coarse aggregates. Tests were conducted to determine the properties—both physical (density and water absorption) and mechanical (compressive and tensile splitting strength and static modulus of elasticity).

The use of high percentages of recycled aggregates in concrete would usually worsen the concrete properties. The paper [128] tries to address the deficiency of the use of recycled aggregates by systematically presenting results on the influence of incorporating Class F fly ash on concrete properties. In this study, two series of concrete mixtures were prepared with water-to-binder (W/B) ratios of 0.45 and 0.55. The recycled aggregate was used as 0, 20, 50, and 100% by weight replacements of natural aggregate. In addition, fly ash was used as 0, 25, and 35% by weight replacements of cement. The results showed that the compressive strengths, tensile strengths, and static modulus of elasticity values of the concrete at all ages decreased as the recycled aggregate and the fly ash contents increased. Further, an increase in the recycled aggregate content decreased the resistance to chloride ion penetration and increased the drying shrinkage and creep of concrete. Nevertheless, the use of fly ash as a substitute for cement improved the resistance to chloride ion penetration and decreased the drying shrinkage and creep of the recycled aggregate concrete. The results showed that one of the practical ways to utilize a high percentage of recycled aggregate in structural concrete is by incorporating 25–35% of fly ash as some of the drawbacks induced by the use of recycled aggregates in concrete could be minimized.

The effects of recycled glass (RG) cullet on fresh and hardened properties of self-compacting concrete (SCC) were investigated [129]. RG was used to replace river sand (in proportions of 10%, 20% and 30%), and 10 mm granite (5%, 10% and 15%) in making the SCC concrete mixes. Fly ash was used in the concrete mixes to suppress the potential alkali–silica reaction. The experimental results showed that the compressive and tensile splitting strengths, static modulus of elasticity, drying shrinkage of the RG–SCC mixes were decreased with an increase in recycled glass aggregate content; however the resistance to chloride ion penetration increased. The results showed that it is feasible to produce SCC with recycled glass cullet.

The paper [130] addresses experiments on earth-moist concrete (EMC) based on the ideas of a new mix design concept. It is shown that by means of an optimized particle packing, stone waste materials can be used to reduce the amount of the most cost intensive materials in earth-moist concrete mixes, viz. binder and filler.

Recycling and reuse of building rubble present interesting possibilities for economy on waste disposal sites and conservation

of natural resources. The paper [131] examines the possibility of using crushed brick as coarse and fine aggregate for a new concrete. Either natural sand, coarse aggregates or both were partially replaced (25, 50, 75 and 100%) with crushed brick aggregates. Compressive and flexural strengths up to 90 days of age were compared with those of concrete made with natural aggregates. Porosity, water absorption, water permeability and shrinkage were also measured. The test results indicate that it is possible to manufacture concrete containing crushed bricks (coarse and fine) with characteristics similar to those of natural aggregates concrete, provided that the percentage of recycled aggregates is limited to 25 and 50% for the coarse and fine aggregates, respectively.

3.6. Effect of natural aggregates

The use of limestone in the construction industry has been increasing due to benefits as aggregate. Some of these benefits include good strength, low possibility of alkali–silica reaction and the decrease in drying shrinkage in concrete. The research [132] discusses the consumption and general characteristics of the limestone aggregate in USA and Japan. Then experiments were conducted on mixtures of different proportions of fine limestone and sand at different water/cement (w/c) ratios. The w/c ratios selected were 45%, 55% and 65% with fine limestone replacements of 0%, 30%, 50% and 100%. The water absorption and porosity of fine limestone and sand were measured to find a relation with the water entrapped in the pores of the surface of the rock and the drying shrinkage. The results show the increases in the compressive and flexural strengths and modulus of elasticity when the fine limestone proportion increases in the mixture. The most outstanding results are found on the drying shrinkage, which decreases considerably with the increase in fine limestone proportions.

The paper [133] examines the influence of aggregate type (gabbro, basalt, quartzite, limestone and sandstone) on strength and abrasion resistance of high strength silica fume concrete. Gabbro concrete showed the highest compressive and flexural tensile strength and abrasion resistance, while sandstone showed the lowest values. High abrasion resistant aggregate produced a concrete with high abrasion resistance. Three-month compressive strengths of concretes made with basalt, limestone and sandstone were found to be equivalent to the uniaxial compressive strengths of their aggregate rocks. However, the concretes made with quartzite and gabbro aggregate showed lower compressive strength than the uniaxial compressive strength of their aggregate rocks.

In the study [134] the relationships between methylene blue values of the concrete samples produced with the aggregates from different quarries, and ultrasonic pulse velocity, compressive strength, and surface abrasion resistance were investigated. Tests were done to determine the quality of microfine material (i.e., passing 0.063 mm sieve). It is shown that clay content, as indicated by the methylene blue value test, affects the concrete properties, but the microfine material percentage does not relate to the clay content.

The work [135] describes the influence of dredged marine sand (DMS) on the properties of concrete in experimental sections of a harbor pavement. It is shown that the hardened properties of concretes made with DMS approached the results of the control concrete.

3.7. Effect of fiber reinforcement

Effect of fiber reinforcement on the properties of hardened concrete continued to draw attention of the researchers, while many publications dealt with synthetic structural fibers, hybrid fibers and combination of fiber reinforcement and pozzolanic additions. The following studies illustrate these research activities.

The study [136] analyzes the impact of polypropylene fibers on mechanical properties of hardened lightweight self-compacting concrete (compressive strength with elapsed age, splitting tensile strength, elastic modulus and flexural strength). Polypropylene fibers did not influence the compressive strength and elastic modulus, however applying these fibers at their maximum percentage volume increased the tensile splitting and flexural strengths by 14.4% and 10.7%, respectively.

Concretes produced with three different replacement ratios of fly ash and three different types of steel and polypropylene fibers were compared to those without fibers in concrete with FA [137]. It is shown that fibers provide better concrete performance, while fly ash may adjust workability and strength losses caused by fibers, and improve strength gain.

The paper [138] presents results of an experimental investigation carried out to study the properties of plain concrete and steel fiber reinforced concrete containing fibers of mixed aspect ratio. Compressive, tensile splitting and flexural strengths were determined in concrete incorporated 1.0, 1.5 and 2.0% of corrugated steel fibers, each volume fraction incorporated mixed steel fibers of size $0.6 \times 2.0 \times 25$ mm and $0.6 \times 2.0 \times 50$ mm in different proportions. Complete load deflection curves under static flexural loads were obtained and the flexural toughness indices were obtained by ASTM C-1018 as well as Japanese Concrete Institute (JCI) method. A fiber combination of 65% 50 mm + 35% 25 mm long fibers was the most appropriate combination for compressive and tensile strengths. However, better workability was obtained as the percentage of shorter fibers increased.

The paper [139] studies high strength concrete reinforced with hybrid fibers (combination of hooked steel and a non-metallic fiber) up to a volume fraction of 0.5%. The mechanical properties (compressive, tensile splitting and flexural strengths and flexural toughness) were studied for concrete with different hybrid fiber combinations—steel–polypropylene, steel–polyester and steel–glass. The flexural properties were studied using four point bending tests on beam specimens as per JCI recommendations. Fiber addition was seen to enhance the pre-peak as well as post-peak region of the load–deflection curve, causing an increase in flexural strength and toughness, respectively. Addition of steel fibers generally contributed towards the energy absorbing mechanism (bridging action), whereas the non-metallic fibers delayed microcracking. Flexural toughness of steel–polypropylene hybrid fiber concretes was comparable to that of steel fiber concrete. Increased fiber availability in the hybrid fiber systems (due to the lower densities of non-metallic fibers), in addition to the ability of non-metallic fibers to bridge smaller micro cracks, are suggested as a tool for the enhancement of mechanical properties.

The paper [140] presents a study of a fiber reinforced self-compacting concrete incorporating high-volume fly ash that does not meet the fineness requirements of ASTM C 618. A polycarboxylic-based superplasticizer was used in combination with a viscosity modifying admixture. In mixtures containing fly ash, 50% of cement by weight was replaced with fly ash. Two different types of steel fibers were used in combination, keeping the total fiber content constant at 60 kg/m^3 . Compressive and splitting tensile strengths and ultrasonic pulse velocity were determined. The results indicated that high-volume coarse fly ash can be used to produce fiber reinforced SCC, although some strength is lost because of high-volume coarse fly ash.

3.8. Effect of slag and pozzolanic additions

The use of slag and pozzolanic additions in concrete is an important subject and is growing in importance day by day. Supplementary cementitious materials (SCM) have become an integral part of high strength and high performance concrete mix design. These may be naturally occurring materials, industrial wastes, or byproducts or the ones requiring less energy to manufacture. Some

of the commonly used supplementary cementing materials are coal fly ash (FA), silica fume (SF), ground granulated blast furnace slag (GGBS), rice husk ash (RHA) and metakaolin (MK). SCM with cementitious or pozzolanic properties may both provide economical advantages and improve concrete quality and durability.

The paper [141] presents experimentally investigated the effects of pozzolan made from various by-product materials on mechanical properties of high-strength concrete. Ground pulverized coal combustion FA, ground fluidized bed combustion fly ash (FB), ground rice husk–bark ash (RHBA), and ground palm oil fuel ash (POFA) having median particle sizes less than $11 \mu\text{m}$ were used to partially replace Portland cement. The results suggest that concretes containing FA, FB, RHBA, and POFA can be used as pozzolanic materials in making high-strength concrete with 28-day compressive strengths higher than 80 MPa. After 7 days of curing, the concretes containing 10–40% FA or FB and 10–30% RHBA or POFA exhibited higher compressive strengths than that of the control concrete. The use of FA, FB, RHBA, and POFA to partially replace Portland cement has no significant effect on splitting tensile strength and modulus of elasticity as compared to control concrete or silica fume concretes.

The paper [142] presents the results of an experimental investigation on the properties of fly ash concrete incorporating either hydrated lime or silica fume to improve early strength. The addition of both improved the early age compressive strength of fly ash concrete. The inclusion of silica fume was also found to increase the 28 days strength significantly. The air permeability of concrete containing lime and silica fume either decreased or remained almost the same. The addition of lime and silica fume improved the sorptivity of concrete. The mercury intrusion porosimetry data confirmed the beneficial action of hydrated lime and silica fume, towards decreasing the total pore volume of fly ash cement paste.

RHA were used as pozzolanic admixtures for high performance concrete (HPC) [143]. The study reports on a chemical treatment before burning that improves the effectiveness of the RHA. The resulting ash (ChRHA) was compared to ash produced by conventional incineration (TRHA). The digestive chemical treatment before burning produced an RHA with properties comparable to SF. The ChRHA was highly amorphous, white in color, presented higher specific surface area and exhibited greater pozzolanic activity. The hardened properties of HPC made with different percentages of these RHAs (modulus of elasticity, compressive and flexural strengths) were compared. It is shown that ChRHA and TRHA are effective supplementary cementitious materials, although concrete mixes required higher dosages of superplasticizer compared to the control mix.

The paper [144] presented herein investigates the effects of using supplementary cementitious materials in binary, ternary, and quaternary blends on the hardened properties of self-compacting concretes (SCCs). A total of 22 concrete mixtures were designed having a constant water/binder ratio of 0.32 and total binder content of 550 kg/m^3 . The control mixture contained only Portland cement (PC) as the binder while the remaining mixtures incorporated binary, ternary, and quaternary cementitious blends of PC, FA, GGBS and SF. Compressive strength, ultrasonic pulse velocity, and electrical resistivity of the hardened concretes were measured. Test results show that the compressive strength and electrical resistivity of concretes with SF and GGBFS were much higher than those of the control concrete.

In the study [145] RHA prepared from the boiler burnt husk residue of a particular rice mill has been evaluated for optimal level of replacement as blending component in cements. The properties of concrete include compressive strength, splitting tensile strength, water absorption, sorptivity, total charge-passed derived from rapid chloride permeability test (RCPT) and rate of chloride ion penetration in terms of diffusion coefficient. This particular RHA consists of 87% of silica, mainly in amorphous form and has an average specific surface

area of 36.47 m²/g. Test results obtained in this study indicate that up to 30% of RHA could be advantageously blended with cement without adversely affecting the strength and permeability properties of concrete. Another interesting observation is the linear relationship that exists among water sorptivity, chloride penetration and chloride diffusion.

The paper [146] presents an overview of the work carried out on the use of metakaolin as partial replacement of cement in mortar and concrete. Properties reported in this paper are pore size distribution, water absorption and sorptivity, compressive, tensile and bending strengths, micro-hardness and relative strength.

Although the capability of metakaolin as pozzolanic material to improve mechanical and durability properties of concrete if used as partial replacement of PC is well noted in concrete science, its utilization in building industry is still limited, mainly due to its high price dictated by the low production amounts. However, with the current shortage of SF and high-quality slag in some countries the attitude of concrete producers to metakaolin may change in the near future. The experimental results obtained in [147] show that the replacement of PC by 10% of MK leads in most cases either to improvements or at least does not significantly impair substantial properties of the analyzed HPC. Basic physical properties and heat transport and storage properties are very similar to common HPC, mechanical properties after 28 days are slightly worse but later improved, water- and water vapor transport parameters are substantially reduced, frost resistance is better, resistance against de-icing salts is slightly worse but still meets well the required criteria. The chemical resistance of concrete with 10% of MK instead of PC in distilled water and HCl is found better than for PC concrete, in MgCl₂ it is slightly worse, and in NH₄Cl, Na₂SO₄ and CO₂ almost the same, carbonation is reduced, and chloride binding capacity is increased.

A wide set of parameters of concrete containing 10% of GGBS as PC replacement involving basic material characteristics, mechanical and fracture-mechanical properties, durability characteristics, hygral and thermal properties and chloride binding characteristics was determined in [148]. The experimental results show that the replacement of Portland cement by even such a low amount of ground granulated blast furnace slag as environmental more friendly and still valuable alternative binder either affects positively or at least does not worsen in a significant way the substantial properties of hardened concrete. The mechanical properties are found to be very similar as compared to the reference mix, the liquid water transport parameters of the mix containing slag are significantly better, the basic durability characteristics such as the frost resistance and corrosion resistance similar and very good, the resistance against de-icing salts slightly worse. These findings may be significant for the future use of slag in the countries where its availability decreases.

The work [149] studied mechanical properties and seawater resistance of the concrete incorporating GGBS and ground basaltic pumice (GBP), at different replacement levels of fine aggregate by GBS and/or GBP. Compressive strength measured on 150 mm cubes was used to assess the changes in the mechanical properties of concrete specimens exposed to seawater attack for 3 years. The effects of exposure were determined by direct measurement of the mass loss of steel bars, embedded in the mortar after 1, 2 and 3 years. The abrasion of concrete was also determined according to mass loss of specimens. The test results showed that the presence of GGBS and GBP had a beneficial effect on the compressive strength loss due to seawater attack, abrasion resistance and corrosion percentage. This improvement can be explained partly by the decrease in the permeability of the specimen and partly by the seawater resistance of the additives. The results allow predicting durability of concrete depending on the types and amount of additives.

A laboratory study on the influence of the combination of ultrafine fly ash (UFFA) and SF on the properties of fresh and hardened concrete is described [150]. Also compared are the performance of

concrete incorporating UFFA and SF (ternary blend of cement), concrete incorporating UFFA or SF (binary blend of cement), and control Portland cement concrete. The test results show that the incorporation of SF or UFFA in concrete resulted in higher strength and improved durability (resistance to chloride penetration). These benefits were found to be more pronounced in the SF concrete. However, the SF concrete demonstrated several limitations such as low slump and high early-age shrinkage. These limitations were not observed in the UFFA concrete; addition of UFFA increased the slump and decreased the early-age shrinkage. To minimize the shortcomings of SF without losing its strength and durability benefits, a concrete mixture incorporating both SF and UFFA was prepared. The test results show that the incorporation of both SF and UFFA produces a concrete mixture that demonstrates high early-age strength and improved durability similar to those properties in SF concrete. In addition, unlike SF concrete, the new concrete mixture demonstrates a higher level of slump and a lower level of free shrinkage.

The effect of high temperatures on mechanical properties of normal and high strength concretes with and without SF was investigated, and image analysis was performed on split concrete surfaces to see the change in aggregate-mortar bond strength [151]. Specimens were heated up to elevated temperatures (50, 100, 150, 200, and 250 °C) without loading, and the residual compressive and splitting tensile strengths, as well as the static modulus of elasticity were determined. For normal strength concrete residual mechanical properties started to decrease at 100 °C, while using SF reduced the losses at high temperatures. In terms of percent residual properties, high strength concrete performed better than normal strength concrete. Image analysis of the split surfaces was used to investigate the effect of high temperatures on the aggregate-mortar bond strength, and the results showed that reduced w/c ratio and the use of SF improved the bond strength at room temperature, and created more stable bonding at elevated temperatures up to 250 °C.

The study [152] investigates the properties and hydration of blended cements with steelmaking slag, a by-product of the conversion process of iron to steel. For this purpose, a reference sample and three cements containing up to 45% w/w steel slag were tested. The steel slag fraction used was the "0–5 mm", due to its high content in calcium silicate phases. Initial and final setting time, standard consistency, flow of normal mortar, autoclave expansion and compressive strength at 2, 7, 28 and 90 days were measured. The hydrated products were identified by X-ray diffraction while the non-evaporable water was determined by TGA. The microstructure of the hardened cement pastes and their morphological characteristics were examined by scanning electron microscopy. It is concluded that slag can be used in the production of composite cements of the strength classes 42.5 and 32.5 of EN 197-1. In addition, the slag cements present satisfactory physical properties. The steel slag slows down the hydration of the blended cements, due to the morphology of contained C₂S and its low content in calcium silicates.

3.9. Effect of chemical admixtures

The influence of a new organic surface-applied corrosion inhibitor (SACI) on selected concrete properties is studied including compressive strength, tensile strength, steel–concrete bond strength, permeability, drying shrinkage, and freeze–thaw resistance [153]. The inhibitor is an aminoalcohol-based (AMA) corrosion inhibitor and it is applied on the hardened concrete surface. The results show that the inhibitor can be used safely and it does not have any significant harmful effect on the properties of hardened concrete and it improves some properties of concrete with its pore-blocking effect.

Lignosulfonate-based air-entraining (AE) water-reducing agents have been used in various concrete structures for over 50 years. Polycarboxylate-based superplasticizers, which are the main superplasticizers in use today, have been on the market for 20 years and

have recently been applied to various kinds of concrete structures. Therefore, it is important to know the difference that these three dispersants (lignosulfonate-based (LG), B-naphthalenesulfonate-based (BNS), and polycarboxylate-based (PC)) have on concrete durability. The authors, using superplasticizers containing each dispersant, studied the properties of concrete at a w/c of 0.50 up to the age of 20 years [154]. This paper discusses the experimental results up to the age of 3 years following standard curing and artificial sea water curing, and under normal external exposure and exposure in a splash zone. As a result, no major difference has been observed in the effect on properties of the hardened concrete between PC and BNS, dispersants in superplasticizers. In addition, the authors consider that concrete incorporating PC-based superplasticizer or BNS-based superplasticizer has equal durability to that of concrete incorporating an AE water-reducing agent, most of which is in service over the long term.

An experimental investigation was conducted to evaluate the influence of elevated temperatures on the mechanical properties, phase composition and microstructure of SF concrete [155]. The blended cement used in this investigation consists of ordinary Portland cement (OPC) and SF. The OPC were partially replaced by 0, 5, 10, 15 and 20% of SF. The blended concrete paste was prepared using the water–binder ratio of 0.5 wt.% of blended cement. The fresh concrete pastes were first cured at 100% relative humidity for 24 h and then cured in water for 28 days. The hardened concrete was thermally treated at 100, 200, 400, 600 and 800 °C for 2 h. The compressive strength, indirect tensile strength, phase composition and microstructure of SF concrete were compared with those of the pure OPC. The results showed that the addition of SF to OPC improves the performance of the produced blended concrete when exposed to elevated temperatures up to 400 °C.

This state-of-the-art report [156] is focused on corrosion inhibitors used in concrete and is based on published studies in the last decade. Emphasis was given to the most commonly used inhibitors such as aminoalcohols (AMAs), calcium nitrites (CN) and sodium monofluorophosphates (MFPs). The report presents information related to (a) basic mechanism study, which gives information about the mechanism of protection provided by inhibitors, (b) effectiveness of inhibitors against corrosion in chloride contaminated and carbonated concrete, which deals with the preventive and curing effect of the inhibitors in different environments, (c) penetrability of the inhibitor, which underlines some difficulties of penetration into concrete for migrating corrosion inhibitors (MCIs), (d) influence on fresh and hardened concrete properties, which compares fresh concrete properties, mechanical performance and durability with and without inhibitor, and (e) field trials, which gives the limited data on the long-term performance of the inhibitors in real structures.

3.10. Properties of hardened light-weight concrete

The influence of surfactant concentration and pozzolanic amorphous nanodispersive SiO₂ (ANS) additive on formation of autoclaved aerated concrete (AAC) structures and properties was investigated in [157]. It was established that in the AAC forming mixture the replacement of 1.0% milled sand by ANS accounts for considerably higher crystallinity of hardened binding material, and that the plate-like shape of crystals generated in this case is typical to hydrosilicates with lower ratio C/S. The formation of such AAC structure conditioned increase in compressive strength by 20.0%, bending strength by 31.0 and decrease in shrinkage at temperature of 700 °C by 0.1% versus AAC without surfactant and ANS. It is concluded that ANS added to AAC forming mass serve as nucleators during the hardening of concrete, stimulating higher crystallinity in the hardened structure than that without these additives and improving AAC mechanical properties. The ANS additive also helps to form the crystalline structure and to improve thermal resistance of concrete.

In the paper [158], cement paste characteristics and porous concrete properties are studied. The results indicate that cement paste characteristics are dependent on the w/c ratio, admixture and mixing time. Cement paste with high viscosity and high flow suitable for making porous concrete is obtained with the use of low w/c of 0.20–0.25, an incorporation of 1% superplasticizer, and sufficient mixing. Porous concretes having suitable void ratios are produced with appropriate paste content and flow, and sufficient compaction. Good porous concretes with void ratio of 15–25% and strength of 22–39 MPa are produced using paste with flow of 150–230 mm and top surface vibration of 10 s with vibrating energy of 90 kN m/m². For low void ratio, high strength porous concrete of 39 MPa is obtained using paste with low flow. For high void ratio, porous concrete of 22 MPa is obtained using paste with high flow. Furthermore, the results indicate that the strength of porous concrete could be estimated from strength equation of porous brittle material.

Lightweight concretes can be produced by using processed natural material, processed by-product or unprocessed porous materials, depending upon the requirements of density and strength levels. The study [159] describes the use of pumice lightweight aggregate (PLA) to produce the lightweight concrete (LWC) for use in construction of load-bearing or non-load bearing elements. In this study, pumice aggregate lightweight concrete (PALWC) blocks were produced with different sizes of 8–16 mm as coarse pumice aggregate (CPA), of 4–8 mm as medium pumice aggregate (MPA) and 0–4 mm as fine pumice aggregate (FPA). According to the preliminary trial batch results, the optimum grade of aggregates was determined as 25% FPA, 25% MPA and 50% CPA by weight. To analyze the effects of CPA, MPA and FPA/cement ratios on the non-structural concrete engineering properties, the range of different pumice aggregate/cement (A/C) ratios from 6:1 to 30:1 by weight and cement contents from 32 to 180 kg/m³ were used to make PALWC mixture testing samples with a slump of 20 to 40 mm. The properties of PALWC with the range of different pumice aggregate/cement ratios were evaluated by conducting comprehensive series of tests on workability, compressive strength, elasticity modulus, bulk density, wetting expansion, drying shrinkage, water absorption and thermal conductivity. Experimental test results showed the PALWC of up to 25:1 A/C ratios has sufficient strength and adequate density to be accepted as load-bearing block applications. The PALWC of A/C ratio higher than 25:1 had sufficient strength, adequate density and the thermal conductivity to be accepted as for non-load bearing infill blocks for insulation purposes. The properties, which increase in value and indicate the increasing quality with lower A/C ratios (high cement contents), are compressive strength, modulus of elasticity and density. Properties, which decrease in value, with higher A/C ratios are water absorption, wetting expansion, drying shrinkage and thermal conductivity. It is shown that lowering the A/C ratios increases strength of PALWC, but increase of the A/C ratio increases the thermal insulation. The research shows that non-structural lightweight concrete can be produced by the use of fine, medium and coarse pumice aggregates mixes without using any additions or admixtures.

Polystyrene aggregate concrete (PAC) is a lightweight concrete with good deformation capacity, but its application is limited to non-structural use because of its apparent low strength properties. The study [160] was an effort to develop a class of structural grade PAC with a wide range of concrete densities between 1400 and 2100 kg/m³ through partial replacement of coarse aggregate with polystyrene aggregate (PA). The focus of this paper was to characterize the strength and long-term drying shrinkage properties of PAC. The parameters studied include PA content and curing conditions. The results show that the concrete density, concrete strength and elastic modulus of PAC decrease with increase of PA content in the mix. From the calorimetric test results, the increase in strength acceleration of PAC at early ages is due to the low specific thermal capacity of polystyrene aggregate. Besides, the long-term shrinkage and swelling of PAC are highly dependent on the PA content and the duration of

water curing. Due to the non-absorbent property of polystyrene aggregate, the ratio of reversible to drying shrinkage observed for PAC was lower compared to that of the control mix.

The effect of different fibers on the workability, mechanical properties, drying shrinkage and water adsorption was investigated on expanded polystyrene (EPS) lightweight concrete of high strength and workability [161]. The results showed that the addition of fibers to the EPS lightweight concrete mixture during mixing substantially reduced the sedimentation of EPS beads and improved the uniformity of the mix as well. Compared with normal EPS concrete, fibers were demonstrated to have greatly increased strength, especially splitting tensile strength. It was also demonstrated that fibers restrained the long-term drying shrinkage. However, no significant effect was found of fibers on the water adsorption of EPS concrete.

Expanded perlite aggregate (EPA) is a heat and sound insulator, and lightweight material which ensures economical benefits in constructions. The paper [162] investigates the properties of concrete containing EPA considering cement types (CEM II 32.5R and CEM I 42.5R), dosages (300, 350 and 400) and replacement ratios (0, 15, 30, 45 and 60). The tests were conducted on fresh and hardened concrete. Cube, cylinder and prismatic specimens were used for destructive and nondestructive tests at 28 days. In experiments, the minimum unit weight of concrete mixture was 1800 kg/m³ at the dosage of 300, and compressive strengths of EPAC (expanded perlite aggregate concrete) were obtained between 20 and 30 MPa at the replacement ratios of 30% considering cement types, thus it was proved that EPAC can be used as lightweight concrete with adequate replacement ratios, despite some losses in mechanical properties.

Structural lightweight concretes produced with pumice (LWC) and normal-weight aggregate concretes (NWC) were investigated in [163]. Compressive strength and weight loss of the concretes were determined after being exposed to room and high temperatures (20, 100, 400, 800, and 1000 °C). SF replaced PC in the ratios of 0, 5 and 10% by weight. Unit weight of LWC was 23% lower than that of NWC. The LWC containing 2% superplasticizer retained 38% of the initial compressive strength. Rate of deterioration was higher in NWC than in LWC. The loss of compressive strengths increased depending on the SF ratio at ~800 °C and over.

3.11. Properties of hardened SCC

Self-compacting (self-consolidating) concrete (SCC) is a relatively new type of concrete with high flowability and cohesiveness, when compared to conventional concrete. The intensive publications growth on properties of hardened SCC has been observed in the last 12 years (Fig. 1), which demonstrates superior properties of this type of concrete—not only in fresh, but also in hardened state.

Data from more than 70 recent studies on the hardened mechanical properties of SCC have been analyzed and correlated to produce comparisons with the properties of equivalent strength normally vibrated concrete (NVC) [164]. Relationships were obtained between cylinder and cube compressive strength, tensile and compressive strengths, and elastic modulus and compressive strength. It is found that limestone powder, a common addition to SCC mixes, makes a substantial contribution to strength gain. Bond strength of SCC to reinforcing and prestressing steel is similar to or higher than that of normally vibrated concrete. It is demonstrated that variation of in situ properties in structural elements cast with SCC is similar to that with NVC, and the performance of the structural elements is largely as predicted by the measured material properties.

The study [165] aimed to develop a new method for proportioning SCC. This method is capable of proportioning SCC mixtures with specified compressive strength, contrary to previous SCC proportioning methods that emphasized the fulfillment of fresh properties requirements more than strength requirements. In addition, no previous method considered the grading of aggregate in SCC mixtures

(fineness modulus of fine aggregate and maximum size of coarse aggregate) as in conventional concrete (CC) proportioning methods, making a need for numerous trial mixtures to adjust the fresh and hardened properties of SCC. Two well-known concrete mixture proportioning methods were adopted to develop the new method. The requirements of these methods were combined with certain modifications and a new method was proposed. In this new method, the actual range of compressive strength of the ACI 211.1 method was widened from 15–40 to 15–75 MPa, covering both normal- and high-strength SCC mixtures. Concrete strength was in agreement with the nominal design strength, except for mixtures with strength of 75 MPa; these mixtures required a slight adjustment in the w/c ratio.

The paper [166] presents the transport and mechanical properties of SCC that contain high percentages of low-lime and high-lime fly ash (FA). SCC containing 30 to 70% content of high-lime FA and low-lime FA as a replacement of cement (by weight of total cementitious material) were examined. The hardened properties included compressive and splitting tensile strengths, drying shrinkage and transport properties (absorption, sorptivity and rapid chloride permeability tests) up to 1 year. Test results confirm that it is possible to produce SCC with a 70% of cement replacement by both types of FA. The use of high volumes of FA in SCC not only improved the workability and transport properties, but also made it possible to produce concretes of 33–40 MPa compressive strength at 28 days, which exceeds the nominal compressive strength for normal concrete (30 MPa).

The paper [167] deals with time-dependent increase of compressive and splitting tensile strengths and modulus of elasticity as well as with compressive stress–strain curves of SCC made with crushed limestone aggregate and high content of limestone filler. The characteristics under consideration were tested at the ages of 1, 3, 7, 28, 180, 360 and 720 days. Time evolution of the strength characteristics and modulus of elasticity was estimated with analytical models given in Eurocode 2. The study revealed that the models can adequately predict time evolution of the SCC properties; however it was quite different from that proposed by Eurocode 2 for used cement strength class.

The objective of the study [168] was to explore the possibility of using manufactured sand produced by crushing rock, as a suitable alternative for river sand in SCC. The influence of paste volume and w/p ratio (water to powder ratio) on the properties of SCC was studied. The powder and aggregate combinations were optimized by using the particle packing approach, which involves the selection of combinations having maximum packing density. The chemical admixtures (superplasticizers and viscosity modifying agent) were optimized based on simple empirical tests. Hardened concrete tests were limited to compressive strength. Low and medium strength (25 to 60 MPa) SCCs with manufactured sand were obtained.

The work [169] presents a statistical study on the variability of the mechanical properties of hardened SCC, including the compressive strength, splitting tensile strength and modulus of elasticity. The variables included the maximum size aggregate, paste and gravel content. Results from the analyzed SCC presented variability measures in the same range than the expected for conventional vibrated concrete: all the results are within a confidence level of 95%. It was found that the modulus of elasticity can be estimated safely from the compressive strength, with lower strength SCC presenting higher safety margins, and that most codes overestimate the material tensile strength.

SCC mixtures for use in prestressed concrete applications were made under laboratory conditions with varying water-to-cementitious materials ratios, sand-to-total aggregate ratios, and cementitious material combinations (Type III cement, Class C fly ash, ground-granular blast-furnace slag, and silica fume) [170]. The SCC mixtures achieved prestress transfer compressive strengths between 38 and 66 MPa. The moduli of elasticity of the SCC mixtures were in

reasonable agreement with the elastic stiffness assumed during the design of conventional slump concrete structures. The long-term drying shrinkage strains for all the SCC mixtures were approximately the same or less than those measured for the control mixtures. A change in sand-to-total aggregate ratio had no significant effect on the long-term drying shrinkage. At later ages of 56 and 112 days, the measured drying shrinkage corresponded reasonably well to those predicted by the ACI 209 procedure.

The paper [171] compares the mechanical performance of highly confined columns cast with normal concrete (NC) vibrated into place to ensure proper filling and consolidation equivalent to that of identical columns cast with SCC. The tested columns had nominal concrete compressive strengths of 40 to 80 MPa. Two confining stirrup configurations representing different degrees of confinement were used. The confining stirrups had nominal steel yield strengths of 400 to 800 MPa. SCC yielded greater ductility, although it developed slightly lower ultimate compressive strength than NC. The study also confirmed that an increase in the stirrup yield strength can generate a high degree of confinement in well-confined concrete columns provided that stirrup spacing is kept small. The coring of unreinforced concrete columns demonstrated that the distribution of in-place properties over the column height is more homogeneous in the case of SCC than NC.

In the study [172] mix proportion parameters of high strength SCC were analyzed by using the Taguchi's experiment design methodology for optimal design. The best possible levels for mix proportions were determined for maximization of ultrasonic pulse velocity, compressive and splitting tensile strengths, and for the minimization of air content, water permeability and water absorption.

The work [173] studied differences between bond and cracking properties of SCC and vibrated concrete (VC). Four different mechanical tests were performed: splitting test, direct axial tension test, tension member test and beam test in flexure. Specific additional tests were carried out to study the effect of the concrete skin on cracking. Tension member tests did not show any significant difference between SCC and VC in terms of transfer length irrespective of the compressive strength of the concrete. Bond properties of both types of concrete are similar. No significant difference between SCC and VC tensile strength was observed by using the splitting test, the direct axial tension test and the beam test. Results obtained on not sawn tension members have shown that SCC cracking load can be significantly lower (up to 40%) than VC one. This reduction in cracking load can be attributed to a lower quality of the SCC skin. If the concrete skin is removed by sawing the specimens or if the concrete skin proportion in the tension cross-section is low (as in beam tests), the cracking loads and then the tensile strength deduced are similar for SCC or VC. It is concluded that the structural performance of the SCC and VC beam casts is similar.

The research [174] investigated SCC with up to 80% cement replacement by fly ash in mixes adjusted to yield constant fresh concrete properties. The hardened concrete and the relationships between hardened properties were studied. The results show that SCC with up to 80% cement replaced by fly ash is possible. To keep the filling ability constant, replacement of cement with fly ash would require an increase in water/powder ratio and a reduction in superplasticizer dosage. Fly ash had negative effects on strength. The comparison between SCC and normally vibrated concrete showed that their material properties are similar.

The effect of limestone fillers with different specific surface area on the hardened properties of SCC was studied in [175]. It was found that filler with a large area results in an increased autogenous shrinkage, decreased evaporation, lower plastic cracking tendency, and a higher compressive strength. With additional water the results were the opposite. The finding about higher autogenous shrinkage and lower plastic cracking potential sounds controversial and requires further study.

The mechanical properties of lightweight and normal-weight SCC were studied [176]. Lightweight SCC with a binder content of 500–650 kg m⁻³ was made using less superplasticizer and viscosity modifying agent and a lower water/binder ratio than normal SCC. The bulk density was only 75% of normal SCC, but with a similar compressive strength. The elastic modulus was about 80% of that of normal SCC. These results indicate that lightweight SCC is excellent in workability and has a lower density, a higher compressive strength and a relatively high elastic modulus than normal SCC.

In the study [177] hardened properties of SCC using recycled concrete aggregate were evaluated. SCC mixtures were prepared with 100% coarse recycled aggregates, and different levels of fine recycled aggregates were used to replace river sand (0, 25, 50, 75 and 100%). The cement content was kept constant. The tests covered fresh, hardened and durability properties. The results indicate that the properties of the SCCs made from river sand and crushed fine recycled aggregates showed only slight differences. The feasibility of using fine and coarse recycled aggregates with rejected fly ash and Class F fly ash for SCC is proven.

SCC offers several economical and technical benefits, but the use of fibers extends its possibilities. In the article [178] the effects of fiber inclusion on the compactability of hybrid (carbon + steel) fiber reinforced concrete were studied.

The construction industry requires new energy saving concepts, one of them is using Phase Change Materials (PCM) enable to absorb and release thermal energy at a specific temperature. The study [179] focuses on the direct mixing of micro-encapsulated PCM with SCC and its influence on the properties, including strength and thermal properties. It is shown that increasing PCM dosages lower thermal conductivity and increase heat capacity, which both significantly improve the thermal performance of concrete and therefore save energy. On the other hand, a significant loss in strength and micro-structural analysis both indicate that a large part of the capsules is destroyed during the mixing process and releases its paraffin wax filling into the surrounding matrix.

4. Summary and perspectives

The present paper reviews the literature related to the properties of fresh and hardened concrete published after the 12th International Congress on the Chemistry of Cement (Montreal, 2007).

In the future, it can be expected that computational tools allowing for the prediction of the effect of casting on hardened properties will be developed. Research work dealing with numerical predictions of the effects of local aggregate content, local air content and local fiber orientation, starts now in different research laboratories around the globe. These tools, when associated with the recent progresses in the prediction of hardened properties as a function of mix design, shall allow for the prediction of local hardened properties and shall improve prediction of structural behavior.

It can moreover be expected that viscosity of concrete shall become more and more important. The recent trends in mix design show a reduction of the clinker content of concrete for environmental reasons. In order to keep similar properties in terms of durability, setting time and mechanical strength, the water amount in the system is also reduced. Viscosity shall increase because of the relative increase in solid content. Contacts between particles shall play an increasing role. Although we know how to tune yield stress by using super plasticizer, the knowledge on how to reduce viscosity is far less developed. This increase in viscosity shall moreover be increased by the use of lower quality aggregates. Around the globe, natural aggregate resources are decreasing. More and more crushed aggregates or even recycled aggregates are used. Their shape and their low packing fraction strongly increase viscosity.

Finally, again for environmental reasons, new binders shall be developed in the future and shall generate new needs in knowledge

and understanding. For instance, clay particle interactions in geopolymer system have nothing in common with clinker grains. Most superplasticizers become useless and anyhow do not resist to the high pH of the interstitial solution needed to activate the clay particles. Some of the tools developed for clinker could be transferred to these new cements but is doubtful that it will be the case for most of our clinker based knowledge.

A certain number of works addressing specific properties of fresh and hardened concrete have been published recently with the goal to develop new methods of testing, interpret test results, model and predict the development of properties in time or their changes under specific mechanical or environmental loading. However, most of the papers on concrete properties published in the last 4 years dealt rather with the influence of numerous factors (such as different type of loading, environmental conditions and introduction of chemical/mineral admixtures, recycled aggregates, etc. into concrete mixes) on properties of concrete, or with the properties of certain types of concrete, such as lightweight, self-compacting, fiber-reinforced, high-strength, high-performance and other types of concrete. It seems that the number of such publications will be growing further.

In several works an attempt to find a correlation between the properties of hardened concrete, fresh concrete and durability, was undertaken, and sometimes such correlations work well.

It can be expected that more focus will be made on studying controversial effects on concrete properties, when a positive change in one property causes an adverse effect in another one. An example of such controversial effect is an improvement of cracking resistance and durability of concrete by introduction of special components, such as internal curing agents or shrinkage-reducing admixtures. Such introduction is often accompanied by a certain strength loss at early age. Another example is introduction of a special component to improve concrete ductility, which can simultaneously lower concrete stiffness.

As was noticed before, the lack of virgin aggregates and the environmental considerations based on the needs to reduce CO₂ emissions and global warming result in the necessity to apply wider low-quality aggregates and low-clinker cements in concrete manufacture. This trend obviously influences the properties of concrete, while some of them may decrease.

Both controversial and adverse effects described before make vital the development of new effective technologies aimed to compensate negative effects on the concrete properties. Another approach is an optimization of the properties, taking into account the environmental and economical considerations, in addition to the purely technical and technological aspects. Speaking about optimization, we assume that the property changes should be translated into the changes of the common parameter (such as life-cycle costs or carbon footprints), which serves to compare different technological and design solutions.

The advanced models which can reliably predict the properties of concrete in both fresh and hardened states as a function of concrete composition, structural geometry, loading and environmental conditions are required for the better design and maintenance of concrete structures based on the sustainability approach.

References

- [1] G.H. Tattersall, P.G.F. Banfill, *The Rheology of Fresh Concrete*, Pitman, London, 1983.
- [2] J. Murata, Flow and deformation of fresh concrete, *Materials and Structures* 98 (1984) 117–129.
- [3] F. De Larrard, *Concrete Mixture Proportioning*, E & FN Spon, London, 1999.
- [4] C. Hu, F. de Larrard, the rheology of fresh high performance concrete, *Cement and Concrete Research* 26 (2) (1996) 283–294.
- [5] R.J. Flatt, Towards a prediction of superplasticized concrete rheology, *Materials and Structures* 27 (2004) 289–300.
- [6] N. Roussel, A. Lemaître, R.J. Flatt, P. Coussot, Steady state flow of cement suspensions: a micromechanical state of the art, *Cement and Concrete Research* 40 (2010) 77–84.
- [7] N. Roussel, Rheology of fresh concrete: from measurements to predictions of casting processes, *Materials and Structures* 40 (10) (2007) 1001–1012.
- [8] R. Shaughnessy, P.E. Clark, The rheological behaviour of fresh cement pastes, *Cement and Concrete Research* 18 (1988) 327–341.
- [9] M. Nehdi, M.-A. Rahman, Estimating rheological properties of cement pastes using various rheological models for different test geometry, gap and surface friction, *Cement and Concrete Research* 34 (2004) 1993–2007.
- [10] C. Hu, F. de Larrard, T. Sedran, C. Boulay, F. Bosc, F. Deflorenne, Validation of BTRHEOM, the new rheometer for soft-to-fluid concrete, *Materials and Structures* 29 (194) (1996) 620–631.
- [11] Operating Manual, the BML Viscometer, the Viscometer 4, Con Tec, 2000.
- [12] G.H. Tattersall, S.J. Bloomer, Further development of the two-point test for workability and extension of its range, *Magazine of Concrete Research* 31 (1979) 202–210.
- [13] ASTM Designation C-143-90, Standard test method for slump of hydraulic cement concrete, *Annual Book of ASTM Standards*, 04.01, Am. Soc. Test. Mat., Easton, MD, 1996, pp. 85–87.
- [14] C.F. Ferraris, L.E. Brower (Eds.), Comparison of Concrete Rheometers: International Tests at LCPC (Nantes, France) in October 2000, National Institute of Standards and Technology Interagency Report (NISTIR), 6819, 2001.
- [15] C.F. Ferraris, L.E. Brower (Eds.), Comparison of Concrete Rheometers: International Tests at MB (Cleveland OH, USA) in May 2003, National Institute of Standards and Technology Interagency Report (NISTIR), 7154, 2004.
- [16] Schowalter, W.R., Christensen, G., Toward a rationalization of the slump test for fresh concrete: comparisons of calculations and experiments, *Journal of Rheology* 42(4) 865–870, (1998).
- [17] N. Pashias, D.V. Boger, J. Summers, D.J. Glenister, A fifty cent rheometer for yield stress measurements, *Journal of Rheology* 40 (6) (1996) 1179–1189.
- [18] P. Domone, The slump flow test for high-workability concrete, *Cement and Concrete Research* 28 (1998) 177–182.
- [19] S. Clayton, T.G. Grice, D.V. Boger, Analysis of the slump test for on-site yield stress measurement of mineral suspensions, *Int. J. Miner. Process.* 70 (2003) 3–21.
- [20] A.W. Saak, H.M. Jennings, S.P. Shah, A generalized approach for the determination of yield stress by slump and slump flow, *Cement and Concrete Research* 34 (2004) 363–371.
- [21] J.E. Wallevik, Relationship between the Bingham parameters and slump, *Cement and Concrete Research* 36 (7) (2006) 1214–1221.
- [22] N. Roussel, P. Coussot, “Fifty-cent rheometer” for yield stress measurements: from slump to spreading flow, *Journal of Rheology* 49 (3) (2005) 705–718.
- [23] N. Roussel, Correlation between yield stress and slump: comparison between numerical simulations and concrete rheometers results, *Materials and Structures* 39 (4) (2006) 501–509.
- [24] N. Roussel, C. Stefani, R. Le Roy, From mini cone test to Abrams cone test: measurement of cement based materials yield stress using slump tests, *Cement and Concrete Research* 35 (5) (2005) 817–822.
- [25] Y. Otsubo, S. Miyai, K. Umeyai, Time-dependent flow of cement pastes, *Cement and Concrete Research* 10 (1980) 631–638.
- [26] P.F.G. Banfill, D.C. Saunders, On the viscosimetric examination of cement pastes, *Cement and Concrete Research* 11 (1981) 363–370.
- [27] R. Lapasin, V. Longo, S. Rajgeli, Thixotropic behaviour of cement pastes, *Cement and Concrete Research* 9 (1979) 309–318.
- [28] M.R. Geiker, M. Brandl, L.N. Thrane, D.H. Bager, O. Wallevik, The effect of measuring procedure on the apparent rheological properties of self compacting concrete, *Cement and Concrete Research* 32 (2002) 1791–1795.
- [29] N. Roussel, Steady and transient flow behaviour of fresh cement pastes, *Cement and Concrete Research* 35 (9) (2005) 1656–1664.
- [30] J.E. Wallevik, Rheological properties of cement paste: thixotropic behavior and structural breakdown, *Cement and Concrete Research* 39 (1) (2009) 14–29.
- [31] P. Billberg, Development of SCC static yield stress at rest and its effect on the lateral form pressure, in: S.P. Shah (Ed.), *Proceedings of the Second North American Conference on the Design and Use of Self-Consolidating Concrete and the Fourth International RILEM Symposium on Self-Compacting Concrete*, October 30–November 3 2005, Chicago, USA.
- [32] S. Jarny, N. Roussel, S. Rodts, R. Le Roy, P. Coussot, Rheological behavior of cement pastes from MRI velocimetry, *Cement and Concrete Research* 35 (2005) 1873–1881.
- [33] J. Assaad, K. Khayat, H. Mesbah, Assessment of thixotropy of flowable and self-consolidating concrete, *ACI Materials Journal* 100 (2) (2003) 99–107.
- [34] N. Roussel, A thixotropy model for fresh fluid concretes: theory, validation and applications, *Cement and Concrete Research* 36 (10) (2006) 1797–1806.
- [35] K. Khayat, A.F. Omran, T.V. Pavate, Inclined plane test to evaluate structural buildup at rest of self-consolidating concrete, *ACI Materials Journal* 107 (5) (2010) 515.
- [36] C. Jolicoeur, M.-A. Simard, Chemical admixtures–cement interactions: phenomenology and physico-chemical concepts, *Cem. Concr. Compos.* 20 (1998) 87–101.
- [37] V. Fernon, A. Vichot, N. Le Goanvic, P. Colombet, F. Corazza, U. Costa, Interaction between Portland cement hydrates and polynaphthalene sulfonates, in: V.M. Malhotra (Ed.), *Proceedings of the 5th CANMET/ACI International Conference on Superplasticizers and Other Chemical Admixtures in Concrete*, SP-173, American Concrete Institute, Farmington Hills, MI, USA, 1997, pp. 225–248.
- [38] H. Matsuyama, J.F. Young, The formation of C–S–H/polymer complexes by hydration of reactive β -dicalcium silicate, *Concr. Sci. Eng.* 1 (1999) 66–75.
- [39] R.J. Flatt, Y.F. Houst, A simplified view on chemical effects perturbing the action of superplasticizers, *Cement and Concrete Research* 31 (2001) 1169–1176.
- [40] L. Nachbaur, J.C. Mutin, A. Nonat, L. Choplin, Dynamic mode rheology of cement and tricalcium silicate pastes from mixing to setting, *Cement and Concrete Research* 31 (2001) 183–192.

- [41] D. Lootens, R. Flatt, Rheology of penetration tests II: link to shear modulus, 12th Int. Conf. Cem. Chem., Montreal, Canada, 8–13 July, 2007.
- [42] K.V. Subramaniam, X. Wang, An investigation of microstructure evolution in cement paste through setting using ultrasonic and rheological measurements, *Cement and Concrete Research* 40 (1) (2010) 33–44.
- [43] N. Robeyst, C.U. Grosse, N. De Belie, Measuring the change in ultrasonic p-wave energy transmitted in fresh mortar with additives to monitor the setting, *Cement and Concrete Research* 39 (10) (2009) 868–875.
- [44] G. Trtnik, M.I. Valič, F. Kavčič, G. Turk, Comparison between two ultrasonic methods in their ability to monitor the setting process of cement pastes, *Cement and Concrete Research* 39 (10) (October 2009) 876–882.
- [45] G. Trtnik, G. Turk, F. Kavčič, V.B. Bosiljkov, Possibilities of using the ultrasonic wave transmission method to estimate initial setting time of cement paste, *Cement and Concrete Research* 38 (11) (November 2008) 1336–1342.
- [46] N. Robeyst, E. Gruyaert, C.U. Grosse, N. De Belie, Monitoring the setting of concrete containing blast-furnace slag by measuring the ultrasonic p-wave velocity, *Cement and Concrete Research* 38 (10) (October 2008) 1169–1176.
- [47] Z. Sun, T. Voigt, S.P. Shah, Rheometric and ultrasonic investigations of viscoelastic properties of fresh Portland cement pastes, *Cement and Concrete Research* 36 (2) (2006) 278–287.
- [48] M.A. Schultz, L. Struble, Use of oscillatory shear to study flow behavior of fresh cement paste, *Cement and Concrete Research* 23 (1993) 273–282.
- [49] Hassan Sleiman, Arnaud Perrot, Sofiane Amziane, A new look at the measurement of cementitious paste setting by Vicat test, *Cement and Concrete Research* 40 (5) (2010) 681–686.
- [50] L. Jossierand, O. Coussy, F. de Larrard, Bleeding of concrete as an ageing consolidation process, *Cement and Concrete Research* 36 (2006) 1603–1608.
- [51] T.S. Tan, T.H. Wee, S.A. Tan, C.T. Tam, S.L. Lee, A consolidation model for bleeding of cement paste, *Adv. Cem. Res.* 1 (1) (1987) 18–26.
- [52] C.A. Clear, D.G. Bonner, Settlement of fresh concrete—an effective stress model, *Magazine of Concrete Research* 40 (142) (1988) 3–12.
- [53] K.H. Khayat, Viscosity-enhancing admixtures for cement-based materials—an overview, *Cement and Concrete Composites* 20 (1998) 171–188.
- [54] F. Cussigh, M. Sonebi, G. De Schutter, Project testing SCC-segregation test methods, *Proceedings of the 3rd international RILEM Symposium on Self-Compacting Concrete*, Reykjavik, Iceland, (RILEM PRO33, 2003), 2003, pp. 311–322.
- [55] J.A. Daczko, A comparison of passing ability test methods for self consolidating concrete, *Proceedings of the 3rd international RILEM Symposium on Self-Compacting Concrete*, Reykjavik, Iceland, (RILEM PRO33, 2003), 2003, pp. 335–344.
- [56] A.W. Saak, H. Jennings, S. Shah, New methodology for designing self-compacting concrete, *ACI Materials Journal* 98 (6) (2001) 429–439.
- [57] N. Roussel, A theoretical frame to study stability of fresh concrete, *Materials and Structures* 39 (2006) 81–91.
- [58] D. Lowke, T. Kränkel, C. Gehlen, P. Shiessl, Effect of cement on super plasticizer adsorption, yield stress, thixotropy and segregation resistance, in: K. Khayat, D. Feys (Eds.), *Proceedings of SCC2010*, Montreal, Canada, Springer, 2010, pp. 91–102.
- [59] L. Shen, L. Struble, D. Lange, Modeling dynamic segregation of self-consolidating concrete, *ACI Materials Journal* 106 (4) (2009) 375–380.
- [60] H. Mori, Y. Tanigawa, Simulation methods for fluidity of fresh concrete, *Memoirs of the School of Engineering, Nagoya University* 44 (1992) 71–133.
- [61] H. Kitaoji, Y. Tanigawa, H. Mori, Y. Kurokawa, S. Urano, Flow simulation of fresh concrete cast into wall structure by viscoplastic divided space element method, *Trans. of the Japan Concrete Institute* 16 (1996) 45–52.
- [62] L.N. Thrane, P. Szabo, M. Geiker, M. Glavind, H. Stang, Simulation and verification of flow in SCC test methods, *Proc. of the 4th Int. RILEM Symp. on SCC*, 2005, Chicago.
- [63] N. Roussel, S. Staquet, L. D'aloia Schwarzentruher, R. Le Roy, F. Toutlemonde, SCC casting prediction for the realization of prototype VHPCC-precambered composite beams, *Materials and Structures* 40 (9) (2007) 877–887.
- [64] N. Roussel, M.R. Geiker, F. Dufour, L.N. Thrane, P. Szabo, Computational modeling of concrete flow: general overview, *Cement and Concrete Research* 37 (9) (2007) 1298–1307.
- [65] N. Martys, C.F. Ferraris, Simulation of SCC flow, *Proc. 1st North American Conf. on the Design and Use of Self-Consolidating Concrete*, Chicago, IL, 2002, pp. 27–30.
- [66] J. Spangenberg, N. Roussel, J.H. Hattel, J. Thorborg, M. Geiker, H. Stang, J. Skoceck, Prediction of flow induced in-homogeneities in self compacting concretes (SCC), in: K. Khayat, D. Feys (Eds.), *Proceedings of SCC2010*, Montreal, Canada, Springer, 2010, pp. 209–218.
- [67] L. Martinie, N. Roussel, Fiber reinforced cementitious materials: from intrinsic isotropic behavior to fiber alignment, in: K. Khayat, D. Feys (Eds.), *Proceedings of SCC2010*, Montreal, Canada, Springer, 2010, pp. 407–416.
- [68] ACI Committee 347, *Guide to Formwork for Concrete* (ACI 347-04), American Concrete Institute, Farmington Hills, MI, 2004, 32 pp.
- [69] British Standard Institution, BS 882—Specification for Aggregates from Natural Sources for Concrete, BSI, December 1992.
- [70] C. Clear, T.N. Harrison, Concrete pressure on formwork, CIRIA Report, 108, 1985, 32 pp.
- [71] M.K. Hurd, Lateral pressures for formwork design, *Concrete International* 29 (6) (2007) 31–33.
- [72] P. Billberg, Form pressure generated by self-compacting concrete, *Proceedings of the 3rd international RILEM Symposium on Self-Compacting Concrete*, RILEM PRO33 Reykjavik, Iceland, 2003, pp. 271–280.
- [73] J. Assaad, K.H. Khayat, H. Mesbah, Variation of formwork pressure with thixotropy of self-consolidating concrete, *ACI Materials Journal* 100 (1) (2003) 29–37.
- [74] G. Ovarlez, N. Roussel, A physical model for the prediction of lateral stress exerted by self-compacting concrete on formwork, *Materials and Structures* 39 (2) (2006) 269–279.
- [75] J.C. Tchamba, S. Amziane, G. Ovarlez, N. Roussel, Lateral stress exerted by fresh cement paste on formwork: laboratory experiments, *Cement and Concrete Research* 38 (2008) 459–466.
- [76] A. Perrot, S. Amziane, G. Ovarlez, N. Roussel, SCC formwork pressure: influence of steel rebars, *Cement and Concrete Research* 39 (2009) 524–528.
- [77] K. Khayat, F.O. Omran, M. D'amrosia, Prediction of SCC formwork pressure in full scale elements, in: K. Khayat, D. Feys (Eds.), *Proceedings of SCC2010*, Montreal, Canada, Springer, 2010, pp. 231–241.
- [78] U. Schneider, Recommendation of RILEM TC 200-HTC: mechanical concrete properties at high temperatures—modelling and application, part 11: relaxation, *Materials and Structures* 40 (5) (2007) 449–458.
- [79] U.C. Hasar, Non-destructive testing of hardened cement specimens at microwave frequencies using a simple free-space method, *NDT & E International* 42 (6) (2009) 550–557.
- [80] F. Indelicato, M. Paggi, Specimen shape and the problem of contact in the assessment of concrete compressive strength, *Materials and Structures* 41 (2008) 431–441.
- [81] B. Graybeal, M. Davis, Cylinder or cube: strength testing of 80 to 200 MPa (11.6 to 29 ksi) ultra-high-performance fiber-reinforced concrete, *ACI Materials Journal* 106 (6) (2008) 603–609.
- [82] A.F. Bingöl, R. Gül, Effect of elevated temperatures and cooling regimes on normal strength concrete, *Fire and Materials* 33 (2) (2009) 79–88.
- [83] H. Taghaddos, H.R. Soleymani, J.D. Robson, Precision of compressive strength testing of concrete with different cylinder specimen sizes, *ACI Materials Journal* 107 (5) (2010) 461–468.
- [84] J.W. Bullard, P.E. Stutzman, L.M. Ordoñez Belloc, E.J. Garboczi, D.P. Bentz, Virtual cement and concrete testing laboratory for quality testing and sustainability of concrete, *ACI Special Publication SP-266* (2009) 27–36.
- [85] P.G. Ranjith, D. Jasinge, J.Y. Song, S.K. Choi, A study of the effect of displacement rate and moisture content on the mechanical properties of concrete: use of acoustic emission, *Mechanics of Materials* 40 (6) (2008) 453–469.
- [86] Shin Sung Woo, Oh Tae Keun, Application of electro-mechanical impedance sensing technique for online monitoring of strength development in concrete using smart PZT patches, *Construction and Building Materials* 23 (2) (2009) 1185–1188.
- [87] Shin Sung Woo, A.R. Qureshi, Lee Jae-Yong, Yun Chung Bang, Piezoelectric sensor based nondestructive active monitoring of strength gain in concrete, *Smart Materials and Structures* 17 (5) (2008) 055002.
- [88] R. Tawie, H.K. Lee, Monitoring the strength development in concrete by EMI sensing technique, *Construction and Building Materials* 24 (9) (2010) 1746–1753.
- [89] I.B. Topcu, M. Sarıdemir, Prediction of rubberized mortar properties using artificial neural network and fuzzy logic, *Journal of Materials Processing Technology* 199 (1–3) (2008) 108–118.
- [90] I.B. Topcu, M. Sarıdemir, Prediction of properties of waste AAC aggregate concrete using artificial neural network, *Computational Materials Science* 41 (1) (2007) 117–125.
- [91] E. Ozbay, M. Gesoglu, E. Güneyisi, Empirical modeling of fresh and hardened properties of self-compacting concretes by genetic programming, *Construction and Building Materials* 22 (8) (2008) 1831–1840.
- [92] J. Roessler, G.H. Paulino, K. Park, C. Gaedcke, Concrete fracture prediction using bilinear softening, *Cement and Concrete Composites* 29 (4) (2007) 300–312.
- [93] E. Ozgan, A. Ozturk, Optimization of the hardened concrete properties with GA and LP, *Journal of Applied Science* 7 (24) (2007) 3918–3926.
- [94] Li Chen, Tai-Sheng Wang, Modeling strength of high-performance concrete using an improved grammatical evolution combined with macrogenetic algorithm, *J. Comp. in Civ. Engrg* 24 (3) (2010) 281–288.
- [95] G. Trtnik, F. Kavčič, G. Turk, Prediction of concrete strength using ultrasonic pulse velocity and artificial neural networks, *Ultrasonics* 49 (1) (2009) 53–60.
- [96] S. Popovics, J. Ujhelyi, Contribution to the concrete strength versus water-cement ratio relationship, *J. Mat. in Civ. Engrg.* 20 (7) (2008) 459–463.
- [97] R. Goel, R. Kumar, D.K. Paul, Comparative study of various creep and shrinkage prediction models for concrete, *J. Mat. in Civ. Engrg.* 19 (3) (2007) 249–260.
- [98] F. Demir, Prediction of elastic modulus of normal and high strength concrete by artificial neural networks, *Construction and Building Materials* 22 (7) (2008) 1428–1435.
- [99] S. Scheiner, C. Hellmich, Continuum microviscoelasticity model for aging basic creep of early-age concrete, *J. Engrg. Mech.* 135 (4) (2009) 307–323.
- [100] S.E. Chidiac, O. Maadani, A.G. Razaqpur, N.P. Mailvaganam, Correlation of rheological properties to durability and strength of hardened concrete, *Journal of Materials in Civil Engineering* 15 (4) (2003) 391–399.
- [101] Z. Giergiczny, M.A. Glinicki, M. Sokołowski, M. Zielinski, Air void system and frost-salt scaling of concrete containing slag-blended cement, *Construction and Building Materials* 23 (6) (2009) 2451–2456.
- [102] D.P. Bentz, A review of early-age properties of cement-based materials, *Cement and Concrete Research* 38 (2) (2008) 196–204.
- [103] K. Kovler, A. Bentur, Cracking sensitivity of normal and high strength concretes, *ACI Materials Journal* 106 (6) (2009) 537–542.
- [104] M. Briffaut, F. Benboudjema, J.M. Torrenti, G. Nahas, A thermal active restrained shrinkage ring test to study the early age concrete behaviour of massive structures, *Cement and Concrete Research* 41 (1) (2011) 56–63.

- [105] N. Makaratat, C. Jaturapitakkul, T. Laosamathikul, Effects of calcium carbide residue–fly ash binder on mechanical properties of concrete, *Journal of Materials in Civil Engineering* 22 (11) (2010) 1164–1170.
- [106] M. Sofi, J.S.J. van Deventer, P.A. Mendis, G.C. Lukey, Engineering properties of inorganic polymer concretes (IPCs), *Cement and Concrete Research* 37 (2) (2007) 251–257.
- [107] Keun-Hyeok Yang, Hey-Zoo Hwang, Seol Lee, Effects of water–binder ratio and fine aggregate–total aggregate ratio on the properties of hwangtoh-based alkali-activated concrete, *J. Mat. in Civ. Engrg* 22 (9) (2010) 887–896.
- [108] M. Etxeberria, E. Vázquez, A. Marí, M. Barra, Influence of amount of recycled coarse aggregates and production process on properties of recycled aggregate concrete, *Cement and Concrete Research* 37 (5) (2007) 735–742.
- [109] B. Taha, G. Nounu, Properties of concrete contains mixed colour waste recycled glass as sand and cement replacement, *Construction and Building Materials* 22 (5) (2008) 713–720.
- [110] Yang Keun-Hyeok, Chung Heon-Soo, A.F. Ashour, Influence of type and replacement level of recycled aggregates on concrete properties, *ACI Materials Journal* 105 (3) (2008).
- [111] L. Evangelista, J. de Brito, Mechanical behaviour of concrete made with fine recycled concrete aggregates, *Cement and Concrete Composites* 29 (5) (2007) 397–401.
- [112] P.B. Cachim, Mechanical properties of brick aggregate concrete, *Construction and Building Materials* 23 (3) (2009) 1292–1297.
- [113] R. Siddique, G. de Schutter, A. Noumowe, Effect of used-foundry sand on the mechanical properties of concrete, *Construction and Building Materials* 23 (2) (2009) 976–980.
- [114] İ.B. Topçu, T. Bilir, Experimental investigation of some fresh and hardened properties of rubberized self-compacting concrete, *Materials & Design* 30 (8) (2009) 3056–3065.
- [115] I. Guerra, I. Vivar, B. Llamas, A. Juan, J. Moran, Eco-efficient concretes: the effects of using recycled ceramic material from sanitary installations on the mechanical properties of concrete, *Waste Management* 29 (2) (2009) 643–646.
- [116] A. Kan, R. Demirboğa, A novel material for lightweight concrete production, *Cement and Concrete Composites* 31 (7) (2009) 489–495.
- [117] S.W. Tabsh, A.S. Abdelfatah, Influence of recycled concrete aggregates on strength properties of concrete, *Construction and Building Materials* 23 (2) (2009) 1163–1167.
- [118] Ö. Eren, K. Marar, Effects of limestone crusher dust and steel fibers on concrete, *Construction and Building Materials* 23 (2) (2009) 981–988.
- [119] İ.B. Topçu, T. Bilir, T. Uygunoğlu, Effect of waste marble dust content as filler on properties of self-compacting concrete, *Construction and Building Materials* 23 (5) (2009) 1947–1953.
- [120] S.L. Yang, S.G. Millard, M.N. Soutsos, S.J. Barnett, T.T. Le, Influence of aggregate and curing regime on the mechanical properties of ultra-high performance fibre reinforced concrete (UHPFRC), *Construction and Building Materials* 23 (6) (2009) 2291–2298.
- [121] Poon Chi Sun, Lam Chi Sing, The effect of aggregate-to-cement ratio and types of aggregates on the properties of pre-cast concrete blocks, *Cement and Concrete Composites* 30 (4) (2008) 283–289.
- [122] Liu Juanyu, Chen Bing, Property of high strength concrete made with field-demolished concrete aggregates, *Transportation Research Board Annual Meeting*, 2008, Paper #08-1752, 9 pp.
- [123] Deyu Kong, Ting Lei, Jianjun Zheng, Chengchang Ma, Jun Jiang, Jing Jiang, Effect and mechanism of surface-coating pozzalancs materials around aggregate on properties and ITZ microstructure of recycled aggregate concrete, *Construction and Building Materials* 24 (5) (2010) 701–708.
- [124] M.C. Limbachiya, Bulk engineering and durability properties of washed glass sand concrete, *Construction and Building Materials* 23 (2) (2009) 1078–1083.
- [125] Poon Chi-Sun, Hui-wen Shi-cong Kou, Etxeberria Wan Miren, Properties of concrete blocks prepared with low grade recycled aggregates, *Waste Management* 29 (8) (2009) 2369–2377.
- [126] V. López, B. Llamas, A. Juan, J.M. Morán, I. Guerra, Eco-efficient concretes: impact of the use of white ceramic powder on the mechanical properties of concrete, *Biosystems Engineering* 96 (4) (2007) 559–564.
- [127] B. González-Fontboa, F. Martínez-Abella, Concretes with aggregates from demolition waste and silica fume, materials and mechanical properties, *Building and Environment* 43 (4) (2008) 429–437.
- [128] Kou Shi Cong, Poon Chi Sun, Chan Dixon, Influence of fly ash as cement replacement on the properties of recycled aggregate concrete, *J. Mat. in Civ. Engrg* 19 (2007) (2007) 709–717.
- [129] S.C. Kou, C.S. Poon, Properties of self-compacting concrete prepared with recycled glass aggregate, *Cement and Concrete Composites* 31 (2) (2009) 107–113.
- [130] G. Hüskén, H.J.H. Brouwers, A new mix design concept for earth-moist concrete: a theoretical and experimental study, *Cement and Concrete Research* 38 (10) (2008) 1246–1259.
- [131] F. Debieb, S. Kenai, The use of coarse and fine crushed bricks as aggregate in concrete, *Construction and Building Materials* 22 (5) (2008) 886–893.
- [132] C. Aquino, M. Inoue, H. Miura, M. Mizuta, T. Okamoto, The effects of limestone aggregate on concrete properties, *Construction and Building Materials* 24 (12) (2010) 2363–2368.
- [133] A. Kılıç, C.D. Atiş, A. Teymen, O. Karahan, F. Özcan, C. Bilim, M. Özdemir, The influence of aggregate type on the strength and abrasion resistance of high strength concrete, *Cement and Concrete Composites* 30 (4) (2008) 290–296.
- [134] İ.B. Topçu, A. Demir, Relationship between methylene blue values of concrete aggregate fines and some concrete properties, *Canadian Journal of Civil Engineering* 35 (4) (2008) 379–383.
- [135] J. Limeira, L. Agullo, M. Etxeberria, Dredged marine sand in concrete: an experimental section of a harbor pavement, *Construction and Building Materials* 24 (6) (2010) 863–870.
- [136] H. Mazaheripour, S. Ghanbarpour, S.H. Mirmoradi, et al., The effect of polypropylene fibers on the properties of fresh and hardened lightweight self-compacting concrete, *Construction and Building Materials* 25 (1) (2011) 351–358.
- [137] İ.B. Topçu, M. Canbaz, Effect of different fibers on the mechanical properties of concrete containing fly ash, *Construction and Building Materials* 21 (7) (2007) 1486–1491.
- [138] Y. Mohammadi, S.P. Singh, S.K. Kaushik, Properties of steel fibrous concrete containing mixed fibres in fresh and hardened state, *Construction and Building Materials* 22 (5) (2008) 956–965.
- [139] A. Sivakumar, M. Santhanam, Mechanical properties of high strength concrete reinforced with metallic and non-metallic fibres, *Cement and Concrete Composites* 29 (8) (2007) 603–660.
- [140] M. Sahmaran, İ.O. Yaman, Hybrid fiber reinforced self-compacting concrete with a high-volume coarse fly ash, *Construction and Building Materials* 21 (1) (2007) 150–156.
- [141] V. Sata, C. Jaturapitakkul, K. Kiattikomo, Influence of pozzolan from various by-product materials on mechanical properties of high-strength concrete, *Construction and Building Materials* 21 (7) (2007) 1589–1598.
- [142] S.A. Barbhuiya, J.K. Gbagbo, M.I. Russell, P.A.M. Basheer, Properties of fly ash concrete modified with hydrated lime and silica fume, *Construction and Building Materials* 23 (10) (2009) 3233–3239.
- [143] A. Salas, S. Delvasto, R.M. de Gutierrez, D. Lange, Comparison of two processes for treating rice husk ash for use in high performance concrete, *Cement and Concrete Research* 39 (9) (2009) 773–778.
- [144] M. Gesoğlu, E. Özbay, Effects of mineral admixtures on fresh and hardened properties of self-compacting concretes: binary, ternary and quaternary systems, *Materials and Structures* 40 (9) (2007) 923–937.
- [145] K. Ganesan, K. Rajagopal, K. Thangavel, Rice husk ash blended cement: assessment of optimal level of replacement for strength and permeability properties of concrete, *Construction and Building Materials* 22 (8) (2008) 1675–1683.
- [146] R. Siddique, J. Klaus, Influence of metakaolin on the properties of mortar and concrete: a review, *Applied Clay Science* 43 (3–4) (2009) 392–400.
- [147] E. Vejmelková, M. Pavlíková, M. Keppert, Z. Keršner, P. Rovnaníková, M. Ondráček, M. Sedlmajer, R. Černý, High performance concrete with Czech metakaolin: experimental analysis of strength, toughness and durability characteristics, *Construction and Building Materials* 24 (8) (2010) 1404–1411.
- [148] E. Vejmelková, M. Pavlíková, Z. Keršner, P. Rovnaníková, M. Ondráček, M. Sedlmajer, R. Černý, High performance concrete containing lower slag amount: a complex view of mechanical and durability properties, *Construction and Building Materials* 23 (6) (2009) 2237–2245.
- [149] H. Binici, O. Aksogan, E.B. Görür, H. Kaplan, M.N. Bodur, Performance of ground blast furnace slag and ground basaltic pumice concrete against seawater attack, *Construction and Building Materials* 22 (7) (2008) 1515–1526.
- [150] A.B. Hossain, S. Shrestha, J. Summers, Properties of concrete incorporating ultrafine fly ash and silica fume, *transportation research record*, *Journal of the Transportation Research Board* 2113 (2009) 41–46.
- [151] M.S. Cülfik, T. Özturan, Mechanical properties of normal and high strength concretes subjected to high temperatures and using image analysis to detect bond deteriorations, *Construction and Building Materials* 24 (8) (2010) 1486–1493.
- [152] S. Kourounis, S. Tsvilis, P.E. Tsakiridis, G.D. Papadimitriou, Z. Tsiabouki, Properties and hydration of blended cements with steelmaking slag, *Cement and Concrete Research* 37 (6) (2007) 815–822.
- [153] T.A. Söylev, C. McNally, M.G. Richardson, The effect of a new generation surface-applied organic inhibitor on concrete properties, *Cement and Concrete Composites* 29 (5) (2007) 357–364.
- [154] M. Ohno, T. Sugiyama, T. Sugamata, A. Ohta, Impact of lignin-based AE water-reducing agent, and BNS- and PCE-based superplasticizers on the properties of hardened concrete, *ACI Special Publication*, SP 262, American Concrete Institute, 2009, pp. 371–380.
- [155] M.S. Morsy, S.H. Alsayed, M. Aql, Effect of elevated temperature on mechanical properties and microstructure of silica flour concrete, *International Journal of Civil & Environmental Engineering* 10 (1) (2010) 1–6.
- [156] T.A. Söylev, M.G. Richardson, Corrosion inhibitors for steel in concrete: state-of-the-art report, *Construction and Building Materials* 22 (4) (2008) 609–622.
- [157] A. Laukaitis, J. Keriene, M. Kligys, D. Mikulskis, L. Lekunaite, Influence of amorphous nanodispersive SiO₂ additive on structure formation and properties of autoclaved aerated concrete materials, *Science-Medziagotyra* 16 (3) (2010) 257–263.
- [158] P. Chindaprasirt, S. Hatanaka, T. Chareerat, N. Mishima, Y. Yuasa, Cement paste characteristics and porous concrete properties, *Construction and Building Materials* 22 (5) (2008) 894–901.
- [159] L. Gündüz, The effects of pumice aggregate/cement ratios on the low-strength concrete properties, *Construction and Building Materials* 22 (5) (2008) 721–728.
- [160] W.C. Tang, Y. Lo, A. Nadeem, Mechanical and drying shrinkage properties of structural-graded polystyrene aggregate concrete, *Cement and Concrete Composites* 30 (5) (2008) 403–409.
- [161] B. Chen, C. Fang, Contribution of fibres to the properties of EPS lightweight concrete, *Magazine of Concrete Research* 61 (9) (2009) 671–678.

- [162] İ.B. Topçu, B. Işıkdag, Effect of expanded perlite aggregate on the properties of lightweight concrete, *Journal of Materials Processing Technology* 204 (1–3) (2008) 34–38.
- [163] E. Sancak, Y.D. Sari, O. Simsek, Effects of elevated temperature on compressive strength and weight loss of the light-weight concrete with silica fume and superplasticizer, *Cement and Concrete Composites* 30 (8) (2008) 715–721.
- [164] P.L. Domone, A review of the hardened mechanical properties of self-compacting concrete, *Cement and Concrete Composites* 29 (1) (2007) 1–12.
- [165] G.F. Kheder, R.S. Al Jadiri, New method for proportioning self-consolidating concrete based on compressive strength requirements, *ACI Materials Journal* 107 (5) (2010) 490–497.
- [166] M. Şahmaran, I.Ö. Yaman, M. Tokyay, Transport and mechanical properties of self consolidating concrete with high volume fly ash, *Cement and Concrete Composites* 31 (2) (2009) 99–106.
- [167] V.B. Bosiljkov, D. Duh, V. Bosiljkov, R. Zarnic, Time evolution of properties of SCC mixtures produced using crushed limestone aggregate and high content of limestone filler, *Design, Production and Placement of Self-Consolidating Concrete*, RILEM Bookseries, Vol. 1, 2010, pp. 317–327, Part 7.
- [168] P. Nanthagopalan, M. Santhanam, Fresh and hardened properties of self-compacting concrete produced with manufactured sand, *Cement and Concrete Composites* 33 (3) (2011) 353–358.
- [169] F.M. Almeida Filho, B.E. Barragán, J.R. Casas, A.L.H.C. El Debs, Hardened properties of self-compacting concrete — a statistical approach, *Construction and Building Materials* 24 (9) (2010) 1608–1615.
- [170] A.K. Schindler, R.W. Barnes, J.B. Roberts, S. Rodriguez, Properties of self-consolidating concrete for prestressed members, *Materials Journal* 104 (1) (2007) 53–61.
- [171] P. Paultre, K.H. Khayat, D. Cusson, S. Tremblay, Structural performance of self-consolidating concrete used in confined concrete columns, *ACI Structural Journal* 102 (4) (2005) 560–568.
- [172] E. Ozbay, A. Oztas, A. Baykasoglu, H. Ozbebek, Investigating mix proportions of high strength self compacting concrete by using Taguchi method, *Construction and Building Materials* 23 (2) (2009) 694–702.
- [173] A. Castel, T. Vidal, R. François, Bond and cracking properties of self-consolidating concrete, *Construction and Building Materials* 24 (7) (2010) 1222–1231.
- [174] M. Liu, Self-compacting concrete with different levels of pulverized fuel ash, *Construction and Building Materials* 24 (7) (2010) 1245–1252.
- [175] O. Esping, Effect of limestone filler BET(H₂O)-area on the fresh and hardened properties of self-compacting concrete, *Cement and Concrete Research* 38 (7) (2008) 938–944.
- [176] T.Y. Lo, P.W.C. Tang, H.Z. Cui, A. Nadeem, Comparison of workability and mechanical properties of self-compacting lightweight concrete and normal self-compacting concrete, *Materials Research Innovations* 11 (1) (2007) 45–50.
- [177] S.C. Kou, C.S. Poon, Properties of self-compacting concrete prepared with coarse and fine recycled concrete aggregates, *Cement and Concrete Composites* 31 (9) (2009) 622–627.
- [178] A.C. Aydin, Self compactability of high volume hybrid fiber reinforced concrete, *Construction and Building Materials* 21 (6) (2007) 1149–1154.
- [179] M. Hunger, A.G. Entrop, I. Mandilaras, H.J.H. Brouwers, M. Founti, The behavior of self-compacting concrete containing micro-encapsulated Phase Change Materials, *Cement and Concrete Composites* 31 (10) (2009) 731–743.