

## Dense nanostructured zirconia compacts obtained by colloidal filtration of binary mixtures

R. Benavente<sup>a</sup>, M.D. Salvador<sup>a</sup>, M.C. Alcázar<sup>b</sup>, R. Moreno<sup>b,\*</sup>

<sup>a</sup> *Instituto de Tecnología de Materiales, Universitat Politècnica de València, 46022 Valencia, Spain*

<sup>b</sup> *Instituto de Cerámica y Vidrio, CSIC, Kelsen 5, 28049 Madrid, Spain*

Received 27 September 2011; received in revised form 18 October 2011; accepted 19 October 2011

Available online 3 November 2011

### Abstract

As starting materials two commercial nanosized zirconias doped with 3 mol% of Y<sub>2</sub>O<sub>3</sub> were used: a powder of about 100 nm (TZ3YE, Tosoh, Japan) and a colloidal suspension of about 15 nm (Mel Chemicals, UK). Colloidal stability in water was studied for both zirconias in terms of zeta potential as a function of deflocculant concentration and pH. Concentrated suspensions were prepared by dispersing the powder in the colloidal suspension to solids loadings ranging from 5 to 30 vol.% using a sonication probe to achieve dispersion. The rheological behavior was optimized in terms of solids content, deflocculant content and sonication time. Optimized suspensions with up to 25 vol.% solids showed a nearly Newtonian behavior and extremely low viscosities and maintain stable for long times (days) which is an important drawback of conventional nanoparticle suspensions. Samples obtained by slip casting in plaster moulds were used for dynamic sintering studies and dense, nanostructured specimens were obtained at temperatures of 1300–1400 °C.

© 2011 Elsevier Ltd and Techna Group S.r.l. All rights reserved.

**Keywords:** A. Suspensions; Y-TZP; Rheology; Nanoparticles

### 1. Introduction

Yttria stabilized tetragonal zirconia polycrystalline (Y-TZP) ceramics are used in a variety of structural and functional applications due to their high strength, high toughness and good wear resistance over a wide temperature range [1–3]. As a biomaterial the most important application of Y-TZP was related to the manufacture of ball heads for total hip replacement, although this application has been stopped and it has received a growing interest for dental applications [4,5].

Y-TZP ceramics belong to the family of transformation toughened ceramics [6,7], which main feature consists in a microstructure completely formed by metastable tetragonal grains at room temperature that can undergo transformation to monoclinic. This is accomplished by a volume increase of 3–4 vol.%, which is the origin of a compressive stress field that operates inversely to the tensile stress that leads the crack and stops it. Factors affecting the phase transformation volume are

the grain size of the tetragonal phase, the amount of stabilizer, and the restraining conditions [8–10]. One important feature of Y-TZP is the superplasticity, that is, the capacity of a polycrystal to support great elongation at high temperature and low stress [11,12].

TZP materials were largely studied over the 80s and 90s, where the main objective was to obtain fully dense tetragonal zirconia at typical temperatures of 1400–1500 °C. Typical grain sizes of the sintered materials were by 0.5–2.0 μm, depending on sintering temperature, holding time, and physicochemical properties of the starting powders [8,9,13,14]. Fracture toughness as high as 12–14 MPa m<sup>-1/2</sup> were obtained and hardness values were by 12–14 GPa.

Moreover, a great effort was devoted to the production of pure and controlled Y-TZP powders in order to obtain dense, fine grained materials at lower sintering temperatures. Different chemical routes, such as sol–gel technology and coprecipitation methods were optimized to achieve dense materials by pressureless sintering methods [15,16]. Nanostructured ceramics display a range of enhanced properties compared to those obtained with submicrometer counterparts [17,18]. However the processing of nanopowders and its further densification to

\* Corresponding author.

E-mail address: [rmoreno@icv.csic.es](mailto:rmoreno@icv.csic.es) (R. Moreno).

obtain dense nanostructures is difficult because of the strong tendency to agglomeration and spontaneous grain growth during sintering [19,20]. To overcome the densification problems pressure assisted sintering techniques have been used, such as hot pressing, and more recently, electric field-assisted sintering (FAST), also known as spark plasma sintering (SPS) [21,22]. Other authors have investigated the possibility of using two-step sintering to achieve high densities while maintaining fine grain sizes [23–25].

Colloidal processing is a powerful way for the processing of nanoparticles that can be maintained far apart each other using deflocculants that help to control the interparticle forces during all processing stages [26–28]. Thus, the colloidal approach has demonstrated its suitability for the production of uniform, dense green bulk bodies from nanopowders [29,30].

The synthesis and colloidal processing of nanozirconia powders has been largely studied [31–35]. Some of these studies have reported the isoelectric point of different powders and the effect of different kinds of deflocculants on the stability, as well as the rheological behavior of concentrated suspensions. In these studies, the dispersion with anionic polyelectrolytes like those based on polyacrylic acid [32,33], cationic polyelectrolytes like polyethylenimine [34], or rhamnolipid biosurfactants [35], for example, have been described in detail for different nanozirconias with average sizes ranging from 15 nm to 60 nm.

The aim of this work was to study the colloidal processing and the rheological behavior of concentrated bimodal suspensions consisting of a mixture of a commercial nanosized powder of Y-TZP and a colloidal suspension of undoped zirconia to produce homogeneous green bodies with high density by slip casting. The obtained compacts were sintered to high density while maintaining controlled grain size.

## 2. Experimental

As starting materials two commercial nanosized zirconias doped with 3 mol% of  $Y_2O_3$  were used: a powder (TZ3YE, Tosoh, Japan), and a colloidal suspension (Mel Chemicals, UK). The former is a powder supplied in the form of spherical granules with a typical diameter below 100 nm. The last is formed by nanoparticles of 15 nm and it is supplied as an aqueous colloidal suspension with pH  $\sim 3$ , and a solids content of 5 vol.% (23 wt%).

The physicochemical characteristics of the TZ3Y powder are the following. The specific surface area, determined using the single-point BET method (Monosorb Surface Area Analyser, MS-13, Quantachrome Corporation, Boynton Beach, USA) after degassing at 150 °C, was  $14.5 \pm 0.5 \text{ m}^2 \text{ g}^{-1}$ . The density (measured by He-pycnometry, with a Multipycnometer, Quantachrome Co., USA), was  $5.9 \pm 0.2 \text{ g cm}^{-3}$ . The BET diameter calculated from the surface area was 70 nm. The colloidal suspension contains particles with an average particle size of 15 nm, and the specific surface area of dried powders was  $\sim 15 \text{ m}^2 \text{ g}^{-1}$ . The thermo-gravimetric analysis of the TZ3Y nanopowders revealed a weight loss of  $\sim 0.5\%$ , whereas the dry solids obtained from the colloidal suspension revealed a weight

loss of  $\sim 6\%$ , thus demonstrating the presence of some organic additive that could difficult the adsorption of deflocculants. The morphology of the as-received powder was observed by field emission gun scanning electron microscopy (FE-SEM, Hitachi S-4700 type I, Tokyo, Japan), and transmission electron microscopy (TEM, H7100, Hitachi, Japan). The crystalline phases were identified by X-ray diffraction (XRD) (Bruker D8 Advance, Karlsruhe, Germany) and using the Garvie's approach the ratio of tetragonal phase (density =  $6.07 \text{ g cm}^{-3}$ , ASTM 83-113) and monoclinic phase (density =  $5.82 \text{ g cm}^{-3}$ , ASTM 37-1484), was found to be 82/18 the resulting density being  $6.01 \text{ g cm}^{-3}$ . Thermogravimetric analysis was performed using a Netzsch apparatus (STA 409, Germany).

All suspensions were prepared in deionised water. The colloidal stability of the nanosuspensions was studied measuring the zeta potential as a function of pH using a Zetasizer NanoZS instrument (Malvern, UK), based in the laser Doppler velocimetry technique. Different dilutions were tested to measure the zeta potential with the best accuracy, which was reached for a concentration of 0.01 wt%, using KCl  $10^{-2} \text{ M}$  as inert electrolyte. pH values were determined with a pH-meter (716 DMS Titrimo, Metrohm, Switzerland) and were adjusted with HCl and KOH solutions ( $10^{-2} \text{ M}$ ). To improve the dispersion state, some sonication times were tested using an ultrasounds probe (UP 400S, Dr. Hielscher GmbH, Germany) in order to avoid agglomerates. A sonication time of 2 min was used for the preparation of diluted suspensions for zeta potential measurements.

According to previous tests, the TZ3Y suspension can be prepared to high solids loadings without any deflocculant. However, to enhance the dispersion of the powder in the colloidal suspension a polyacrylic-acid based deflocculant (Duramax D3005, Rohm & Haas, USA) was successfully added to concentrations of 1, 2, and 3 wt% on a dry solids basis.

The rheological behavior of the TZ3Y nanopowder was optimized for a solids loading of 30 vol.% (72 wt%). Then, suspensions of the mixtures (Mel + Tosoh) were prepared by adding the TZ3Y nanopowder into the colloidal suspension to final solids loadings of 10, 15, 20, 25, and 30 vol.% (i.e. 40, 51, 60, 66, and 72 wt%, respectively). The rheological behavior of these nanosuspensions was determined using a rheometer (Haake RS50, Thermo, Karlsruhe, Germany) operating at controlled shear rate (CR) by loading the shear rate from 0 to  $1000 \text{ s}^{-1}$  in 5 min, maintaining at  $1000 \text{ s}^{-1}$  for 1 minute and unloading from 1000 to 0 in 5 min. The measurements were performed at 25 °C using a double-cone and plate system.

These suspensions were slip cast in plaster moulds to obtain discs with 20 mm in thickness. Green densities were measured by Hg immersion after drying for 48 h. Static sintering experiments were done to temperatures of 1300, 1350 and 1400 °C with heating and cooling rates of  $5 \text{ °C min}^{-1}$ . The annealing time selected was 2 h. The microstructures of diamond polished (down to  $1 \mu\text{m}$ ) samples were characterized by field emission gun-scanning electron microscopy. The crystallinity of the sintered specimens was determined by X-ray diffraction (XRD) (Bruker Advance D8, USA) with Cu  $K\alpha$

radiation. The sintered density was measured by Archimedes' method in water.

### 3. Results and discussion

Fig. 1 shows the morphology of the starting powders observed by TEM. The colloidal suspension shows regular, well-dispersed particles of nanometric size and without large agglomerates. The powder TZ3Y is supplied in the form of spherical granules with nanometric size ( $<100$  nm) in good agreement with the calculated BET mean diameter. TEM pictures show that primary particles are readily dispersed with some small agglomerates formed by several units.

The variation of zeta potential of TZ3Y powders as a function of pH is shown in Fig. 2 for suspensions dispersed with different concentrations of deflocculant. The isoelectric point (IEP) occurs at pH 3.2, and the zeta potential values are higher than 30 mV at pH  $> 7$ . The measured IEP is significantly lower than other values found in the literature for Y-TZP powders (typically within the range 6–8) [36,37], suggesting that some organic is present at the particles surface which modifies the surface behavior. The addition of PAA shifts the isoelectric point very slightly, until pH 2.6 for 3 wt% PAA. However, high absolute zeta potential values are reached at pH  $\geq 4$ . The small variation of the IEP with PAA confirms that it practically does

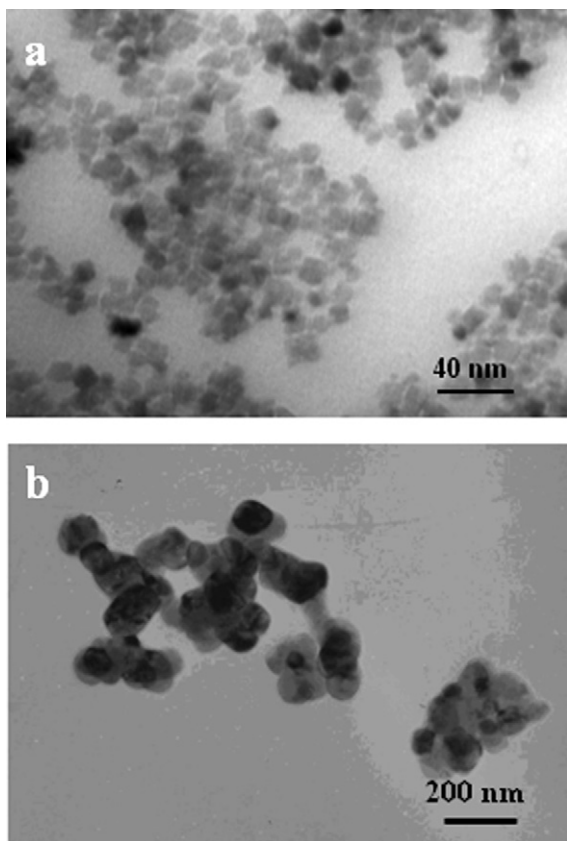


Fig. 1. Morphology of the starting zirconia powders as observed by transmission electron microscopy: (a) colloidal zirconia Mel and (b) Y-TZP powder Tosoh.

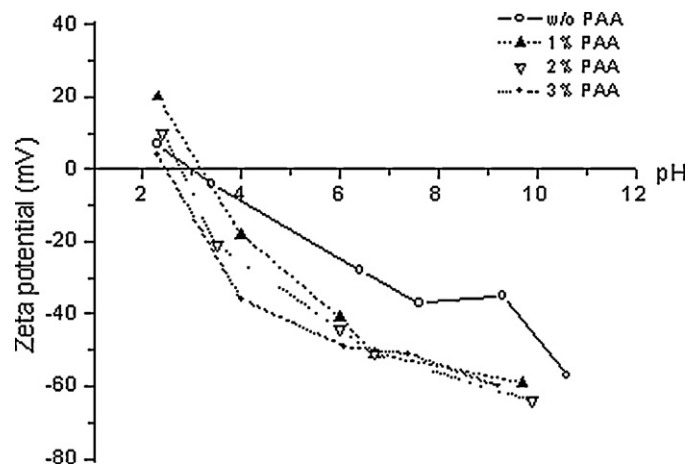


Fig. 2. Variation of zeta potential of TZ3Y suspension (Tosoh) as a function of pH for suspensions dispersed with different concentrations of deflocculant.

not adsorb due to the presence of other organics at the particles surface.

The variation of zeta potential versus pH for the colloidal suspension (Mel) without PAA and with PAA contents of 1, 2, and 3 wt% is shown in Fig. 3. The isoelectric point without adsorbed deflocculant occurs at pH 6.5, and decreases to near 6, 3.5, and 2.5 for 1, 2, and 3 wt% PAA, respectively. In addition to zeta potential, the particle size distribution of the colloidal suspensions was determined for all dispersing conditions. Fig. 4 shows the variation of average size as a function of pH for suspensions prepared with different PAA contents. It can be observed that for any deflocculant content the particle size strongly increases at a pH value that corresponds very accurately with the corresponding IEP. This illustrates the agglomeration of particles occurring at the vicinity of the IEP. It is also observed that the values of these maxima are lower as the PAA content increases thus demonstrating that the agglomeration level is lower for higher PAA concentration.

Concentrated suspensions of TZ3Y powder were prepared to solids loadings of 30 vol.% without PAA and with 1 wt% PAA. For both concentrations the effect of sonication time on

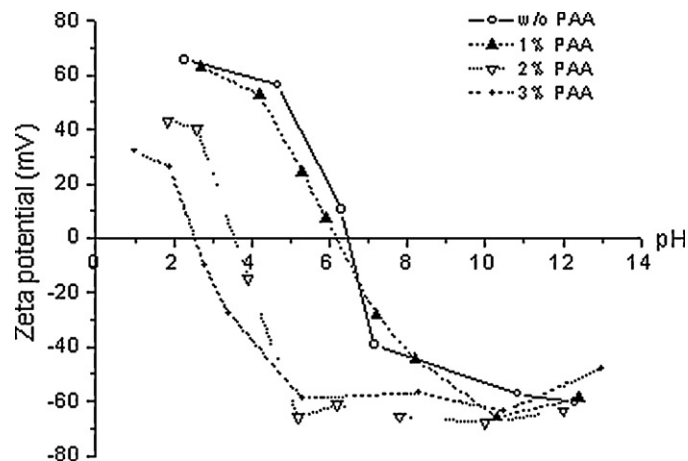


Fig. 3. Variation of zeta potential of colloidal zirconia (Mel) as a function of pH for suspensions dispersed with different concentrations of deflocculant.

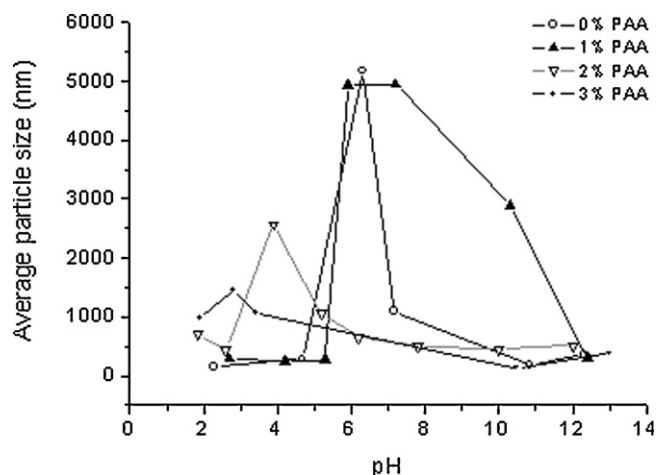


Fig. 4. Variation of mean particle size of colloidal zirconia (Mel) as a function of pH for suspensions dispersed with different concentrations of deflocculant.

suspension stability was studied. Figs. 5 and 6 show the flow curves of suspensions without and with PAA, respectively, homogenized by mechanical mixing without ultrasounds first, and with sonication times of 2, 4, and 6 min. In both cases there is a similar tendency according to which the suspensions prepared without ultrasounds exhibit a high viscosity and a broad thixotropic cycle, demonstrating that these suspensions have a complex behavior and particles develop some structure at rest. The application of ultrasounds strongly reduces both the viscosity and the time dependency, which becomes negligible in the case of suspensions without PAA. The comparison of both figures clearly shows that the addition of PAA increases both the viscosity and the thixotropy, that is, it has a deleterious effect on the suspensions stability.

According to these results concentrated suspensions of mixtures of both types of zirconia (colloidal and powder) were prepared without any deflocculant addition. Suspensions were prepared by adding TZ3Y powder to the colloidal suspension. The colloidal suspension has a solids content of 5 vol.% and TZ3Y powder was added until total zirconia concentrations of 10, 15, 20, and 30 vol.%. As in the case of TZ3Y suspensions

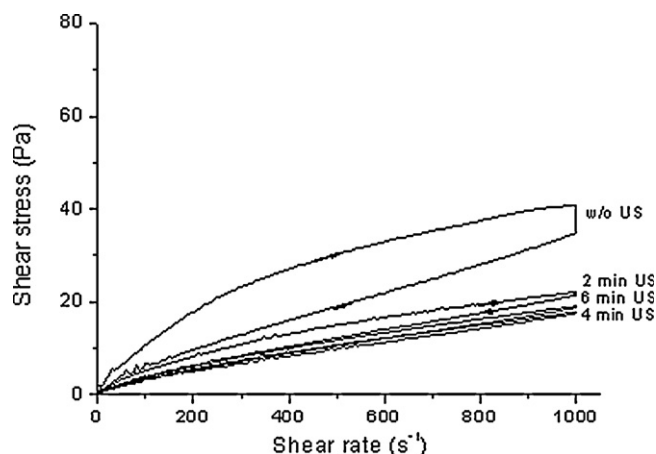


Fig. 5. Flow curves of 30 vol.% suspensions of TZ3Yzirconia (Tosoh) without deflocculant prepared without and with sonication for 2, 4, and 6 min.

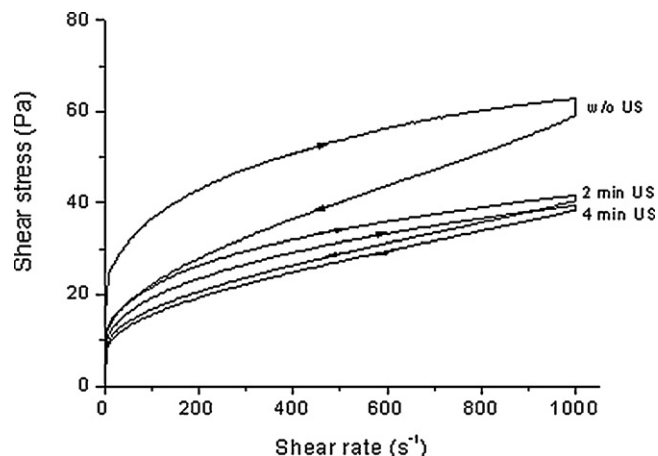


Fig. 6. Flow curves of 30 vol.% suspensions of TZ3Yzirconia (Tosoh) with 1 wt% of deflocculant prepared without and with sonication for 2, 4, and 6 min.

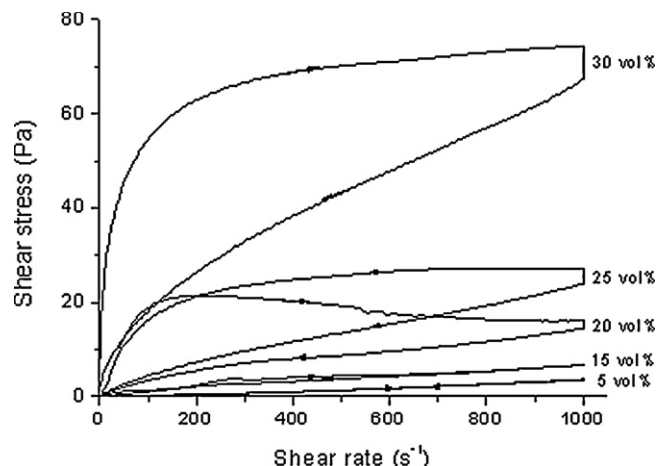


Fig. 7. Flow curves suspensions of mixtures of TZ3Yzirconia (Tosoh) and colloidal zirconia (Mel) prepared without sonication to different solids loadings (5–30 vol.%).

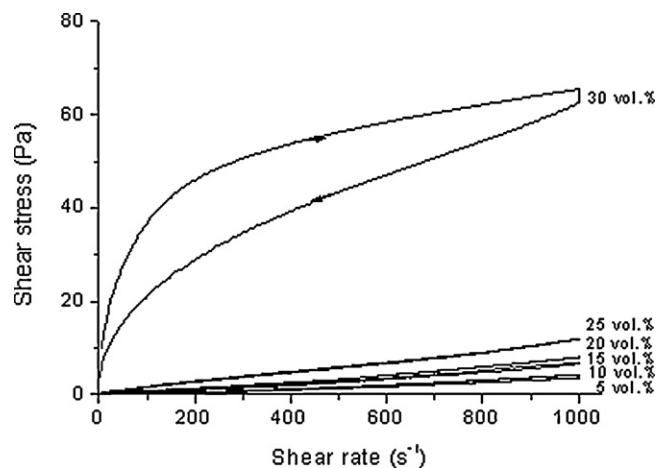


Fig. 8. Flow curves suspensions of mixtures of TZ3Yzirconia (Tosoh) and colloidal zirconia (Mel) prepared with 2 min sonication to different solids loadings (5–30 vol.%).



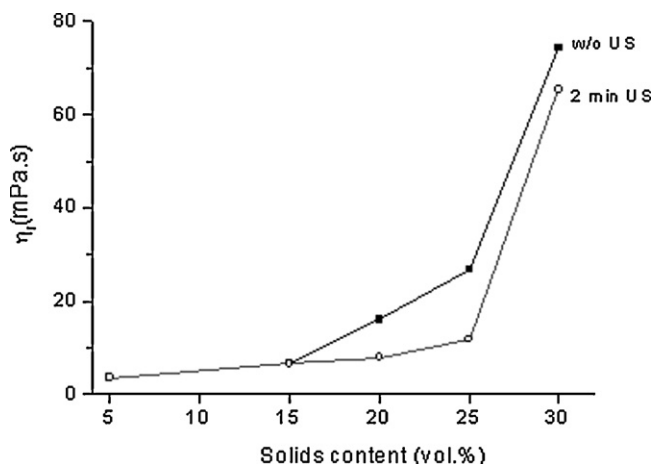


Fig. 9. Variation of high shear viscosity of suspensions of the mixtures as a function of solids loading, as-prepared and after 2 min sonication.

the effect of sonication on the rheological behavior was studied. Figs. 7 and 8 show the flow curves for the different solids loading for as-prepared suspensions without sonication and the same suspensions homogenized with 2 min US.

Suspensions prepared by mechanical mixing without sonication had some thixotropy above solid concentrations of 15 vol.%. However, optimized suspensions, i.e. those prepared with 2 min sonication, showed a nearly Newtonian behavior, excepting the most concentrated one that exhibited a shear thinning response with a broad thixotropic cycle. In spite of the high solids loadings achieved for these suspensions of nanoparticles viscosities are extremely low, thus facilitating shape forming. It is worthy to note that the pH value increased progressively from 2.8 to 5.2 as the solids loading increased from 5 to 30 vol.%, but the application of ultrasounds did not change the pH.

From these curves it is possible to draw the variation of viscosity with solids loading, as it is shown in Fig. 9 for suspensions with and without sonication. Viscosity values were

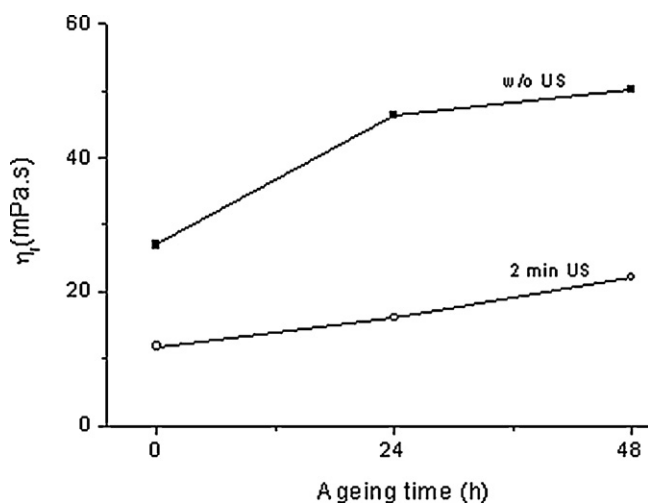


Fig. 10. Variation of viscosity with aging time for suspensions with 25 vol.% solids prepared without and with 2 min sonication.

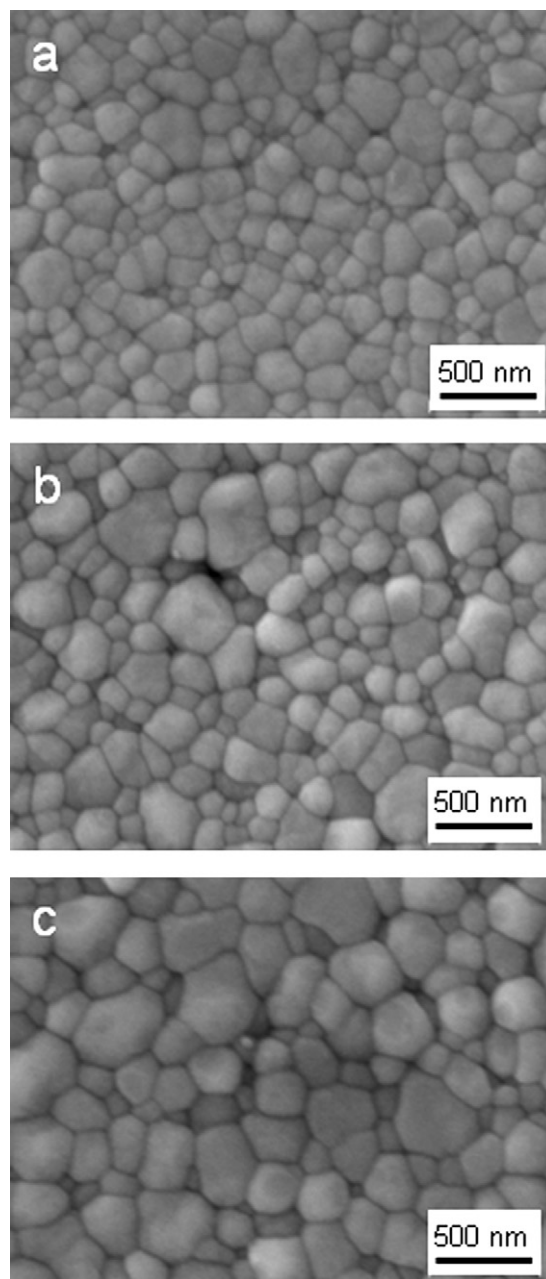


Fig. 11. FEG-SEM microstructure of cast specimens sintered at temperatures of 1300 °C (a), 1350 °C (b), and 1400 °C (c).

taken at a shear rate of  $1000 \text{ s}^{-1}$ , which can be assimilated to infinite shear rate extrapolation. The non-sonicated suspensions show an increase of viscosity at very low solids loadings, whereas suspensions sonicated for 2 min maintain very low viscosity until the maximum solids loading, where a sharp increase is also detected.

Sonication has an important effect on the rheological behavior of the suspensions and changes significantly their aging behavior. Fig. 10 compares the variation of viscosity with aging time for suspensions with 25 vol.% solids prepared without and with 2 min sonication. Viscosity significantly increases for non-sonicated suspensions but maintains nearly

constant for sonicated suspensions, thus meaning that the stability of these suspensions is preserved for longer times. This is an important point as it is frequently observed that concentrated suspensions of nanoparticles destabilize after short aging times of even a few hours.

These suspensions were slip cast and dried before sintering tests. The green density of the cast bodies seems to slightly increase with solids content from 55% to near 57% of theoretical. In Fig. 11 the FEG-SEM microstructure of specimens treated at temperatures of 1300, 1350, and 1400 °C are shown. Although the diffraction patterns are not shown to avoid unnecessary drawings the XRD analyses showed that there was practically no monoclinic phase (<5%). The particle size maintains in the nanometer size region, but a clear tendency to coarsening with increasing sintering temperature is observed. The average grain size (evaluated by the intercepting line method) increases from  $160 \pm 15$  nm to  $180 \pm 30$  nm and  $230 \pm 60$  nm for temperatures of 1300, 1350 and 1400 °C. As it can be seen not only the average size but also the deviation increases, that is, the distribution becomes broader as coarse grains are being formed at expenses of the smallest grains.

#### 4. Conclusions

It is possible to prepare concentrated, bimodal nanosuspensions of Y-TZP by mixing commercial dry powders with a colloidal suspension, with average diameters of 15 and <100 nm, respectively. The isoelectric point of the dry powder was lower than that reported for most Y-TZP powders (by 3.2), probably due to the presence of adsorbed organics. The colloidal suspension has a larger weight loss and then, higher content of organics, but the isoelectric point is 6.5, similar to most reported IEPs for Y-TZP powders. Then, bimodal mixtures must be prepared, the resulting pH being acidic. Concentrated suspensions were prepared without deflocculants up to solids contents of 30 vol.% (i.e. 72 wt%). Suspensions with minimum viscosity and thixotropy values were obtained by dispersing with ultrasounds for 2 min. These bimodal suspensions were cast on plaster moulds and the green densities increased very slightly with solids content, from 55% to near 57% of TD. Dense specimens with controlled size and homogeneous microstructure were obtained after sintering at temperatures of 1300, 1350 and 1400 °C, but the average grain size increased from  $160 \pm 15$  nm to  $180 \pm 30$  nm and  $230 \pm 60$  nm.

#### Acknowledgements

This work has been supported by Spanish Ministry of Science and Innovation (Projects MAT2009-14144-C03-02 and MAT2009-14369-C02-01). R. Moreno thanks to Universidad Politécnica de Valencia for the concession of a grant in the frame of its Programme of Support to R + D (PAID-02-11, R-1752).

#### Appendix A. Supplementary data

Supplementary data associated with this article can be found, in the online version, at [doi:10.1016/j.ceramint.2011.10.051](https://doi.org/10.1016/j.ceramint.2011.10.051).

#### References

- [1] R.C. Garvie, Structural applications of ZrO<sub>2</sub>-bearing materials, *Zirconia II*, Adv. Ceram., Vol. 12, ed. N. Claussen, et al. American Ceramic Society, Westerville, OH, 1984, 465–478.
- [2] B. Basu, J. Vleugels, O. van der Biest, Toughening tailoring of yttria-doped zirconia ceramics, *Mater. Sci. Eng. A* 380 (1–2) (2004) 215–221.
- [3] A.G. Evans, Perspective on the development of high-toughness ceramics, *J. Am. Ceram. Soc.* 73 (1990) 187–206.
- [4] J. Chevalier, A.H. De Aza, G. Fantozzi, M. Schehl, R. Torrecillas, Extending the lifetime of ceramic orthopaedic implants, *Adv. Mater.* 12 (2000) 1619–1621.
- [5] C. Piconi, W. Burger, H.G. Richter, A. Cittadini, G. Maccauro, V. Covacci, N. Bruzzese, G.A. Ricci, E. Marmo, Y-TZP ceramics for artificial joint replacements, *Biomaterials* 19 (1998) 1489–1494.
- [6] N. Claussen, “Microstructural design of zirconia-toughened ceramics (ZTC),” *Zirconia II*, Adv. Ceram., Vol. 12, ed. N. Claussen, et al. American Ceramic Society, Westerville, OH, 1984, 325–351.
- [7] M. Ruhle, A.H. Heuer, “Phase transformations in ZrO<sub>2</sub> containing ceramics: II, The martensitic reaction in t-ZrO<sub>2</sub>,” *Zirconia II*, Adv. Ceram., Vol. 12, ed. N. Claussen, et al. American Ceramic Society, Westerville, OH, 1984, 14–32.
- [8] F.F. Lange, Transformation-toughened ZrO<sub>2</sub>: correlation between grain size control and composition in the system ZrO<sub>2</sub>–Y<sub>2</sub>O<sub>3</sub>, *J. Am. Ceram. Soc.* 69 (3) (1986) 240–242.
- [9] R.H.J. Hannik, P.M. Kelly, B.C. Muddle, Transformation toughening in zirconia containing ceramics, *J. Am. Ceram. Soc.* 83 (3) (2000) 461–487.
- [10] B. Basu, J. Vleugels, O. van der Biest, Transformation behaviour of tetragonal zirconia. Role of dopant content and distribution, *Mater. Sci. Eng. A* 366 (2) (2004) 338–347.
- [11] F. Wakai, S. Sakaguchi, Y. Matsuno, Superplasticity of yttria-stabilized tetragonal ZrO<sub>2</sub> polycrystals, *Adv. Ceram. Mater.* 1 (1986) 259–263.
- [12] M. Jimenez-Melendo, A. Dominguez-Rodriguez, A. Bravo-Leon, Superplastic flow of fine-grained Y<sub>2</sub>O<sub>3</sub>-stabilized ZrO<sub>2</sub> polycrystals. Constitutive equation and deformation mechanisms, *J. Am. Ceram. Soc.* 81 (1998) 2761–2776.
- [13] R.A. Cutler, J.R. Reynolds, A. Jones, Sintering and characterization of polycrystalline monoclinic, tetragonal, and cubic zirconia, *J. Am. Ceram. Soc.* 75 (8) (1992) 2173–2183.
- [14] T.K. Gupta, J.H. Bechtold, R.C. Kuznickie, L.H. Cadoff, B.R. Rossing, Stabilization of tetragonal phase in polycrystalline zirconia, *J. Mater. Sci.* 12 (12) (1977) 2421–2426.
- [15] Better ceramics through chemistry, C.J. Brinker, D.E. Clark, D.R. Ulrich (Eds.), *Mat. Res. Soc. Proc.*, 32 North-Holland, New York (EEUU), 1984.
- [16] P. Durán, M. Villegas, J.F. Fernández, F. Capel, C. Moure, Theoretically dense and nanostructured ceramics by pressureless sintering of nanosized Y-TZP powders, *Mater. Sci. Eng. A* 232 (1) (1997) 168–176.
- [17] M. Mayo, Processing of nanocrystalline ceramics from ultrafine particles, *Int. Mater. Rev.* 41 (1996) 85–115.
- [18] M.A. Meyers, A. Mishra, D.J. Benso, Mechanical properties of nanocrystalline materials, *Prog. Mater. Sci.* 51 (2006) 427–556.
- [19] J.G.P. Binner, B. Vaidyanathan, Processing of bulk nanostructured ceramics, *J. Eur. Ceram. Soc.* 28 (2008) 1329–1333.
- [20] J.R. Groza, Sintering of nanocrystalline powder, *Int. J. Powder Metall.* 35 (7) (1999) 59–66.
- [21] D. Yang, R. Raj, H. Conrad, Enhanced sintering rate of zirconia (3Y-TZP) through the effect of a weak dc electric field on grain growth, *J. Am. Ceram. Soc.* 93 (10) (2010) 2935–2937.
- [22] J. Langer, M.J. Hoffmann, O. Guillon, Electric field assisted sintering in comparison with the hot pressing of yttria stabilized zirconia, *J. Am. Ceram. Soc.* 94 (1) (2011) 24–31.

- [23] C. Robert, F. Ansart, C. Deloget, M. Gaudon, A. Rousset, Dense yttria stabilized zirconia: sintering and microstructure, *Ceram. Int.* 29 (2) (2003) 151–158.
- [24] X.H. Wang, P.L. Chen, I.W. Chen, Two-step sintering of ceramics with constant grain size. I:  $Y_2O_3$ , *J. Am. Ceram. Soc.* 89 (2) (2006) 431–437.
- [25] J. Binner, K. Annappoorani, A. Paul, I. Santacruz, B. Vaidhyanathan, Dense nanostructured zirconia by two stage conventional/hybrid microwave sintering, *J. Eur. Ceram. Soc.* 28 (2008) 973–977.
- [26] F.F. Lange, Powder processing science and technology for increased reliability, *J. Am. Ceram. Soc.* 72 (91) (1989) 3–15.
- [27] R. Moreno, The role of slip additives in tape casting technology. I: solvents and dispersants, *Am. Ceram. Soc. Bull.* 71 (10) (1992) 1521–1531.
- [28] W.M. Sigmund, N.S. Bell, L. Bergström, Novel powder-processing methods for advanced ceramics, *J. Am. Ceram. Soc.* 83 (10) (2000) 1557–1574.
- [29] I. Santacruz, M.I. Nieto, J. Binner, R. Moreno, Gel casting of aqueous suspensions of  $BaTiO_3$  nanopowders, *Ceram. Int.* 5 (2009) 321–326.
- [30] L.P. Meier, L. Urech, L.J. Gauckler, Tape casting of nanocrystalline ceria gadolinia powder, *J. Eur. Ceram. Soc.* 24 (2004) 3753–3758.
- [31] O. Vasylykiv, Y. Sakka, Synthesis and colloidal processing of zirconia nanopowder, *J. Am. Ceram. Soc.* 84 (11) (2001) 2489–2494.
- [32] I. Santacruz, K. Annappoorani, J.G.P. Binner, Preparation of high solids content nanozirconia suspensions, *J. Am. Ceram. Soc.* 91 (2) (2008) 398–405.
- [33] B.P.C. Ragupathy, J.G.P. Binner, Spray granulation of nanometric zirconia particles, *J. Am. Ceram. Soc.* 94 (1) (2011) 42–48.
- [34] J. Wang, L. Gao, Adsorption of polyethylenimine on nanosized zirconia particles in aqueous suspensions, *J. Colloid Interface Sci.* 216 (1999) 436–439.
- [35] M. Biswas, A.M. Raichur, Electrokinetic and rheological properties of nano zirconia in the presence of rhamnolipid biosurfactant, *J. Am. Ceram. Soc.* 91 (19) (2008) 3197–3201.
- [36] R. Moreno, J. Requena, J.S. Moya, Slip casting of yttria-stabilized tetragonal zirconia polycrystals, *J. Am. Ceram. Soc.* 71 (1988) 1036.
- [37] E. López-López, C. Baudín, R. Moreno, Synthesis of zirconium titanate-based materials by colloidal filtration and reaction sintering, *Int. J. Appl. Ceram. Technol.* 5 (4) (2008) 394–400.