

Investigation on ferromagnetic and ferroelectric properties of (La, K)-doped $\text{BiFeO}_3\text{--BaTiO}_3$ solid solution

Anurak Prasatkhetragarn^{a,*}, Pantip Muangkonkad^a, Parichart Aommongkol^a,
Pongsakorn Jantaratana^b, Naratip Vittayakorn^c, Rattikorn Yimnirun^d

^aDepartment of Materials Science, School of Science, University of Phayao, Phayao 56000, Thailand

^bDepartment of Physics, Faculty of Science, Kasetsart University, Bangkok 10900, Thailand

^cDepartment of Chemistry, Faculty of Science, King Mongkut's Institute of Technology Ladkrabang, Bangkok 10520, Thailand

^dSchool of Physics, Institute of Science, Suranaree University of Technology, and Synchrotron Light Research Institute (Public Organization), Nakhon Ratchasima 30000, Thailand

Available online 24 October 2012

Abstract

Multiferroic materials of $\text{BiFeO}_3\text{--BaTiO}_3$ solid solution have been fabricated in order to improve ferromagnetic and ferroelectric properties. The effects of La (1 mol%) and K (varied from 0.5–5 mol%) doped $0.75\text{BiFeO}_3\text{--}0.25\text{BaTiO}_3$ on phase formation, ferromagnetic and ferroelectric properties have been investigated and discussed. The rhombohedral perovskite phase of specimens was characterized by XRD technique. Fracture morphology reveals the grain growth characteristics with increasing K content. (La, K)-doped $0.75\text{BiFeO}_3\text{--}0.25\text{BaTiO}_3$ with La = 1 mol% and K = 3 mol% exhibits the highest remnant polarization and remnant magnetization.

© 2012 Elsevier Ltd and Techna Group S.r.l. All rights reserved.

Keywords: Ferroelectric properties; Magnetic properties; Multiferroic

1. Introduction

BiFeO_3 -based compounds have received considerable attention and have been studied extensively, because they exhibit both ferroelectric and ferromagnetic characteristics; thus they provide the possibility of applications in devices such as nonvolatile memory, sensors, waveguides, modulators, switches, phase invertors, rectifiers, etc. [1–4]. Bulk BiFeO_3 ceramic possesses a ferroelectric Curie temperature (T_C) of 1103 K (830 °C) and an antiferromagnet Néel temperature (T_N) of 643 K (370 °C) [3]. However, bulk BiFeO_3 ceramic has some disadvantages such as it is difficult to prepare pure single phase BiFeO_3 , and BiFeO_3 -based materials have a low electrical resistivity. The relatively high conductivity of BiFeO_3 is believed to be due to the degradation of Fe^{3+} species to Fe^{2+} species, thus creating oxygen vacancies for charge compensation.

These problems have prevented the material's practical applications as piezoelectric or magnetoelectric functional components [3].

Processing BiFeO_3 with other perovskite structured materials, such as BaTiO_3 (BT) and PbTiO_3 , would prevent the formation of secondary phases [5–7] and enhance the electrical resistivity. In addition, Ti substitution at the Fe sites can increase the magnetization of the novel compounds [7]. Prior research, S.O. Leontsev and R.E. Eitel have been prepared on Mn-doped $(1-x)\text{BiFeO}_3\text{--}x\text{BaTiO}_3$, it was found that ceramics with 25 mol% BT showed the highest value of dielectric and ferroelectric properties. It is expected that with continuous processing improvements and composition modification, the $0.75\text{BiFeO}_3\text{--}0.25\text{BaTiO}_3$ (0.75BF–0.25BT) system will form the basis of an important family of high-performance lead free piezoelectric ceramics [8].

Although the perovskite structure of these solid solutions has been found to be stable at room temperature, their ferromagnetism is still weak. To improve the ferroelectric and ferromagnetic properties, (La, K)-doped

*Corresponding author. Tel.: +6654 466666; fax: +6654 466664.

E-mail addresses:

prasatkhetragarn@yahoo.com (A. Prasatkhetragarn),

rattikorn@g.sut.ac.th (R. Yimnirun).

0.75BiFeO₃–0.25BaTiO₃ ceramics, with fixed La of 1 mol% and varied K of 0.5, 1.0, 3.0 and 5.0 mol% will be investigated and discussed, of which no report has been found to date.

2. Experimental

Multiferroic materials of (La, K)-doped 0.75BiFeO₃–0.25BaTiO₃ were prepared by a solid state mechanical milling technique. The effects of La (Fixed 1 mol%) and K (varied from 0.5–5 mol%) addition on ferroelectric and ferromagnetic properties of 0.75BiFeO₃–0.25BaTiO₃ have also been investigated and discussed. Stoichiometric mixtures of starting reagent-grade oxides of BaCO₃ (98.5%), Bi₂O₃ (99.9%), K₂CO₃ (99.9%), Fe₂O₃ (99.9%) La₂O₃ (98.5%) and TiO₂ (anatase-structure) (99.9%) were ball milled in ethanol with yttria-stabilized zirconia balls for 24 h. To achieve phase homogeneity, the powders were calcined in a cover alumina crucible at a temperature of 900 °C for 6 h [8]. The calcined powders were then uniaxially cold-pressed at 2500 psi into disc-shaped pellets with a diameter of 10 mm and a thickness of 1 mm with 3 wt% poly (vinyl alcohol) (PVA) added as a binder. Following binder burnout at 500 °C, the pellets were sintered at 1025 °C for 2 h with a heating/cooling rate of 5 °C/min. The phase structure of the ceramics was analyzed via X-ray diffraction (XRD; Philips XPert Pro). The microstructures of the sintered samples were examined using scanning electron microscopy (SEM; JEOL JSM-840A). The room temperature ferroelectric and ferromagnetic properties were determined using a simple Sawyer–Tower circuit (at fixed measuring frequency of 50 Hz) and Vibrating Sample Magnetometer (VSM), respectively.

3. Results and discussion

Fig. 1 shows the XRD patterns of (La, K)-doped 0.75BiFeO₃–0.25BaTiO₃ ceramics with fixed La-doped of 1 mol% and varied K-doped of 0.5, 1.0, 3.0 and 5.0 mol%, prepared by a solid-state reaction. The ceramics were sintered at 1025 °C for 2 h with a heating/cooling rate of 5 °C/min. XRD patterns clearly present the perovskite structure without traces of secondary phase for all compositions. As reported earlier, the BF–xBT system with $x < 33$ mol% is expected to have rhombohedrally-distorted perovskite structure [8]. For the samples in this present study, no characteristic splitting associated with (1 1 0) could be seen in the XRD patterns, possibly due to a small rhombohedral distortion [8]. However, all observed diffraction lines of (La, K)-doped BF–BT compounds suggest the presence of the rhombohedral-rich phase with increasing K content of up to 5 mol%, as sharpening of (0 1 0), (0 2 0) and (2 1 1) peaks is noticed.

Fig. 2 shows the fracture morphology of (La, K)-doped 0.75BiFeO₃–0.25BaTiO₃ ceramics, with fixed La of 1 mol% and varied K of 0.5, 1.0, 3.0 and 5.0 mol%, characterized by scanning electron microscopy (SEM) technique. The SEM micrographs clearly elucidate the

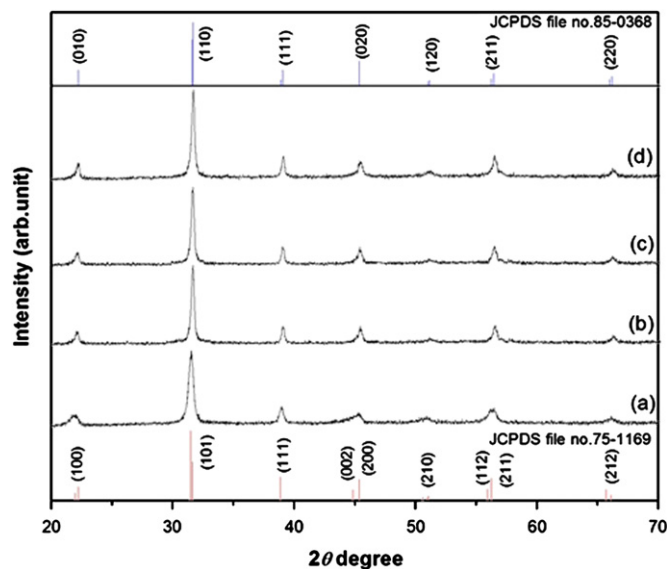


Fig. 1. XRD patterns of (La, K)-doped 0.75BiFeO₃–0.25BaTiO₃ ceramics with fixed La of 1 mol% and varied K of (a) 0.5, (b) 1.0, (c) 3.0 and (d) 5.0 mol% K content. (For interpretation of the references to color in this figure legend, the reader is referred to the web version of this article.)

grain growth characteristics with increasing K content. The observation could be caused by the La and K doping in the crystal structure are affected on the movement of grain boundaries of the specimens. A similar behavior is observed in other K-doped LiNbO₃ systems [9].

The polarization-electric field (P – E) hysteresis loops of (La, K)-doped 0.75BiFeO₃–0.25BaTiO₃ ceramics, with fixed La of 1 mol% and varied K of 0.5, 1.0, 3.0 and 5.0 mol%, measured at 10 kV/cm are presented in Fig. 3. It is seen that remnant polarization (P_r) and coercive field (E_c) slightly increase with increasing K content. The decrease in the remnant polarization at K-doped for 5.0 mol% could be caused by rhombohedral-rich phase in this composition [10]. It is of great interest to observe that the ferroelectric properties of 0.75BiFeO₃–0.25BaTiO₃ ceramics can be controlled by addition of La and K. An enhancement of ferroelectric properties is probably due to Ba, La and K ions replacing Bi ions in the perovskite unit cell, releasing the dislocation of the Fe ion in the [1 1 1] direction. This dislocation originated from Bi to O orbital hybridization [8], resulting in the emergence of the Cm phase and breaking the toroidal order of the BiFeO₃ structure ($R3c$). In fact, the hybridization of Ti–O orbitals supports the dislocation of the Ti ion in the [1 0 0] direction [8].

Fig. 4 shows the M – H hysteresis loops of (La, K)-doped 0.75BiFeO₃–0.25BaTiO₃ ceramics with fixed La and varied K. In some of these doped materials, slim hysteresis loops are observed in the ceramics with 0.5 mol% K content. As the K content increases from 0.5 to 3 mol%, the remnant magnetization (M_r) increases and reaches a maximum value of $M_r \approx 0.6$ emu/g at 3 mol%. Upon further increasing the K content from 3 mol% to 5 mol%, M_r decreases. Nevertheless, the coercive field (H_c) is seen to decrease with increasing K content, the lowest H_c is also seen at 3.0 mol% ($H_c \approx 1.5$ kOe). Usual

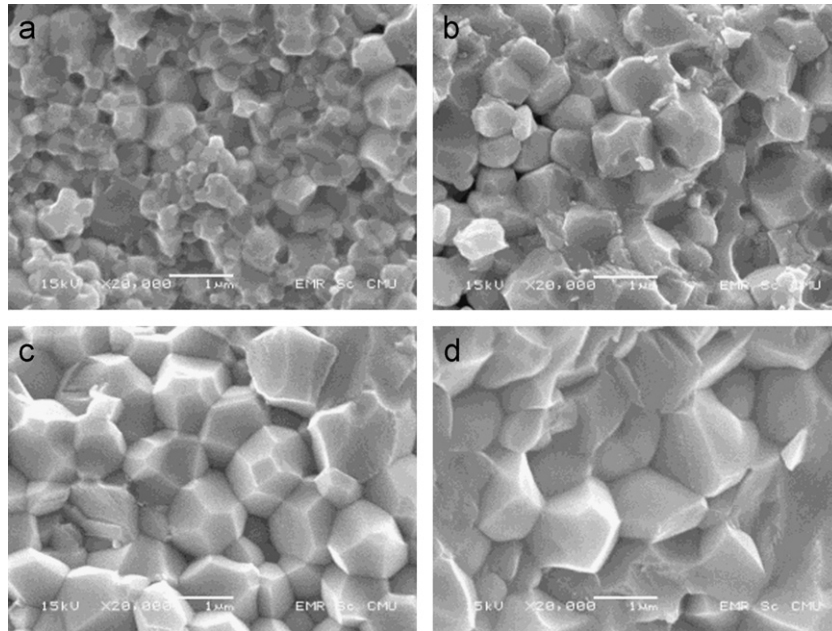


Fig. 2. SEM micrographs of (La, K)-doped $0.75\text{BiFeO}_3\text{--}0.25\text{BaTiO}_3$ ceramics, with fixed La of 1 mol% and varied K of (a) 0.5, (b) 1.0, (c) 3.0 and (d) 5.0 mol%. (For interpretation of the references to color in this figure legend, the reader is referred to the web version of this article.)

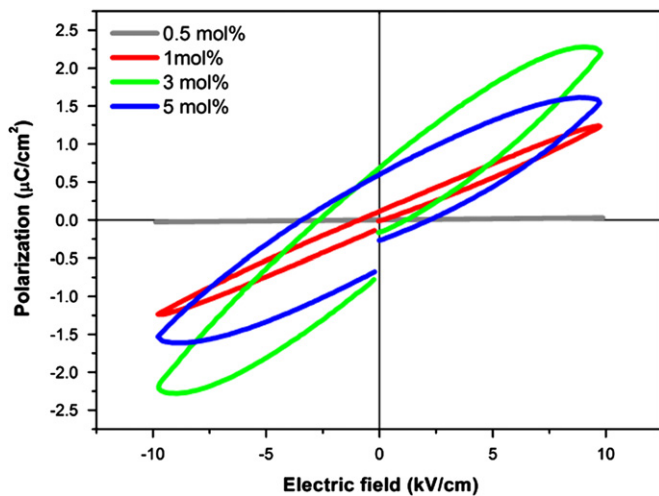


Fig. 3. P – E loops of (La, K)-doped $0.75\text{BiFeO}_3\text{--}0.25\text{BaTiO}_3$ ceramics with fixed La of 1 mol% and varied K of 0.5, 1.0, 3.0 and 5.0 mol%. (For interpretation of the references to color in this figure legend, the reader is referred to the web version of this article.)

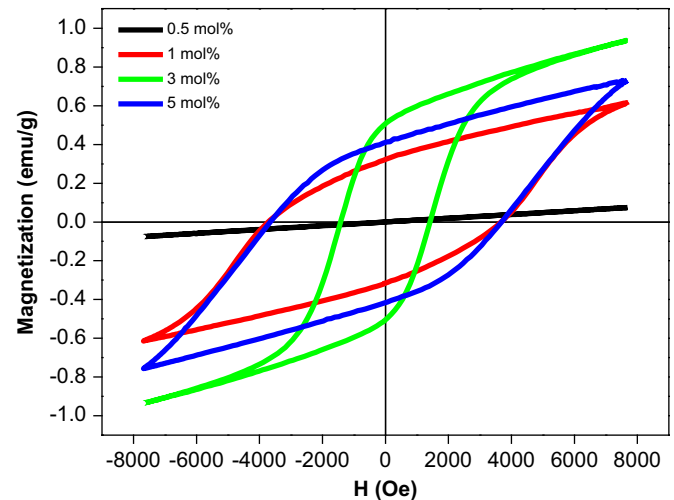


Fig. 4. M – H loops of (La, K)-doped $0.75\text{BiFeO}_3\text{--}0.25\text{BaTiO}_3$ ceramics with fixed La of 1 mol% and varied K of 0.5, 1.0, 3.0 and 5.0 mol%. (For interpretation of the references to color in this figure legend, the reader is referred to the web version of this article.)

polycrystalline BiFeO_3 also exhibits a very small magnetization and M – H hysteresis loops without spontaneous magnetization [11]. For the current samples, a larger induced magnetization was observed. These results clearly demonstrate that the (La, K)-doped BF–BT prepared in this study can induce a ferromagnetic state that has remnant magnetization. This result supports the interpretation of a releasing of the spin-cyclical arrangement, associated with breaking of its periodicity [8]. The appearance of ferromagnetism in solid solution systems with 1 to 5 mol% K content can be attributed to either the canting of the antiferromagnetically ordered spins by a structural distortion [7,8] or the breakdown of the balance

between the antiparallel sublattice magnetization of Fe^{3+} due to metal ion substitution with a different valence [1,8]. Similar magnetic behavior with the presence of ferromagnetism was observed in a previous study on magnetization in the $\text{BiFeO}_3\text{--}\text{PbTiO}_3$ solid solution system [7].

4. Conclusions

In this study, (La, K)-doped $0.75\text{BiFeO}_3\text{--}0.25\text{BaTiO}_3$ ceramics with fixed La of 1 mol% and varied K of 0.5, 1.0, 3.0 and 5.0 mol%, have been fabricated to improve the

ferroelectric and ferromagnetic properties. The XRD study shows that single phase perovskite ceramics are successfully obtained with sintering temperature of 1025 °C for 2 h. The fracture SEM micrographs indicate the grain growth behavior with increasing K content. In addition, ferromagnetic and ferroelectric properties increase with increasing K content. More importantly, this study suggests that phase formation behavior, microstructure, ferroelectric and ferromagnetic properties of 0.75BiFeO₃–0.25BaTiO₃ can be controlled by the addition of La and K.

Acknowledgements

This work was supported by the Industry/University Cooperative Research Center (I/U CRC) in HDD Component, Faculty of Engineering, Khon Kaen University, and School of Science, University of Phayao.

References

- [1] T. Shao, A. Scholl, F. Zavaliche, K. Lee, M. Barry, A. Doran, M.P. Cruz, Y.H. Chu, C. Ederer, N.A. Spaldin, R.R. Das, D.M. Kim, S.H. Baek, C.B. Eom, R. Ramesh, Electrical control of antiferromagnetic domain in multiferroic BiFeO₃ film at room temperature, *Nature Materials* 5 (2006) 823–829.
- [2] H. Fukumura, S. Matsui, N. Tonari, T. Nakamura, N. Hasuike, K. Nishio, T. Isshiki, H. Harima, K. Kisoda, Synthesis and characterization of Mn-doped BiFeO₃ nanoparticles, *Acta Physica Polonica A* 116 (2009) 47–50.
- [3] A.Z. Simões, A.H.M. Gonzalez, L.S. Cavalcante, C.S. Riccardi, E. Longo, J.A. Varela, Ferroelectric characteristics of BiFeO₃ thin films prepared via a simple chemical solution deposition, *Journal of Applied Physics* 101 (2007) 1–6 074108.
- [4] V.A. Khomchenko, D.A. Kiselev, M. Kopcewicz, M. Maglione, V.V. Shvartsman, P. Borisov, W. Kleemann, A.M.L. Lopes, Y.G. Pogorelov, J.P. Araujo, R.M. Rubinger, N.A. Sobolev, J.M. Vieira, A.L. Kholkin, Doping strategies for increased performance in BiFeO₃, *Journal of Magnetism and Magnetic Materials* 321 (2009) 1692–1698.
- [5] R. Rai, I. Bdikin, M.A. Valente, A.L. Kholkin, Ferroelectric and ferromagnetic properties of Gd-doped BiFeO₃–BaTiO₃ solid solution, *Materials Chemistry and Physics* 119 (2010) 539–545.
- [6] R.A.M. Gotardo, I.A. Santos, L.F. Cótica, E.R. Botero, D. Garcia, J.A. Eiras, Improved ferroelectric and magnetic properties of monoclinic structured 0.8BiFeO₃–0.2BaTiO₃ magnetoelectric ceramics, *Scripta Materialia* 61 (2009) 508–511.
- [7] W. Sakamoto, A. Iwata, M. Moriya, T. Yogo, Electrical and magnetic properties of Mn-doped 0.7BiFeO₃–0.3PbTiO₃ thin films prepared under various heating atmospheres, *Materials Chemistry and Physics* 116 (2009) 536–541.
- [8] S.O. Leontsev, R.E. Eitel, Dielectric and piezoelectric properties in Mn-modified (1–x)BiFeO₃–xBaTiO₃ ceramics, *Journal of the American Ceramic Society* 92 (2009) 2957–2961.
- [9] G.I. Malovichko, V.G. Grachev, L.P. Yurchenko, V.Ya. Proshko, E.P. Kokanyan, V.T. Gabrielyan, Improvement of LiNbO₃ microstructure by crystal growth with potassium, *Physica Status Solidi (a)* 133 (1992) K29–K32.
- [10] A. Prasatkhetragarn, M. Unruan, A. Ngamjarurojana, Y. Laosiritaworn, S. Ananta, R. Yimnirun, D.P. Cann, Effects of Zr/Ti ratio on dielectric and ferroelectric properties of 0.8Pb(Zr_xTi_{1–x})O₃–0.2Pb(Co_{1/3}Nb_{2/3})O₃ ceramics, *Current Applied Physics* 9 (2009) 802–806.
- [11] A.K. Pradhan, K. Zhang, D. Hunter, J.B. Dadson, G.B. Loutts, P. Bhattacharya, R. Katiyar, J. Zhang, D.J. Sellmyer, U.N. Roy, Y. Cui, A. Burger, Magnetic and electrical properties of single-phase multiferroic BiFeO₃, *Journal of Applied Physics* 97 (2005) 093903.