

Synthesis and luminescence properties of nitrided lanthanum magnesium hexaluminate $\text{LaMgAl}_{11}\text{O}_{19}$ phosphors

Xin Min, Minghao Fang*, Zhaohui Huang, Yan'gai Liu, Chao Tang, Tingting Qian, Xiaowen Wu

School of Materials Science and Technology, China University of Geosciences (Beijing), Beijing 100083, PR China

Received 3 July 2013; received in revised form 29 August 2013; accepted 29 August 2013

Available online 7 September 2013

Abstract

Nitrided $\text{LaMgAl}_{11}\text{O}_{19}$ phosphors were prepared by a two-step method involving synthesis at 1550 °C for 4 h, trituration, and firing at 1650 °C for 5 h under a nitrogen atmosphere. Nitrogen was doped into $\text{LaMgAl}_{11}\text{O}_{19}$ and bonded with aluminium atoms. The nitrided $\text{LaMgAl}_{11}\text{O}_{19}$ phosphors showed plate-like morphology with a rough surface and exhibited strong blue emission at 442 nm and 450 nm, which may be attributed to the energy transition between defect levels. A weak emission band at 590 nm was ascribed to the transition between the V_{Al} acceptor and the valence band, which was excited at 254 nm.

© 2013 Elsevier Ltd and Techna Group S.r.l. All rights reserved.

Keywords: $\text{LaMgAl}_{11}\text{O}_{19}$; Oxynitrides; Phosphors; Luminescence

1. Introduction

Lanthanum magnesium hexaluminate, $\text{LaMgAl}_{11}\text{O}_{19}$ (LMA), has garnered the attention of researchers because of its high-temperature performance and properties [1,2]. Thus, LMA has been widely investigated for many applications, such as a thermal barrier coating, combustion catalyst support, and active element of solid-state lasers [1–5]. Among this body of research, studies of the material's optical properties (*i.e.*, for laser and phosphor hosts) are of particular interest in this work. Because it is similar to other hexaluminates, the crystalline structure of $\text{LaMgAl}_{11}\text{O}_{19}$ is of the magnetoplumbite type with a $P6_3/mmc$ space group [6–9]. Materials with this structure can be easily doped or replaced with other transition-metal and rare-earth ions and their performance thereby rendered tuneable [7,8,10–17]. Thus, current work on $\text{LaMgAl}_{11}\text{O}_{19}$ phosphors shows that the material exhibits various efficient luminescent properties when doped with transition-metal and rare-earth ions. For example, $\text{LaMgAl}_{11}\text{O}_{19}$ doped with Tb^{3+} ions emits weakly in both the blue and orange regions of the visible spectrum and strongly in the green region when excited by ultraviolet light with a wavelength of 261 nm [16]; $\text{LaMgAl}_{11}\text{O}_{19}$ doped with Mn^{2+}

and Tb^{3+} is known to emit in the green region when excited by ultraviolet radiation [18].

Although extensive work on the luminescence properties of doped $\text{LaMgAl}_{11}\text{O}_{19}$ has been reported in detail, little published work concerning $\text{LaMgAl}_{11}\text{O}_{19}$ oxynitride phosphors exists. Compared with oxide phosphors, the nitrogen–metal bonds in oxynitride-based materials are more strongly covalent than their oxygen–metal counterparts [19]. Oxynitrides doped with rare-earth metal ions can also shift their excitation and emission spectra across a broad range (*e.g.*, $\text{Sr}_2\text{SiO}_4\text{:Eu} \rightarrow \text{SrSi}_2\text{O}_2\text{N}_2\text{:Eu} \rightarrow \text{Sr}_2\text{Si}_5\text{N}_8\text{:Eu}$ phosphors and $\text{BaAl}_{2-x}\text{Si}_x\text{O}_{4-x}\text{N}_x\text{:Eu}^{2+}$ phosphors emitting green light) [20–22]. Thus, research on $\text{LaMgAl}_{11}\text{O}_{19}$ oxynitrides has been deemed highly significant.

The authors synthesised nitrided $\text{LaMgAl}_{11}\text{O}_{19}$, a blue-emitting phosphor, by initially preparing $\text{LaMgAl}_{11}\text{O}_{19}$ as a precursor and then introducing nitrogen by high-temperature solid-state reaction under a nitrogen atmosphere. The structural and luminescent characteristics of the phosphors are herein discussed.

2. Experimental

$\text{LaMgAl}_{11}\text{O}_{19}$ powders were synthesised by solid-state reaction in air using $\text{Al}(\text{OH})_3$ (purity: 99.9%), La_2O_3 (purity: 99.95%),

*Corresponding author. Tel./fax: +86 10 82322186.

E-mail address: fmh@cugb.edu.cn (M. Fang).

and $\text{Mg}(\text{OH})_2$ (purity: 99.9%) as raw materials. La_2O_3 powder could rapidly absorb atmospheric water, so it was heated to 1100°C for 1 h and weighed at a temperature above 100°C . The stoichiometric powders were mixed and ball-milled in ethanol for 6 h to homogenise them before being dried at 75°C . The mixtures were calcined at 1550°C for 4 h, tritured, and fired at 1650°C for 5 h under a nitrogen atmosphere to form nitrided $\text{LaMgAl}_{11}\text{O}_{19}$, using coke particles to surround and protect the material.

The phase and crystal structure of the phosphors were identified by X-ray diffraction (XRD, D8 Advance diffractometer, Bruker Corporation, Germany) using $\text{Cu-K}\alpha$ radiation ($\lambda=1.5406\text{ \AA}$). A PHI 5300 X-ray photoelectron spectroscopy system (XPS, Perkin Elmer, USA) was used to determine the chemical states of La 3d, Mg 1s, Al 2p, and O 1s with a chamber base pressure of approximately 10^{-7} Torr. XPS data were acquired using Mg $\text{K}\alpha$ X-rays at a take-off angle of 45° and a total power of 400 W. Micrographs of the phosphors were obtained using a scanning electron microscope (SEM, JSM-6460LV, JEOL, Japan) equipped with an energy dispersive analysis (EDS) attachment. Photoluminescent emission (PL) and excitation (PLE) spectra were recorded using a PMT and xenon lamp (PSI, South Korea). All measurements were carried out at room temperature.

3. Results and discussion

3.1. Phase composition analysis

Fig. 1 shows the XRD patterns of the as-prepared $\text{LaMgAl}_{11}\text{O}_{19}$ and nitrided $\text{LaMgAl}_{11}\text{O}_{19}$ powders: the pattern of the nitrided $\text{LaMgAl}_{11}\text{O}_{19}$ phosphor matched that of the as-prepared $\text{LaMgAl}_{11}\text{O}_{19}$ (JCPDS card number 26-0873). The observed XRD pattern shows that the nitrided $\text{LaMgAl}_{11}\text{O}_{19}$ also possessed a magnetoplumbite structure and was included in the $\text{P6}_3/\text{mmc}$ space group, showing a structure similar to that of other hexagonal, rare-earth aluminates. This result demonstrated that doping with nitrogen did not change the crystal structure of LMA. The XRD spectrum of the material in the range from 33.5° to 35° is shown in Fig. 1(b), which indicates that the peaks broadened and split into two different peaks as nitrogen was incorporated into the $\text{LaMgAl}_{11}\text{O}_{19}$

lattice, thus changing the symmetry of the corresponding crystal planes.

3.2. Chemical states of La, Mg, O, Al, and N in nitrided $\text{LaMgAl}_{11}\text{O}_{19}$ phosphors

Fig. 2(a)–(f) shows the high-resolution XPS spectra of the La 3d, Mg 2p, Al 2p, O 1s, and N 1s states of nitrided $\text{LaMgAl}_{11}\text{O}_{19}$ phosphors prepared by the aforementioned two-step process. The La $3d_{5/2}$ and La $3d_{3/2}$ peaks at 835.1 eV and 851.8 eV are shown in Fig. 2, which match the spectrum for an La_2O_3 standard with peak values of 834 eV and 851 eV reported in the literature [23,24]. These values indicated the presence of a La^{3+} species. Moreover, characteristic satellites were observed at approximately 4 eV to each of the $3d_{5/2}$ and $3d_{3/2}$ peaks, which are attributed to a ligand-to-metal charge-transfer process [25]. In Fig. 2(b), the Mg 2p peak of 50.2 eV is consistent with the value of 50.2 eV for crystalline MgAl_2O_4 [26]. The O 1s spectrum shown in Fig. 2c is composed of three peaks at 529 eV, 530.7 eV, and 531.84 eV, which are due to the lattice oxygen of the La–O octahedral structure [27], the lattice oxygen of the spinel structure [28], and surface-adsorbed oxygen [29], respectively. The Al 2p spectra shown in Fig. 2(d) exhibit an asymmetrical peak composed of two sub-peaks at 73.6 eV and 74.3 eV; these peaks were fitted with the Bes of AlN and Al_2O_3 at 73.5 eV and 74.5 eV within experimental error bounds [30]. Fig. 2(f) shows two peaks in the spectrum of N 1s at 398 eV and 400 eV. Thus, it can be concluded that some nitrogen was doped into the $\text{LaMgAl}_{11}\text{O}_{19}$ lattice and that it replaced the position held by oxygen in the lattice of LMA to form nitrided $\text{LaMgAl}_{11}\text{O}_{19}$.

According to the results of XRD analysis discussed above, this luminescent nitrided $\text{LaMgAl}_{11}\text{O}_{19}$ phosphor exhibited the same structure as $\text{LaMgAl}_{11}\text{O}_{19}$. Fig. 3 shows the crystal structure of nitrided $\text{LaMgAl}_{11}\text{O}_{19}$, also composed of two spinel layers and an LaAlO_3 layer, which exhibited reflective symmetry in its lattice. The aluminium and lanthanum atoms were both surrounded by six oxygen atoms; however, the La–O bonds were more stable than the Al–O bonds. Thus, the nitrogen atoms were doped into the structure, replacing the oxygen atoms to form more stable bonds with aluminium atoms, as shown in Fig. 3(b).

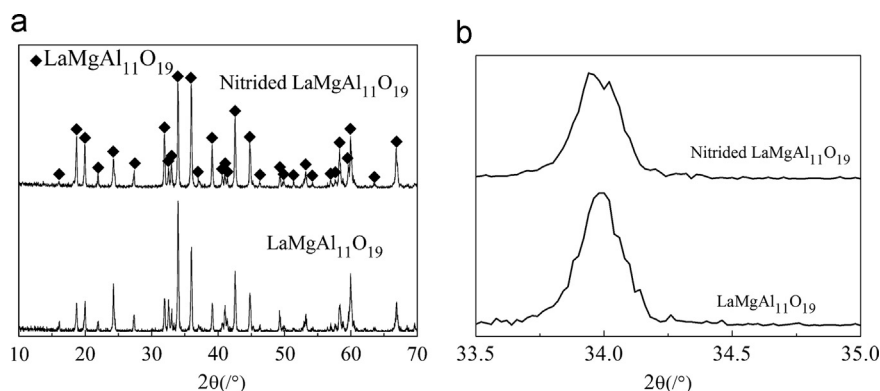


Fig. 1. XRD patterns of as-prepared $\text{LaMgAl}_{11}\text{O}_{19}$ and nitrided $\text{LaMgAl}_{11}\text{O}_{19}$ phosphors. (a) $10^\circ \leq 2\theta \leq 70^\circ$ and (b) $33.5^\circ \leq 2\theta \leq 35^\circ$.

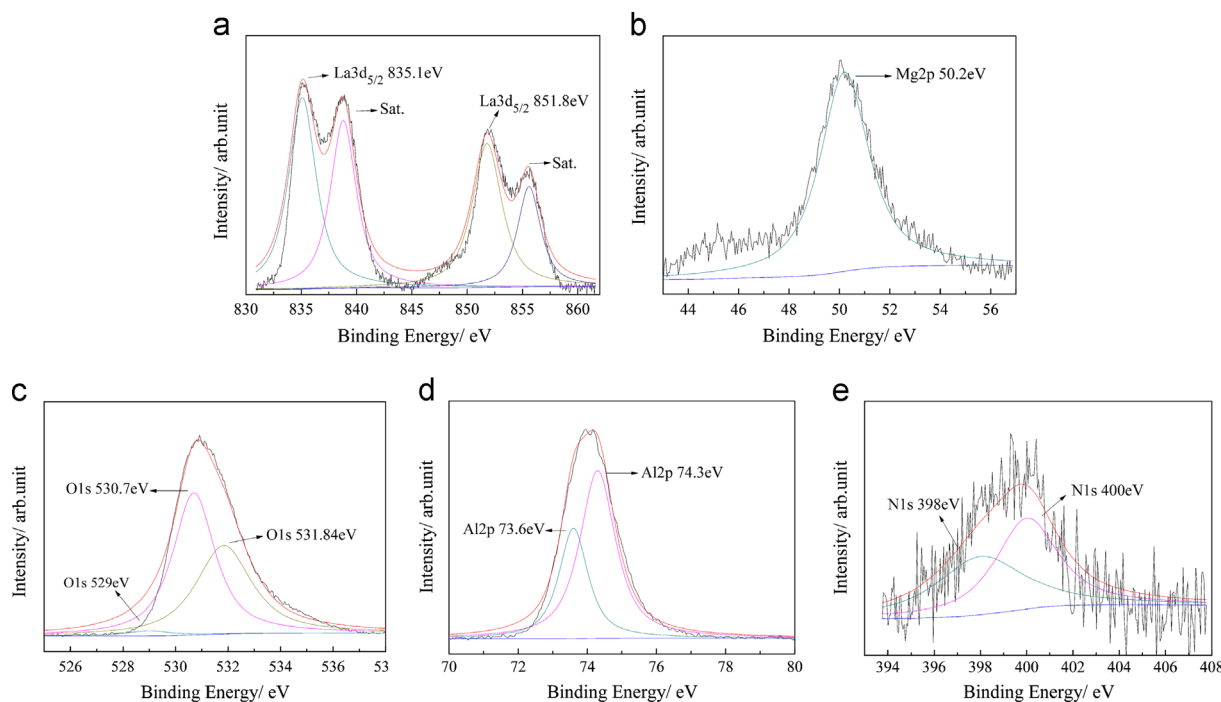


Fig. 2. XPS spectra with peak fitting of nitrided $\text{LaMgAl}_{11}\text{O}_{19}$ phosphors. (a), (b), (c), and (d) correspond to La(3d), Mg(1s), Al(2p), O(1s), and N(1s) XPS spectra, respectively.

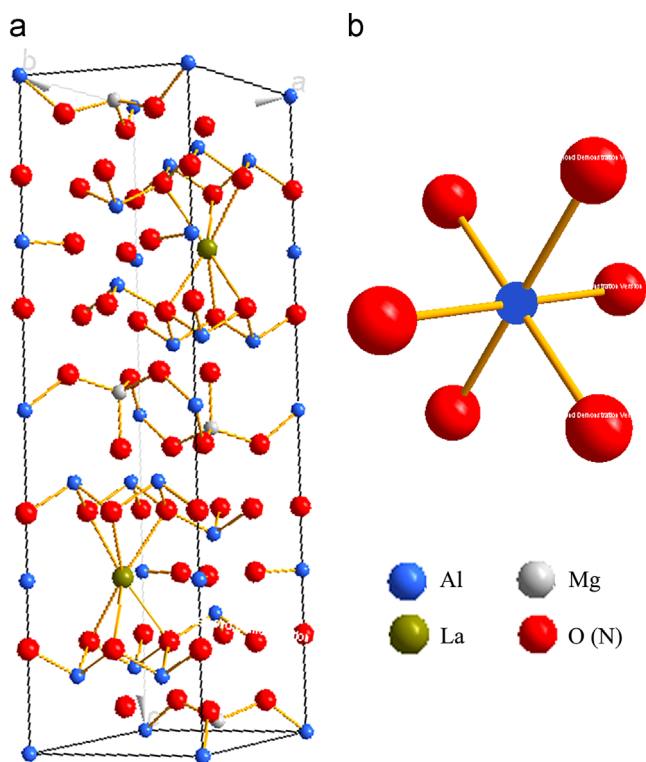


Fig. 3. Crystal structures of nitrided $\text{LaMgAl}_{11}\text{O}_{19}$. (a) The unit cell structure of nitrided $\text{LaMgAl}_{11}\text{O}_{19}$ and (b) the coordination environment of Al.

3.3. FESEM micrographs and EDS analysis

Fig. 4 shows FESEM photographs of as-prepared $\text{LaMgAl}_{11}\text{O}_{19}$ and nitrided $\text{LaMgAl}_{11}\text{O}_{19}$ powders. The morphology

of the LMA grains shows a plate-like structure (Fig. 4(a)). The large area covered by the low-magnification SEM micrographs of prepared nitrided LMA particles also reveals plate-like crystals with non-uniform sizes and shapes (Fig. 4(b)). Magnifying the image in Fig. 4(b) to yield Fig. 4(c) demonstrated that the nitrided LMA platelets had rough surfaces with smaller particles attached. As shown in the figure, the size of these attached particles ranged from 300 to 500 nm. The EDS patterns (Fig. 4(d)) of these smaller particles also revealed that the main composition of this area was nitrided $\text{LaMgAl}_{11}\text{O}_{19}$ composed of the stoichiometric elements La, Mg, Al, O, and N.

3.4. Photoluminescence properties of the nitrided $\text{LaMgAl}_{11}\text{O}_{19}$ phosphors

The excitation and emission spectra of the $\text{LaMgAl}_{11}\text{O}_{19}$ powders and nitrided $\text{LaMgAl}_{11}\text{O}_{19}$ phosphors are shown in Fig. 5(a)–(c). The pure $\text{LaMgAl}_{11}\text{O}_{19}$ material did not show any luminescence, as shown in Fig. 5. The excitation spectrum of $\text{LaMgAl}_{11}\text{O}_{19}$ doped with nitrogen appeared when monitoring the strongest 440-nm emission. It is well known that La^{3+} ions are stable with a complete inner shell electronic structure and a stable outermost electronic structure of $5s^25p^6$, resulting in the non-luminous character of pure LMA [13,16]. The spectrum in Fig. 5(a) shows a broad, intense band between 250 and 350 nm, with two distinct bands at 254 nm and 307 nm and additional weak bands at 320 nm and 344 nm. Fig. 5(b) shows the emission spectrum of the nitrided $\text{LaMgAl}_{11}\text{O}_{19}$ phosphors, recorded under 254-nm excitation. The spectrum shows a broad blue emission band at 442 nm (2.8 eV) and a narrow red emission peak at 595 nm (2.1 eV). The literature [30] indicates that the emission at approximately 2.0 eV can be ascribed to V_{Al}

(the native aluminium vacancies). Previous studies [31,32] have confirmed that the acceptor level of V_{Al} is approximately 2.0 eV above the valence band. Therefore, the weak red emission at 595 nm may have been due to the direct radiative recombination between the V_{Al} acceptor and VB. Some research [32–35] also suggests that the emission peak at approximately 3.0 eV may be related to oxygen defect levels ($O_{(N)}$, redundant oxygen affected

by nitrogen from EDS analysis), which arise from the deformation of electron clouds between oxygen and doped nitrogen. As mentioned in the preceding discussion of the XPS and EDS analyses, nitrogen was doped into the $LaMgAl_{11}O_{19}$ material and occupied the sites formerly occupied by oxygen. Thus, the broad emission band at 442 nm can be ascribed to the transition between $O_{(N)}$ and an $O_{(N)}-V_{Al}$ complex. The spectrum of

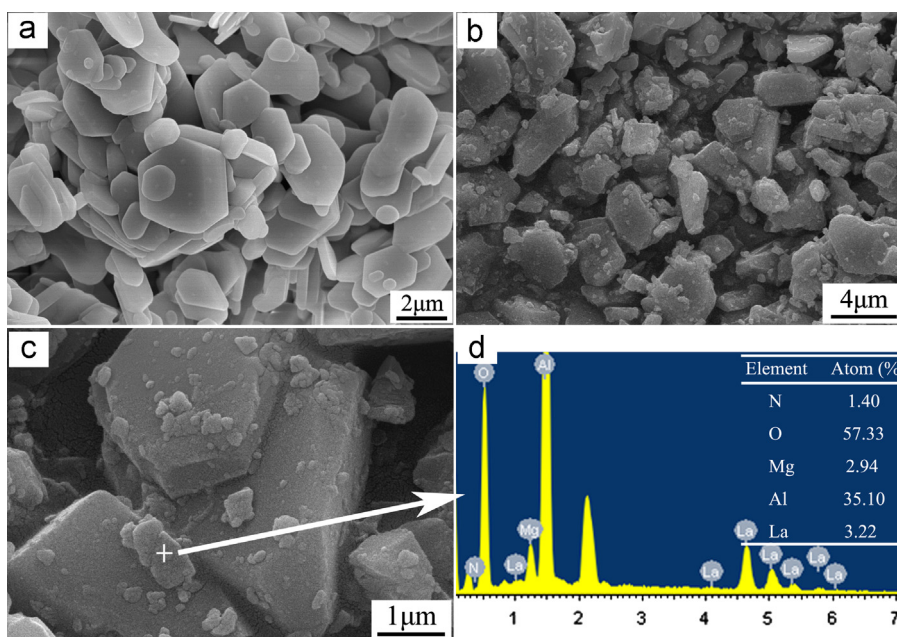


Fig. 4. FESEM micrographs and EDS patterns of as-prepared $LaMgAl_{11}O_{19}$ and nitrided $LaMgAl_{11}O_{19}$ phosphors. (a) SEM image of $LaMgAl_{11}O_{19}$, (b) SEM image of nitrided $LaMgAl_{11}O_{19}$, (c) surface micrograph of nitrided $LaMgAl_{11}O_{19}$ platelets, and (d) EDS analysis results.

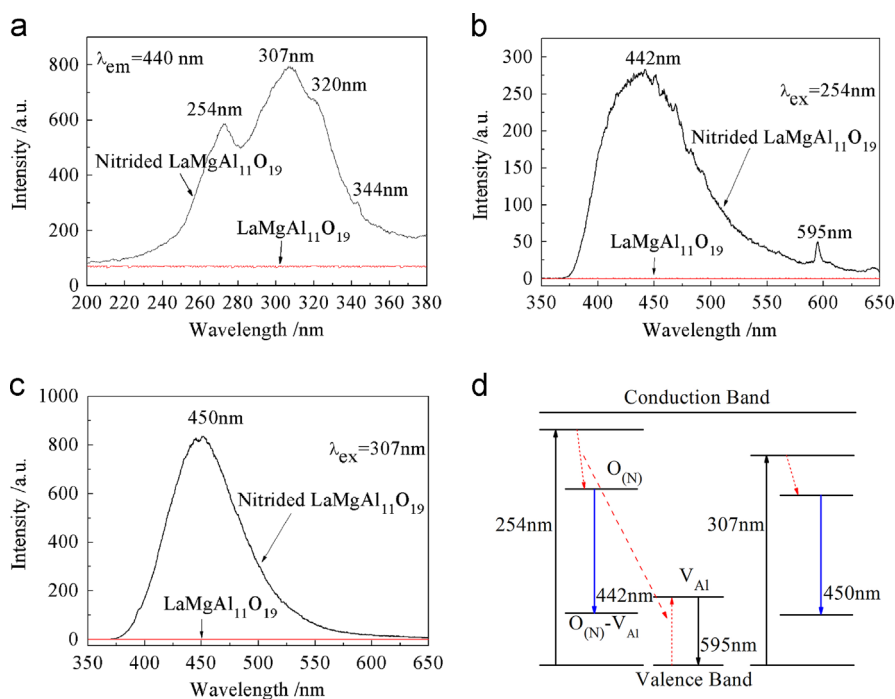


Fig. 5. Photoluminescence spectra of the as-prepared $LaMgAl_{11}O_{19}$ and nitrided $LaMgAl_{11}O_{19}$ phosphors. (a) Excitation spectrum ($\lambda_{em}=440$ nm), (b) emission spectrum ($\lambda_{ex}=254$ nm), (c) emission spectrum ($\lambda_{ex}=307$ nm), and (d) energy level transition diagram.

nitrided $\text{LaMgAl}_{11}\text{O}_{19}$ phosphors in Fig. 5(c) was excited at a wavelength of 307 nm. The spectrum only showed a strong emission peak at 450 nm (2.8 eV) in the form of a Gaussian curve. Thus, the mechanism of emission at 450 nm was similar to that at 442 nm. However, Fig. 5(c) also shows that there was no emission peak at approximately 595 nm, as the excitation energy was lower than that at 254 nm and no excess energy was converted for the emission at 595 nm. The corresponding energy level transition diagram is shown in Fig. 5(d).

4. Conclusions

In summary, nitrided $\text{LaMgAl}_{11}\text{O}_{19}$ was prepared by a two-step method. Nitrogen atoms were doped into the $\text{LaMgAl}_{11}\text{O}_{19}$ structure and bonded with aluminium atoms. The nitrided $\text{LaMgAl}_{11}\text{O}_{19}$ phosphors exhibited strong blue emission bands at 442 and 450 nm, which can be attributed to an energy transition involving oxygen-related defect levels. A weak emission band at 590 nm is ascribed to the transition between the V_{Al} acceptor and the valence band.

Acknowledgements

This work was financially supported by the National Natural Science Foundation of China (NSFC Grant no. 51172216) and the Fundamental Research Funds for the Central Universities (Grant no. 2652013051).

References

- [1] N.P. Bansal, D.M. Zhu, Thermal properties of oxides with magnetoplumbite structure for advanced thermal barrier coatings, *Surface and Coatings Technology* 202 (2008) 2698–2703.
- [2] X.L. Chen, Y. Zhao, W.Z. Huang, H.M. Ma, B.L. Zou, Y. Wang, X.Q. Cao, Thermal aging behavior of plasma sprayed $\text{LaMgAl}_{11}\text{O}_{19}$ thermal barrier coating, *Journal of the European Ceramic Society* 31 (2011) 2285–2294.
- [3] B. Jiang, M.H. Fang, Y.G. Liu, Z.H. Huang, P. Peng, J. Zhang, Mechanical and thermal properties of $\text{LaMgAl}_{11}\text{O}_{19}$, *Materials Research Bulletin* 45 (2010) 1506–1508.
- [4] X.Q. Cao, Y.F. Zhang, J.F. Zhang, X.H. Zhong, Y. Wang, H.M. Ma, Z. H. Xu, L.M. He, F. Lu, Failure of the plasma-sprayed coating of lanthanum hexaluminate, *Journal of the European Ceramic Society* 28 (2008) 1979–1986.
- [5] X.Q. Cao, R. Vassen, D. Stoeber, Ceramic materials for thermal barrier coatings, *Journal of the European Ceramic Society* 24 (2004) 1–10.
- [6] L. Maarten, H. ter Heerdt, E. van der Kolk, W.M. Yen, A.M. Srivastava, Vacuum ultraviolet spectroscopy of Pr^{3+} in CaAl_2O_7 , $\text{LaMgAl}_{11}\text{O}_{19}$ and SrLaAlO_4 , *Journal of Luminescence* 100 (2002) 107–113.
- [7] H. Qi, X. Hou, Y. Li, Y. Sun, H. Zhang, J. Wang, Co^{2+} : $\text{LaMgAl}_{11}\text{O}_{19}$ saturable absorber Q-switch for a 1.319 mm Nd^{3+} : YAG laser, *Optics and Laser Technology* 39 (2007) 724–727.
- [8] B.R. Jovanic, B. Viana, High-pressure and optical properties of lanthanum magnesium hexa-aluminate doped with Mn^{2+} (LMA: Mn^{2+}) laser material, *Optics Communications* 282 (2009) 1798–1800.
- [9] Y.H. Wang, Z.G. Liu, J.H. Ouyang, H.Z. Zhi, R.X. Zhu, Preparation and thermophysical properties of $\text{LaMgAl}_{11}\text{O}_{19}$ - $\text{Yb}_3\text{Al}_5\text{O}_{12}$ ceramic composites, *Ceramics International* 37 (2011) 2489–2493.
- [10] F. Laville, A.M. Lejus, Crystal growth and characterization of $\text{LaAl}_{11}\text{O}_{19}$ lanthanum aluminates, *Journal of Crystal Growth* 63 (1983) 426–428.
- [11] M. Gasperin, M.C. Saine, A. Kahn, F. Laville, A.M. Lejus, Influence of M^{2+} ions substitution on the structure of lanthanum hexaaluminates with magnetoplumbite structure, *Journal of Solid State Chemistry* 54 (1984) 61–69.
- [12] A.M. Lejus, F. Laville, J. Théry, Microdureté de monocristaux d'hexaaluminates de lanthanides de type magnetoplumbite, *Materials Research Bulletin* 23 (1988) 913–922.
- [13] V. Singh, R.P.S. Chakradhar, J.L. Rao, H.Y. Kwak, Enhanced blue emission and EPR study of $\text{LaMgAl}_{11}\text{O}_{19}$: Eu phosphors, *Journal of Luminescence* 131 (2011) 247–252.
- [14] B.R. Jovanic, B. Viana, High pressure and the luminescence of $\text{LaMgAl}_{11}\text{O}_{19}$: Cr^{3+} , Nd^{3+} , *Radiation Effects and Defects in Solids* 159 (2004) 241–247.
- [15] P.Y. Jia, M. Yu, J. Lin, Sol-gel deposition and luminescent properties of $\text{LaMgAl}_{11}\text{O}_{19}$: $\text{Ce}^{3+}/\text{Tb}^{3+}$ phosphor films, *Journal of Solid State Chemistry* 178 (2005) 2734–2740.
- [16] V. Singh, S. Watanabe, T.K.G. Rao, H.Y. Kwak, Luminescence and defect centres in Tb^{3+} doped $\text{LaMgAl}_{11}\text{O}_{19}$ phosphors, *Solid State Sciences* 12 (2010) 1981–1987.
- [17] B. Viana, P. Derouineau, J. Barrie, A.M. Lejus, B. Dunn, O. Stafsudd, D. Vivien, Fluorescence of Pr^{3+} and Dy^{3+} in $\text{LaMgAl}_{11}\text{O}_{19}$ single-crystals, *Journal of Physics* 48 (1987) 509–511.
- [18] H.P. You, Y.H. Song, G. Jia, G.Y. Hong, Energy transfer from Tb^{3+} to Mn^{2+} in $\text{LaMgAl}_{11}\text{O}_{19}$: Tb, Mn phosphors, *Optical Materials* 31 (2008) 342–345.
- [19] R.J. Xie, H.T. Hintzen, Optical properties of (oxy) nitride materials: a review, *Journal of the American Ceramic Society* 96 (2013) 665–687.
- [20] M. Zeuner, S. Pagano, W. Schnick, Nitridosilicates and oxonitridosilicates: from ceramic materials to structural and functional diversity, *Angewandte Chemie International Edition* 50 (2011) 7754–7775.
- [21] R.J. Xie, Y.Q. Li, N. Hirosaki, H. Yamamoto, Nitride Phosphors and Solid State Lighting, CRC Press (Taylor and Francis), New York, 2011.
- [22] R.J. Xie, N. Hirosaki, Silicon-based oxynitride and nitride phosphors for white LEDs—a review, *Science and Technology of Advanced Materials* 8 (2007) 588–600.
- [23] A.P. Grosvenor, R.G. Cavell, A. Mar, X-ray photoelectron spectroscopy study of the skutterudites $\text{LaFe}_4\text{Sb}_{12}$, $\text{CeFe}_4\text{Sb}_{12}$, CoSb_3 , and CoP_3 , *Physical Review B* 74 (2006) 125102–125111.
- [24] A.P. Grosvenor, R.G. Cavell, A. Mar, X-ray photoelectron spectroscopy study of rare-earth filled skutterudites $\text{LaFe}_4\text{P}_{12}$ and $\text{CeFe}_4\text{P}_{12}$, *Chemistry of Materials* 18 (2006) 1650–1657.
- [25] C.J. Niu, Y.Q. Jia, X-Ray photoelectron spectra of some bioinorganic complexes of the rare earths with N-acetylalanine, *Spectrochimica Acta Part A* 49 (1993) 947–951.
- [26] D. Briggs, M.P. Seah, Practical Surface Analysis, John Wiley & Sons, Chichester, 1983.
- [27] T.L. Barr., An ESCA study of the termination of the passivation of elemental metals, *Journal of Physical Chemistry* 82 (1978) 1801–1810.
- [28] A.M. Beccaria, G. Poggi, G. Castello, Influence of passive film composition and sea water pressure on resistance to localised corrosion of some stainless steels in sea water, *British Corrosion Journal* 30 (1995) 283–287.
- [29] A.I. Boronin, S.V. Koscheev, G.M. Zhidomirov, XPS and UPS study of oxygen states on silver, *Journal of Electron Spectroscopy* 96 (1998) 43–51.
- [30] L.H. Shen, N. Wang, X. Xiao, Strong orange luminescence from AlN whiskers, *Materials Letters* 94 (2013) 150–153.
- [31] T. Schulz, M. Albrecht, K. Irmscher, C. Hartmann, J. Wollweber, R. Fornari, Ultraviolet luminescence in AlN, *Physica Status Solidi B* 248 (2011) 1513–1518.
- [32] I.A. Weinstein, A.S. Vokhmintsev, D.M. Spiridonov, Thermoluminescence kinetics of oxygen-related centers in AlN single crystals, *Diamond and Related Materials* 25 (2012) 59–62.
- [33] R.A. Youngman, J.H. Harris, Luminescence studies of oxygen-related defects in aluminum nitride, *Journal of the American Ceramic Society* 73 (1990) 3238–3246.
- [34] G.A. Slack, L.J. Schowalter, D. Morelli, J.A. Freitas, Some effects of oxygen impurities on AlN and GaN, *Journal of Crystal Growth* 246 (2002) 287–298.
- [35] S. Schweizer, U. Rogulis, J.M. Spaeth, L. Trinkler, B. Berzina, Investigation of oxygen-related luminescence centres in AlN ceramics, *Physica Status Solidi B* 219 (2000) 171–180.